

(December 21, 1931)

NOMOGRAPHIC CHART FOR USE WITH STEEL MEASURING TAPES

I. Introduction and Mathematical Formulae

The standard test for a 100-foot steel tape at the National Bureau of Standards is made with the tape supported horizontally throughout its length at room temperature under a tension of 10 pounds (for tapes over 100 feet in length a tension of 20 pounds is used). From the length thus observed, the length at 68°F. (20°C.) is computed, assuming a coefficient of thermal expansion of 0.000 006 45 per 1°F. (0.000 011 6 per 1°C.). Other tests are made when requested.

Tapes may be used in the field either under a tension at which they have been standardized in the laboratory, or under the tension which will give the nominal length of the tape, i.e., the tension of accuracy. In the first case corrections must nearly always be made on account of changes from the standard temperature or of changes in the method of support; in the second case no corrections need be made. Using the usual methods of computation it is not easy to calculate the tension of accuracy of a tape at a given temperature when supported at equidistant points. An attempt to remedy this condition is the basis of this discussion.

The length of a tape supported at equidistant points at the same height and held under tension is given with sufficient accuracy by the formula

$$L = L' \left[1 + \frac{P}{AE} + \alpha (t - t_0) - \frac{1}{24} \left(\frac{wd}{P} \right)^2 \right] \quad (1)$$

where

L' = distance between the terminal graduations when the tape is lying flat under no tension at the standard temperature. This is actually never realized,

L = distance between terminal graduations on tape under the given conditions,

P = tension on tape,

A = cross-sectional area of tape,

E = Young's Modulus of Elasticity of tape,

α = coefficient of thermal expansion of tape,

t = temperature,

t_0 = standard temperature,

w = weight of tape per unit length,

d = span or distance between equidistant points of support.

These should be in consistent units: for example all lengths in inches, weights and tensions in pounds, Young's Modulus in pounds per square inch, temperatures in degrees Fahrenheit, and expansion in inches per inch per 1° Fahrenheit.

Here $\frac{L'P}{AE}$ is the stretch under tension, $L'\alpha(t - t_0)$ the elongation under the temperature change, and $\frac{L'}{24} \left(\frac{wd}{P}\right)^2$ the sag correction calculated under the assumption that a parabola is a sufficiently close approximation to the actual catenary.¹

¹ For equation (1) see any standard textbook on surveying, or the following references on the theory of metallic tapes:

Woodward, R.S., On the Measurement of the Base Lines at Holton, Ind., and at St. Albans, W. Va., App. 8, U.S. Coast & Geodetic Survey Report for 1892.

Woodward, R.S., Mathematical Theory of Metallic Tapes, U.S. Coast & Geodetic Survey Report for 1892, App. 8, pp. 480 to 489.

Jaderin, E., On the Measurement of Base Lines with Steel Tapes and with Steel and Brass Wires. (Translated by J. H. Gore), U.S. Coast & Geodetic Survey Report for 1893, App. 5.

Henrici, Prof. O., and Henrici, Capt. E. O., Theory of Tapes in Catenary. Professional Papers No. 1 (New Series), Ordnance Survey of Great Britain, 1912.

Young, A. E., On the Form of a Suspended Wire or Tape, including the Effect of Stiffness, Phil. Mag. 29, p. 96; 1915.

Since all these corrections are small they may be treated as independently additive. Designating the condition of calibration by the subscript (0) and the field conditions by the

... ..
... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

... ..

subscript (1) the tension of accuracy is determined by the equation $L_1 = L_0 =$ nominal length of the tape.

$$L' \left[1 + \frac{P_1}{AE} + \alpha (t_1 - t_0) - \frac{1}{24} \left(\frac{wd}{P_1} \right)^2 \right] = L' \left[1 + \frac{P_0}{AE} \right] \quad (2)$$

where

P_0 is the tension of accuracy of the tape at standard temperature t_0 when supported throughout

and

P_1 is the tension of accuracy of the tape at temperature t_1 when supported at equidistant points at a distance d apart.

After dividing by L_1 and rearranging one obtains the cubic equation

$$P_1^3 - P_x P_1^2 - K = 0 \quad (3)$$

where

$$K = \frac{AE w^2 d^2}{24}$$

and

$$P_x = P_0 - AE\alpha(t_1 - t_0)$$

(Here P_x is the tension of accuracy of the tape when supported throughout at temperature t_1)

This equation (3) may readily be solved for the tension of accuracy P_1 by any of the usual methods for the numerical solution of algebraic equations but may more readily be handled in this case by a nomographic chart, as suggested to the author by Dr. L. B. Tuckerman.

The equation is in Soreau's² canonical form IV_0 permitting

²Soreau, Nomographie, pp. 172, 174, 184 and 192 Chiron, Paris, 1921.

parallel linear scales of $\frac{AE w^2 d^2}{24}$ and $P_0 - AE\alpha(t_1 - t_0)$ with a curved functional scale of P_1 . The multiplication of

1870
No. 100
1000

1000
1000
1000

1000
1000

1000
1000
1000

1000
1000

1000
1000
1000

1000
1000

1000
1000

1000
1000

1000
1000

$AE \propto (t_1 - t_0)$ permits of two parallel linear scales of $AE \propto (t_1 - t_0)$ and $AE \propto (t_1 - t_0)$ with an inclined projective scale of $(t_1 - t_0)$. The subtraction of $AE \propto (t_1 - t_0)$ from P_0 permits of three parallel linear scales of $AE \propto (t_1 - t_0)$, P_0 , and $P_0 - AE \propto (t_1 - t_0)$. Since both the scales of $AE \propto (t_1 - t_0)$ and $P_0 - AE \propto (t_1 - t_0)$ are linear the three nomograms may readily be combined in one as shown in Figure 1.

II. Experimental Work

a. Verification of the Tension of Accuracy Formula.

Experimental determinations of the tension of accuracy were made using a group of 45 tapes, 100 feet in length, which were being studied for some of their physical characteristics. The tension of accuracy was determined experimentally for each of the 45 tapes, when supported at the 0 and 100-foot points, at four or more temperatures between 50° and 95°F. In making these observations special precautions were taken to obtain an accuracy of 0.1 pound. The observed values of tension of accuracy were found to agree with the computed values to within 0.1 to 0.3 pound.

b. Constants to be Used in the Formula.

1. Coefficient of thermal expansion.

The coefficient of thermal expansion of steel tapes has been assumed at the National Bureau of Standards to be 0.000 006 45 per degree Fahrenheit (0.000 011 6 per degree Centigrade), this being the best value obtained by experiment, and one from which the variations have been found to be practically negligible. This value was checked in this investigation as being applicable to these 45 tapes, some of which were made of ordinary tape steel, and others of stainless steel. The group of tapes having the maximum deviation from the value given above has coefficients so near this adopted value that an error of less than 0.0005 foot in 100 feet for a change in temperature of 30°F, is made if this nominal value is used instead of the experimentally determined value.

2. Young's Modulus of Elasticity

Young's Modulus of elasticity may be assumed as 28.0×10^6 pounds per square inch. This is the mean value, experimentally determined in this investigation, and is in agreement with the results of other tests of tapes at the Bureau of Standards. This mean value may for all practical purposes be used for any steel

tape because the experiments just referred to indicate that the maximum error introduced by this assumption in using a 100-foot tape with a change in tension of 15 pounds would only be about 0.0005 foot.

Because of the difficulty in obtaining a sufficiently precise value for the cross-sectional area in many cases, it is often preferable when using this chart to determine the value for the product AE by measurements of change of length made on the tape when supported throughout at constant temperature at two tensions differing by 15 pounds or more, since AE is equal to $\frac{(P_2 - P_1) L}{\Delta L}$ where ΔL is the change in the length L when the tension is changed from P_1 to P_2 .

3. Correction for Sag

The sag correction was checked experimentally and found to be correct for the purpose of this "tension of accuracy" formula to better than 0.001 foot.

III. Nomographic Chart

A nomographic chart was constructed which was applicable to any of the 45 tapes tested in the above research. Nearly all of the types and sizes of 100-foot steel tapes manufactured and used in the United States were represented in this research. The chart is applicable to tapes of any length within the range of the scales of the nomogram.

Other nomograms may be drawn for tapes whose constants do not come within the scales on this nomogram.

Referring to the nomogram, Figure 1, the values for the 45 tapes of $AE \propto$, axis "A", varied from 0.3 to 0.9. The inclined projective scale of $(t_1 - t_0)$, "B", is calibrated in terms of the observed temperature, t_1 , from 30 to 110°F. The numerical value of the product $AE \propto$ and $(t_1 - t_0)$ is not necessary, and axis "C" is a dummy axis. While the value, P_0 , axis "D", is generally positive, it is made for the sake of uniformity in units from -40 to 40 pounds. (For purposes of computation the value of P_0 may theoretically be negative for some tapes.) Axis "E" is a dummy axis, but in case the value P_x is known at the observed temperature, t_1 , it is calibrated in pounds from -40 to 40. Axis "G" is calibrated in units between 0 and 20,000, and the tension of accuracy curve "F" is given in units between 4 and 40 pounds, which tensions are the approximate limiting usable values for 100-foot tapes.

1117
1118
1119
1120
1121
1122
1123
1124
1125
1126
1127
1128
1129
1130
1131
1132
1133
1134
1135
1136
1137
1138
1139
1140
1141
1142
1143
1144
1145
1146
1147
1148
1149
1150
1151
1152
1153
1154
1155
1156
1157
1158
1159
1160
1161
1162
1163
1164
1165
1166
1167
1168
1169
1170
1171
1172
1173
1174
1175
1176
1177
1178
1179
1180
1181
1182
1183
1184
1185
1186
1187
1188
1189
1190
1191
1192
1193
1194
1195
1196
1197
1198
1199
1200

1201
1202
1203
1204
1205
1206
1207
1208
1209
1210
1211
1212
1213
1214
1215
1216
1217
1218
1219
1220
1221
1222
1223
1224
1225
1226
1227
1228
1229
1230
1231
1232
1233
1234
1235
1236
1237
1238
1239
1240
1241
1242
1243
1244
1245
1246
1247
1248
1249
1250
1251
1252
1253
1254
1255
1256
1257
1258
1259
1260
1261
1262
1263
1264
1265
1266
1267
1268
1269
1270
1271
1272
1273
1274
1275
1276
1277
1278
1279
1280
1281
1282
1283
1284
1285
1286
1287
1288
1289
1290
1291
1292
1293
1294
1295
1296
1297
1298
1299
1300

1301
1302
1303
1304
1305
1306
1307
1308
1309
1310
1311
1312
1313
1314
1315
1316
1317
1318
1319
1320
1321
1322
1323
1324
1325
1326
1327
1328
1329
1330
1331
1332
1333
1334
1335
1336
1337
1338
1339
1340
1341
1342
1343
1344
1345
1346
1347
1348
1349
1350
1351
1352
1353
1354
1355
1356
1357
1358
1359
1360
1361
1362
1363
1364
1365
1366
1367
1368
1369
1370
1371
1372
1373
1374
1375
1376
1377
1378
1379
1380
1381
1382
1383
1384
1385
1386
1387
1388
1389
1390
1391
1392
1393
1394
1395
1396
1397
1398
1399
1400

1401
1402
1403
1404
1405
1406
1407
1408
1409
1410
1411
1412
1413
1414
1415
1416
1417
1418
1419
1420
1421
1422
1423
1424
1425
1426
1427
1428
1429
1430
1431
1432
1433
1434
1435
1436
1437
1438
1439
1440
1441
1442
1443
1444
1445
1446
1447
1448
1449
1450
1451
1452
1453
1454
1455
1456
1457
1458
1459
1460
1461
1462
1463
1464
1465
1466
1467
1468
1469
1470
1471
1472
1473
1474
1475
1476
1477
1478
1479
1480
1481
1482
1483
1484
1485
1486
1487
1488
1489
1490
1491
1492
1493
1494
1495
1496
1497
1498
1499
1500

1501
1502
1503
1504
1505
1506
1507
1508
1509
1510
1511
1512
1513
1514
1515
1516
1517
1518
1519
1520
1521
1522
1523
1524
1525
1526
1527
1528
1529
1530
1531
1532
1533
1534
1535
1536
1537
1538
1539
1540
1541
1542
1543
1544
1545
1546
1547
1548
1549
1550
1551
1552
1553
1554
1555
1556
1557
1558
1559
1560
1561
1562
1563
1564
1565
1566
1567
1568
1569
1570
1571
1572
1573
1574
1575
1576
1577
1578
1579
1580
1581
1582
1583
1584
1585
1586
1587
1588
1589
1590
1591
1592
1593
1594
1595
1596
1597
1598
1599
1600

The terms used in the nomogram should be stated in the following consistent units:-

A = Young's modulus of elasticity in pounds per sq. in.

E = cross-sectional area of tape in sq. in.

Note: It is advised that AE be determined from

$$\frac{(P_2 - P_1) L}{\Delta L} \quad (\text{See Sect. IIb - 2, page 4})$$

α = coefficient of thermal expansion (.00000645 per °F.)

t_0 = standard temperature, 68°F.

t_1 = observed temperature in °F.

w = weight of tape in pounds per foot

d = distance between equidistant points of support in feet.

P_0 = tension in pounds at which tape has its nominal length when supported throughout at standard temperature.

P_1 = tension in pounds to be applied to tape when used at the observed temperature, t_1 , and supported at equidistant points at a distance d apart, in order that the tape will have its nominal length.

These quantities should be determined as accurately as possible.

To find the tension of accuracy for a tape, place a straight-edge on the point representing the constant $AE\alpha$, axis "A", and on the point representing the observed temperature t_1 , inclined scale "B". The intersection of the straight-edge with the dummy axis "C" is noted. The straight-edge is then placed on this point and on the point representing the value P_0 , axis "D".

The point where the straight-edge intersects axis "E" is determined. Place the straight-edge on this point and the point representing the constant $\frac{AE w^2 d^2}{24}$, axis "G". The point where

the straight-edge intersects the curve "F" determines the tension to apply to the tape under the given method of support and at the observed temperature t_1 .

It should be noted that the constants $AE\alpha$, P_0 , and $\frac{AE w^2 d^2}{24}$

are constants of the tape, independent of the conditions of its use and can be permanently marked on the chart for each tape, in the office, in preparation for use of the chart in the field.

IV. Conclusions

A mathematical formula is given with a nomographic chart enabling one to determine readily the tension of accuracy of a

... ..
... ..
... ..
... ..

... ..
... ..
... ..
... ..

... ..
... ..
... ..
... ..

... ..
... ..
... ..
... ..

... ..
... ..
... ..
... ..

steel tape as used under field conditions.

Experimental verification of the formula is given with information as to the values of the several constants to be used.

NOMOGRAM FOR STEEL TAPES

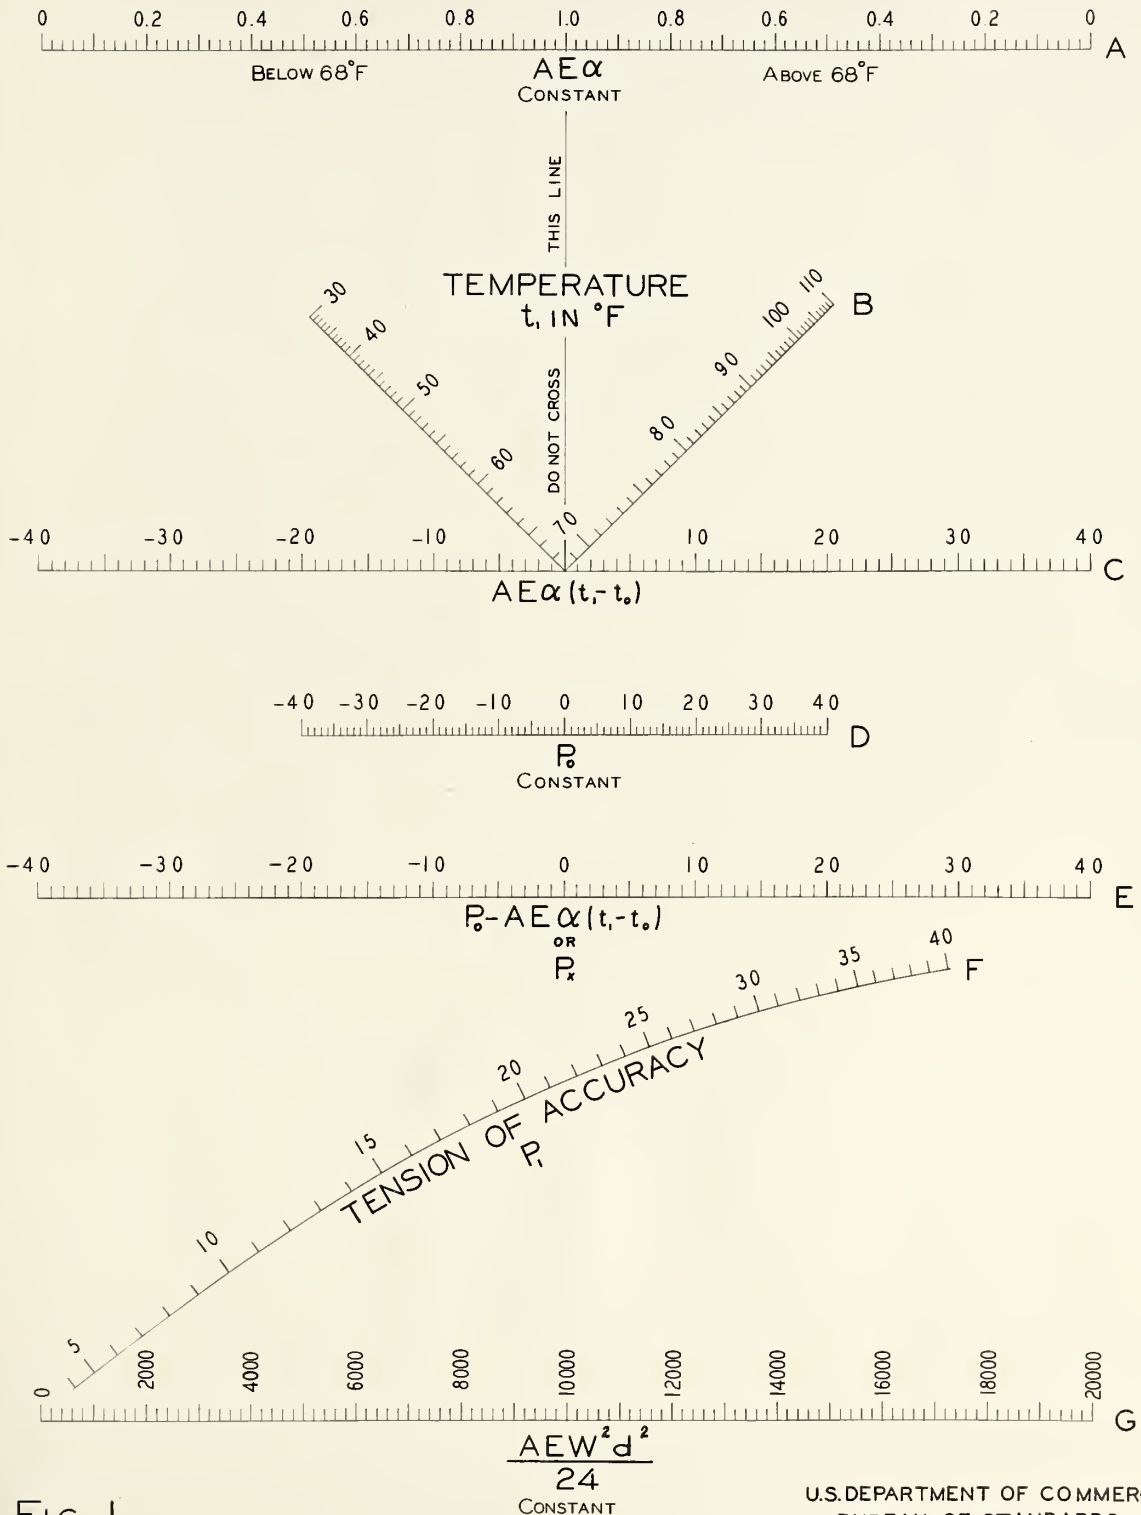


FIG. 1.

