

Electrode Function (pH Response), Hygroscopicity, and Chemical Durability of Soda-Lead Oxide-Silica Glasses

By Donald Hubbard, Mason H. Black, and Gerald F. Rynders

The pH response, hygroscopicity, and chemical durability of a series of $\text{Na}_2\text{O-PbO-SiO}_2$ (soda-lead oxide-silica) glasses have been investigated. The results obtained are in complete accord with the data previously published for a series of $\text{Na}_2\text{O-CaO-SiO}_2$ glasses and show that: 1. Glasses of very low hygroscopicity yield electrodes whose pH responses fall appreciably below the theoretical 59 millivolts per pH at 25° C; 2. electrodes prepared from glasses of poor chemical durability also fail to develop the full theoretical voltage.

When the approximate compositions at which changes in the primary phase appear for the $\text{Na}_2\text{O-PbO-SiO}_2$ system are superimposed upon the pH response and chemical durability curves, the marked changes in these properties appear to reflect some of the critical compositions of the phase equilibrium diagram.

The chemical durability data obtained by the interferometer procedure indicate that the property of swelling in acid solutions is much more universal for silicate glasses than previously realized.

I. Introduction

All glasses, when immersed in aqueous solutions, develop an electromotive force [1 to 6],¹ which in some cases serves as a reliable indicator of the hydrogen ion activity of the solution in quantitative accord with the prediction of the Nernst equation, $\Delta E = 0.000198 T \Delta \text{pH}$ [7, 8]. Nevertheless, many glasses, show little or no pH response, whereas still others give the theoretical increment of voltage over only a limited pH range [1, 9 to 11]. From this apparent chaotic pH performance of glasses of different compositions have emerged certain definite characteristics of behavior, as follows:

1. Glasses of very low hygroscopicity or low water content produce electrodes that fail to develop the theoretical 59 mv per pH at 25° C [1, 6, 12, 13].

2. Electrodes prepared from glasses of very poor chemical durability also fail to develop the full theoretical voltage [13, 14].

3. Only those glasses having both adequate hygroscopicity and uniform chemical durability over an extended pH range produce electrodes that approximate the correct pH response [7, 12, 13, 15].

4. Voltage departures (errors) for electrodes prepared from pH responsive glasses occur in those solutions that cause an appreciable change in the attack on the glass, such as strong alkaline and hydrofluoric acid solutions [5, 13, 15, 17].

5. Voltage departures that appear in solutions of a dehydrating nature, such as strong H_2SO_4 and acetic acid [11], as well as in nonaqueous solutions such as ethanol, are accompanied by detectable changes in the surface of the glass, notably the repression of swelling [6 (p. 81), 16, 17].

In the present investigation, the hygroscopicity, chemical durability, and pH response of a series of $\text{Na}_2\text{O-PbO-SiO}_2$ glasses were studied for the purpose of determining if the above generalizations are valid for this series, and also to observe if the above properties reflect any of the critical compositions of the phase equilibrium diagram.

II. Experimental Procedure

The hygroscopicity data were obtained by weighing the water "sorbed" [18] by powdered samples of the glasses exposed for 1- and 2-hr periods, to the high humidity maintained by a saturated solution of $\text{CaSO}_4 \cdot 2\text{H}_2\text{O}$ at 25° C [12, 13]. The samples consisted of approximately 1.5 g of the powdered glass that passed through a Tyler standard 150 mesh sieve.² In order to make a legitimate comparison between glasses differing greatly in density, the hygroscopicity values are reported as milligrams of water sorbed per cubic centimeter, that is, water sorbed times the density of the glass divided by the weight of the sample.

The chemical durability determinations were made by the interferometer procedure [15, 19, 20], which consists of determining the displacement of fringes by the alteration of the surface of the experimental glass after partial immersion in the test solution. Swelling is plotted in all figures as negative attack. To make the results comparable with previous publications [13, 14, 15, 17, 21, 22] the exposures were made at $80^\circ \pm 0.2^\circ \text{C}$ to Britton-Robinson universal buffer solutions [23] ranging from pH 2 to 11.8. All values are reported for a 6-hr period, although the durabilities for many of the glasses were so poor that exposure times had to be reduced in order to keep the attack values within the limitations of the interferometer and preserve the optical quality of the surfaces. In one extreme case it was necessary to reduce the time of exposure to 5 secs.

The experimental electrodes were made by blowing a small thin-walled bulb on the end of tubing, which was drawn from the melts at the time of pouring. The inner electrical connection was established by filling the bulb and a portion of the stem with mercury [2, 24]. The emf measurements were made at room temperature with a Beckman pH meter, model G, using a well-conditioned Beckman glass electrode

¹ Figures in brackets indicate the literature references at the end of this paper.

² No. 140 sieve of U. S. Standard Sieve Series.

as a reference electrode. The voltage difference between the reference and experimental electrodes obtained in the buffer of pH 2 was taken as the zero departure. This reference point, for some of the glasses, proved to be an unfortunate choice, as the readings were more unsteady in this buffer than at other acid pH values.³ The data for pH response (mv per pH) were calculated from the voltage readings at pH 4.1 and 8.2.

The voltage data presented in this paper generally represent the best performance recorded for an electrode from a given glass. These optimum values were obtained for periods ranging from a few minutes

³ This unsteady "zero" voltage feature was undoubtedly associated with the chemical durability of the glass. Differences in appearance of the specimens and tarnishing of the surface upon exposure to the acid buffers were evident, although surface alteration could not be definitely demonstrated by the interferometer.

TABLE I. Hygroscopicity (water sorbed), pH response and chemical durability of some Na₂O-PbO-SiO₂ glasses

No.	Glasses			Water sorbed for—		Voltage departure at pH—						pH response, pH 4.1 to 8.1	Chemical durability (attack) at pH—					
	Na ₂ O	PbO	SiO ₂	1 hr	2 hr	2.0	4.1	6.0	8.2	10.2	11.8		2.0	4.1	6.0	8.2	10.2	11.8
	%	%	%	mg/cm ³	mg/cm ³	mv	mv	mv	mv	mv	mv	mv per pH	Fringes	Fringes	Fringes	Fringes	Fringes	Fringes
1	10	10	80	37	69	0	2	4	9	20	46	57+	*ND	ND	ND	ND	(?)	2
2	15	5	80	62	105	0	0	0	0	0	-8	59	1/10 swell	1/10 swell	D swell	D swell	D swell	3-
3	20	0	80	108	256	0	10	17	25	37	49	55	1 1/2 swell	2 swell	2 swell	2 swell	1 swell	3+
4	10	20	70	30	62	0	0	2	12	26	56	56	ND	ND	ND	ND	1/10+	2 1/2
5	15	15	70	52	99	0	0	1	2	5	11	58+	1/10 swell	D swell	D+swell	D	D	3
6	20	10	70	81	189	0	2	5	15	26	37	56	1+swell	1+swell	1+swell	1+swell	D	4 1/2
7	25	5	70	120	250	0	5	18	30	45	52	53-	18 swell	18 swell	18 swell	12 swell	12 swell	96
8	30	0	70	186	-----	0	35	117	221	315	395	13	72 swell	72 swell	72 swell	72 swell	18 swell	252
9	5	35	60	20	29	(b)	(b)	(b)	(b)	(b)	(b)	-----	ND	ND	ND	ND	1/10	2+
10	10	30	60	33	59	0	0	3	12	22	58	56	ND	ND	ND	ND	1/10	4+
11	15	25	60	51	95	0	0	0	0	5	17	59	1/10 swell	1/10 swell	1/10+swell	1/10+swell	1/10+	6-
12	20	20	60	75	163	0	0	0	1	15	40	59-	1/4 swell	1/4 swell	1/4 swell	1/4 swell	D+	7
13	25	15	60	113	228	0	-3	15	45	90	150	49	15 swell	18 swell	18 swell	18 swell	*SC, swell	12
14	30	10	60	208	300	0	-46	22	111	186	282	20	180 swell	180 swell	180 swell	(?)	(?)	50
15	40	-----	60	>300	-----	0	95	180	282	365	460	13	-----	-----	-----	Failed to maintain polish.	-----	-----
16	5	45	50	20	32	(b)	(b)	(b)	(b)	(b)	(b)	-----	D	ND	ND	D	1/10+	3-
17	10	40	50	34	59	0	0	1	1	43	68	57	D swell	1/10 swell	1/10 swell	1 1/2	1 1/2	5+
18	15	35	50	50	102	0	0	5	13	41	62	56	1/2 swell	1/2 swell	1/2 swell	2	1 1/2	7+
19	20	30	50	72	154	0	2	7	24	68	126	54	15 swell	15 swell	10 swell	1 swell	1 1/2	10
20	25	25	50	118	228	0	-33	-2	33	85	156	42	72 swell	72 swell	60 swell	50 swell	10 swell	48
21	30	20	50	219	329	0	-25	51	149	240	-----	15	450 swell	450 swell	720 swell	720 swell	10 swell	360
22	5	55	40	20	39	(b)	(b)	(b)	(b)	(b)	(b)	-----	1/10 swell	1/10 swell	1/10 swell	2-	3/4	6 1/2
23	10	50	40	33	68	0	0	3	13	42	7	56	1/10	1/10	D	1 1/2 swell	1+	9 1/2
24	15	45	40	49	108	0	0	8	20	54	96	54	1	1 1/2+	1 1/2+	4	1 1/2	15
25	20	40	40	75	156	0	-18	-14	16	89	187	51	4 1/2 swell	9 swell	1 1/2	9	2 1/2+	24
26	25	35	40	127	280	0	-27	38	132	236	358	20	180 swell	180 swell	54 swell	54 swell	>2,160 swell	>50
27	30	30	40	300	515	(d)	(d)	(d)	(d)	(d)	(d)	<15	4,320 swell	4,320 swell	4,320 swell	>2,160 swell	2,160	(?)
28	0	70	30	14	17	(b)	(b)	(b)	(b)	(b)	(b)	-----	1/10	1/4+swell	1/2 swell	4	3-	9+
29	5	65	30	22	50	(b)	(b)	(b)	(b)	(b)	(b)	-----	2-	3/4	1 1/2 swell	3+	D+	12
30	10	60	30	37	92	0	0	2	18	29	7	55	3+	3- swell	3- swell	15-	15	18
31	15	55	30	65	130	0	27	58	78	107	67	47	1 1/2	3	3 swell	15	15	18
32	0	80	20	13	16	(b)	(b)	(b)	(b)	(b)	(b)	0	3-	3+swell	3 swell	6 swell	3-swell	24-
33	5	75	20	30	68	0	-26	-28	13	53	107	49	3-	3 swell	3 swell	3-swell	3	54
34	12	0	88	52	104	0	10	18	32	45	54	55	D swell	D swell	D	(?)	(?)	3
35	14	0	86	61	124	0	2	4	6	8	10	58	1/10 swell	1/10 swell	1/10 swell	D	(?)	2-
36	16	0	84	83	178	0	3	7	7	9	11	58	1/4+swell	1/4+swell	1/4+swell	1/10 swell	(?)	1 1/4
37	18	0	82	96	220	0	10	18	18	26	34	57	1/2 swell	1/2 swell	1/2 swell	1/2 swell	(?)	2 1/2
3	20	0	80	108	256	0	10	17	25	37	49	55	1 1/2 swell	2 swell	2 swell	2 swell	1 swell	3+
38	22	0	78	112	265	0	10	18	28	39	49	55	2 1/2 swell	6-swell	6-swell	6-swell	(?)	6
39	24	0	76	127	270	0	9	24	32	49	52	53	12 swell	12 swell	12 swell	6-swell	2 1/2 swell	30-
40	0	65	35	14	21	(b)	(b)	(b)	(b)	(b)	(b)	-----	1/10 swell	3 swell	1/10 swell	3-swell	D	9-
41	0	70	30	14	17	(b)	(b)	(b)	(b)	(b)	(b)	-----	1/4	1/4+swell	1/2 swell	SC	3-	9+
42	0	75	25	12	14	(b)	(b)	(b)	(b)	(b)	(b)	-----	3-	18 swell	3-swell	3-swell	6	18
43	0	78.8	21.2	12	15	(b)	(b)	(b)	(b)	(b)	(b)	-----	9	9 swell	3-swell	3-swell	3-	21
44	0	80	20	13	16	(b)	(b)	(b)	(b)	(b)	(b)	-----	3-	3+swell	3 swell	6 swell	3-swell	24
45	0	84.6	15.4	12	15	(b)	(b)	(b)	(b)	(b)	(b)	-----	3-	3-swell	3 swell	3 swell	3-swell	60
46	0	88.1	11.9	13	22	(b)	(b)	(b)	(b)	(b)	(b)	-----	White and gelatinous.	3-swell	3-swell	2 swell	3-	72
47	Corning 015			59	138	0	0	0	0	0	3	59	1/10-swell	1/10-swell	1/10-swell	SC	1/4+	2

* D, Detectable; ND, not detectable.

b No definite pH response.

* The voltage departure and pH response of electrodes prepared from glass 12:0:88 are not in accord with the hygroscopicity and chemical durability values of this glass. However, difficulty was encountered in melting the batch, and the tubes obtained consisted of stringy glass, indicating incipient devitrification.

* SC, Surface cut.

d Tube disintegrated.

after the electrodes were prepared, for some glasses, to several days for others, depending on the life span of the electrodes as dictated by the chemical durability of the glasses.

The glasses investigated were from a series furnished by F. W. Glaze and J. M. Florence as a part of their general study of infrared transmittance of glasses [25, 26]. The compositions of these glasses were computed from the batch and are identified throughout the text of this paper as weight percent in the ratio of Na₂O:PbO:SiO₂.

III. Results and Discussion

Typical data for hygroscopicity, chemical durability, voltage departure, and pH response for the Na₂O-PbO-SiO₂ glasses are listed in table 1.

1. Hygroscopicity and pH Response

Figure 1 illustrates the results obtained upon plotting the pH response of these glasses against the hygroscopicity. As was the case for the Na_2O - CaO - SiO_2 series [13], these glasses also fall into distinct family groups of equal percentage of SiO_2 . The curves for each family in which sufficient members could be prepared without devitrification passed through a region of optimum performance. Electrodes from the glasses of very low hygroscopicity gave little or no pH response, while those of intermediate hygroscopicity more nearly approached the theoretical. All glasses to the right of the optimum showed a falling off in pH function, which was accompanied by a progressive decrease in chemical durability (table 1, figs. 2 to 15, incl.) with increasing hygroscopicity. Thus, the suggestion that a low pH response might be used as an indicator of serviceability of optical glasses [27] must be accepted with reservations, because only the glasses of low pH response and low hygroscopicity possess any degree of acceptable serviceability, whereas those of low pH response and high hygroscopicity are accompanied by poor chemical durability and poor serviceability.

2. Chemical Durability and Voltage Departure

A visual comparison of the chemical durability and voltage departure characteristics of those family groups of glasses having like SiO_2 content shown in figure 1 can be obtained from inspection of figures 2 to 8 in which the above properties have been plotted over an extended pH range. In some cases the correlation of voltage departure with the chemical durability may be confusing or even appear contradictory, but if one keeps in mind that low hygroscopicity as well as poor chemical durability contributes to voltage departures from the theoretical, order is established from the apparent chaos. For example, in the family for 80 percent of SiO_2 (fig. 2) the member 15:5:80⁴ more nearly approaches the hygroscopicity and chemical durability characteristics of Corning 015 [6, 29] than any of the others, and at the same time its voltage characteristics are the best of the 80 percent SiO_2 group. The large voltage departures for glass 20:0:80 is due to the inferior durability compared to 015, whereas the large departures for glass 10:10:80 results from its low hygroscopicity.

For the family of 70 percent of SiO_2 (fig. 3), the glass 15:15:70 has the best voltage characteristics of the group. Its hygroscopicity and chemical durability characteristics also more nearly duplicate 015 than do any of the other members studied. Glass 10:20:70 has much lower hygroscopicity than 015, while the remaining members have poorer chemical durabilities over the entire pH range.

The same qualitative conditions prevail for the 60 percent SiO_2 family (fig. 4), in which glass 15:25:60

⁴A glance at fig. 2 shows an apparent discrepancy between the voltage departure and the chemical durability value at pH 11.8 for glasses 15:5:80 and 015. However, there is no reason to suppose that the increment of voltage departure per unit of attack for the soda-lead-silica glasses would be the same as for that of the soda-lime-silica system.

has the least voltage departure and at the same time, its hygroscopicity and chemical durability characteristics more nearly approach 015 than do any of the other members of this group. The members with low hygroscopicity have voltage departures in accord with their respective water-sorbing capacities. The other members having poorer chemical durabilities than 015 have voltage departures that are qualitatively in the same order as their durabilities.

None of the glasses from the 50 percent SiO_2 (fig. 5) family gave satisfactory voltages, but their relative order of performance can be readily ascertained by a glance at their hygroscopicity and chemical durability characteristics. Some of the chemical durability curves for this family group exhibited an abnormal attack at pH 8 with some improvement at pH 10, followed in turn by vigorous attack at pH 11.8. The same feature is exhibited to a more exaggerated degree for the 40 percent SiO_2 series (fig. 6). For the 30 percent SiO_2 group, the same durability characteristics persist, although in a somewhat confused fashion (fig. 7). This particular type of chemical durability curve has been previously reported for some optical glasses [28].

Several of the electrodes whose voltage departure curves are shown in figures 4, 5, 6, and 8 exhibited large negative departures in the acid range [11].

The emf behavior of the glasses for the families 40 percent, 30 percent, and 20 percent of SiO_2 is in no case in accord with the straight-line relation of the Nernst equation. The glasses of very low hygroscopicity 5:55:40, 0:70:30, 5:65:30, and 0:80:20 failed to develop any definite pH response. The remaining glasses gave erratic electrode performance to accompany their erratic chemical durability curves. The dashed lines for the voltage departure for glasses such as 5:55:40 and 30:30:40 in figure 6 and for other glasses in figures 4, 5, 7, and 8 are included merely to emphasize that glasses having very low hygroscopicity and those at the other extreme having such high hygroscopicity values and poor chemical durability as to behave as punctured electrodes, approach the theoretical limiting voltage for an electrode possessing no hydrogen electrode function [14].

Such glasses as 5:65:30 and 5:75:20 (table 1, and figs. 7 and 8) serve well to illustrate that low hygroscopicity is not an indicator of good chemical durability. These glasses of low hygroscopicity and poor chemical durability maintain clear surfaces in air, but tarnish rapidly in the buffer solutions.

None of the glasses containing only lead oxide and silica had sufficient hygroscopicity to produce electrodes showing any pH function (table 1).

The behavior of a limited number of glasses with 0 percent of lead oxide is included in table 1 for comparison. However, as but two of these (20:0:80 and 30:0:70) fit into the family groups, a discussion of these glasses will be postponed to a later publication on the Na_2O - K_2O - SiO_2 system. It is of interest to note that the pH response of electrodes prepared from glass 12:0:88 was less than that expected from the hygroscopicity and chemical durability values. This is not surprising, as difficulty was encountered

in melting the batch, and the tubes obtained consisted of stringy, partially crystallized glass [29].

3. Effect of Composition on Hygroscopicity, Chemical Durability, and pH Response

To further emphasize the orderly interrelation between the hygroscopicity, chemical durability, and voltage performance of the $\text{Na}_2\text{O-PbO-SiO}_2$ glasses, these properties were plotted against the PbO content for each family in figures 9 to 15. From the hygroscopicity curves, it is evident that all glasses having low water "sorption" properties fail to develop the full theoretical pH response.

The chemical durability curves presented are for the extremes of pH studied, namely pH 2 and 11.8. These curves illustrate the marked difference in chemical durability behavior for glasses in acid and basic solutions, with swelling predominating in the acid pH range and solution occurring at high alkalinity. The divergence of these curves serves to emphasize the compositions at which marked durability differences appear. Further, a glance at the pH response curves reveals that the hydrogen electrode function of the glasses starts declining at the same compositions at which the chemical durabilities show a marked change.

The question always arises, do the chemical or physical properties of a series of glasses reflect any of the critical compositions of the phase-equilibrium diagram? In figures 9 to 14, dashed lines are drawn near the compositions at which a change of primary phase occurs [30]. In figure 10 a sharp change in the chemical durability of the series appears between the successive glass members, one of which falls in the composition range where $\text{Na}_2\text{O} \cdot 2\text{SiO}_2$ is the primary phase, and the other in which SiO_2 becomes the primary phase. A similar correspondence appears for the pH response-composition curve in figure 10. The same features seem to be indicated in figures 11 and 12. The pH response of the electrode prepared from the glass of 20 percent of PbO in figure 11 appears to be "too good" for convincing agreement. A comparison of the durability data for this glass with other glasses of table 1 implies that a lower pH response from this glass might well be expected. The cross sections of the phase-equilibrium diagram for the data presented in figures 13 and 14 are complicated and the experimental data inadequate for specific conclusions, yet the over-all picture is one of correspondence to the major composition changes. Figure 15 indicates that the region of high percentages of PbO is not a good one to explore for glasses having satisfactory pH response characteristics.

An over-all picture of the hygroscopicity versus composition for the $\text{Na}_2\text{O-PbO-SiO}_2$ glasses is presented in the ternary diagram, figure 16. The compositions of equal hygroscopicity (isosorbs) were obtained by interpolation of the observed data. The glass compositions that gave electrodes that developed pH functions as high as 56 mv/pH between pH 4 and 8 are included in the shaded area,

while those glasses that produced electrodes developing the full 59 mv/pH are connected by a heavy dashed line. The glasses of higher Na_2O content and higher hygroscopicity gave electrodes that fell appreciably below the theoretical voltage and were also short-lived. It appears that the $\text{Na}_2\text{O-PbO-SiO}_2$ glasses fall into the same three groups that were characteristic of the $\text{Na}_2\text{O-CaO-SiO}_2$ series [13]: A, glasses that are too "dry" for successful electrodes; B, glasses that produce successful electrodes; and C, glasses having poor chemical durability, which are too "wet". Actually, the area B is also very much reduced because of poor durability of its members.

IV. Conclusions

The $\text{Na}_2\text{O-PbO-SiO}_2$ series of glasses appear to follow the generalizations for the hydrogen electrode behavior of glasses as outlined in the introduction of this report. All the members having very low hygroscopicity gave electrodes that failed to develop the theoretical voltage predictable from the Nernst equation at room temperatures. Likewise, the electrodes from glasses of very poor chemical durability failed to develop the full theoretical voltage. Although it is improbable that the best possible of the $\text{Na}_2\text{O-PbO-SiO}_2$ glasses for pH measurement were included in this series, it is obvious that those members that most nearly approached the hygroscopicity and chemical durability characteristics of Corning 015 most nearly approached the ideal hydrogen electrode performance at 25° C. Poor chemical durability in the alkaline range, even for the best glasses produced, is one of the major factors limiting their usefulness.

Most of the durability measurements reported are qualitative. They are of interest in demonstrating the initial alteration of glass surfaces during attack by aqueous solutions, especially for the acid buffers in which many of the glasses exhibited a rapid rate of swelling. The pH-response and chemical-durability curves appear to reflect some of the critical compositions of the phase equilibrium diagram for the $\text{Na}_2\text{O-PbO-SiO}_2$ system.

V. References

- [1] M. Cremer, On the causes of the electromotive properties of tissue and a discussion of polyphase electric cells, *Z. Biol.* **47**, 562 (1906).
- [2] F. Haber and Z. Klemensiewicz, On electrical interfacial potentials, *Z. physik. Chem.* **67**, 385 (1909).
- [3] G. Borelius, Interfacial potentials of solutions in contact with insulators, *Ann. physik.* [4] **45**, 929 (1914).
- [4] H. Freundlich and Rona, The relation between electrokinetic potential pressure and the electric force at phase interfaces, *Sitz. preuss. Akad. Wiss.* **20**, 397 (1920).
- [5] W. S. Hughes, The potential difference between glass and electrolytes in contact with glass, *J. Am. Chem. Soc.* **44**, 2860 (1922).
- [6] M. Dole, *Glass electrode* (John Wiley & Sons, Inc., New York, N. Y., 1941).
- [7] D. A. MacInnes and M. Dole, The behavior of glass electrodes of different compositions, *J. Am. Chem. Soc.* **52**, 29 (1930).

- [8] George A. Perley, Glasses for measurement of pH, *Anal. Chem.* **21**, 394 (1949); U. S. Patent 2,444,845 (1948).
- [9] B. Lengyel and E. Blum, The behavior of the glass electrode in connection with its chemical composition, *Trans. Faraday Soc.* **30**, 461 (1934).
- [10] W. E. L. Brown, The measurement of hydrogen-ion concentration with glass electrodes, *J. Sci. Instr.* **2**, 12 (1924).
- [11] D. A. MacInnes and D. Belcher, Further studies of the glass electrode, *J. Am. Chem. Soc.* **53**, 3315 (1931).
- [12] Donald Hubbard, Hygroscopicity of optical glasses as an indicator of serviceability, *J. Research NBS* **36**, 365 (1946) RP1706.
- [13] Donald Hubbard, Given W. Cleek, and Gerald F. Rynders, Electrode Function (pH response), hygroscopicity, and chemical durability of $\text{Na}_2\text{O-CaO-SiO}_2$ glasses, *J. Research NBS* **45**, 247 (1950) RP2076.
- [14] Gerald F. Rynders, Oscar H. Grauer and Donald Hubbard, Electrode Function (pH response) of soda-silica glasses, *J. Research NBS* **41**, 273 (1948) RP1923.
- [15] Donald Hubbard, Edgar H. Hamilton and A. N. Finn, Effect of the solubility of glass on the behavior of the glass electrode, *J. Research NBS* **22**, 339 (1939) RP1187.
- [16] G. Buchbock, A property of the glass electrode, *Z. physik. Chem.* **156A** 232 (1931).
- [17] Donald Hubbard and Gerald F. Rynders, Voltage anomalies of the glass electrode and the chemical durability of the glass, *J. Research NBS* **39**, 561 (1947) RP1848.
- [18] James W. McBain, The mechanism of the adsorption ("sorption") of hydrogen on carbon, *Phil. Mag.* **18**, 916 (1909); *Z. physik. chem.* **68**, 471 (1909).
- [19] Relative durability of optical glass, NBS Technical News Bulletin No. 221, 88 (1935).
- [20] E. Berger, Grundsatzliches uber die chemische angreifbarkeit von glasen I, *Glastech. Ber.* **14**, 351 (1936).
- [21] Donald Hubbard and Gerald F. Rynders, Effect of annealing and other heat treatments on the pH response of the glass electrode, *J. Research NBS* **40**, 105 (1948) RP1859.
- [22] Donald Hubbard and Gerald F. Rynders, Thickness of inhibiting films on glass electrode surfaces, *J. Research NBS* **41**, 163 (1948) RP1915.
- [23] H. T. S. Britton, Hydrogen ions, **1**, 3d ed., 88C, p. 313 (D. Van Nostrand Co., Inc., New York, N. Y., 1943).
- [24] M. R. Thompson, A metal-connected glass electrode, *BS J. Research* **9**, 833 (1932) RP 511.
- [25] Jack M. Florence, Francis W. Glaze, Clarence H. Hahner, and Ralph Stair, Transmittance of near infra red energy by binary glasses, *J. Research NBS* **41**, 623 (1948) RP1945.
- [26] J. M. Florence, C. C. Allshouse, F. W. Glaze, C. H. Hahner, The absorbance of near-infrared energy by certain glasses, *J. Research NBS* **45**, 121 (1950) RP2118.
- [27] Donald Hubbard, Hygroscopicity and electrode function (pH response) of glasses as a measure of serviceability, *J. Research NBS* **36**, 511 (1946) RP1719.
- [28] Donald Hubbard and Edgar H. Hamilton, Studies of the chemical durability of glass by an interferometer method, *J. Research NBS* **27**, 143 (1941) RP1409.
- [29] W. S. Hughes, On Haber's glass cell, *J. Chem. Soc.* 491 (1928).
- [30] K. A. Krakou, E. J. Mukhin, and M. S. Heinrich, Equilibrium diagram of the ternary system $\text{Na}_2\text{SiO}_3\text{-PbSiO}_3\text{-SiO}_2$, *Compt. rend. acad. sci. URSS* **14**, 281 (1937).

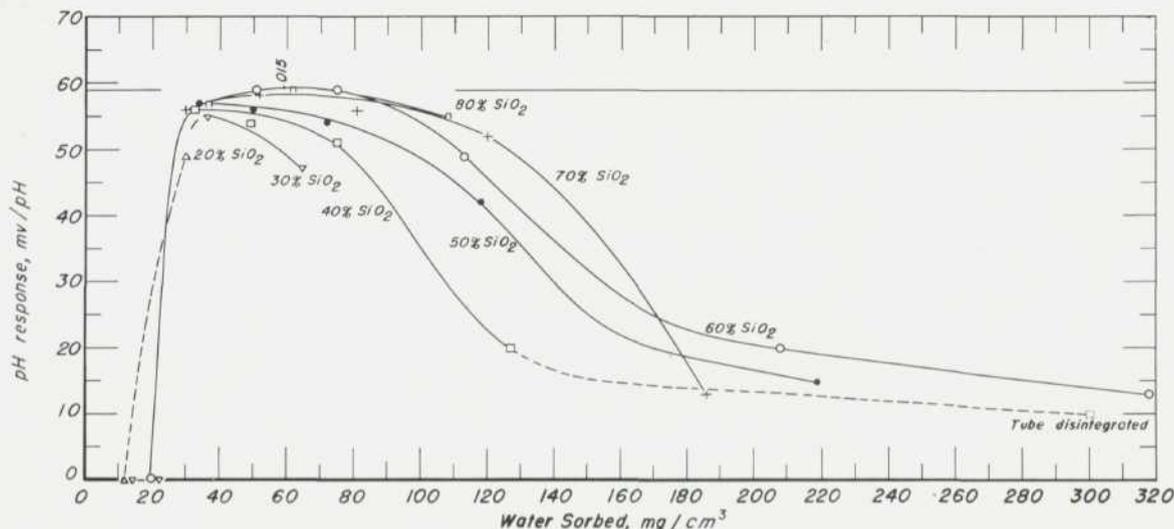


FIGURE 1. Comparison of the hygroscopicity (water sorbed, 1 hr) and pH response of a series of $\text{Na}_2\text{O-PbO-SiO}_2$ glasses.

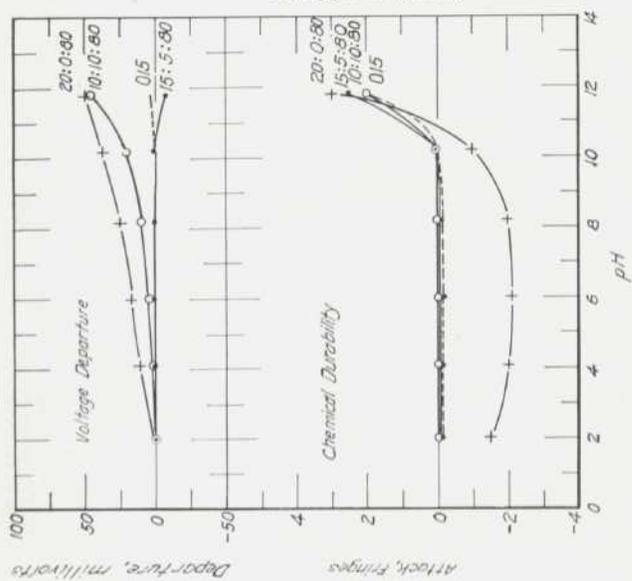


FIGURE 2. The pH-voltage departure curves for electrodes prepared from $\text{Na}_2\text{O-PbO-SiO}_2$ glasses containing 80 percent of SiO_2 compared with the chemical durability curves of the glasses.

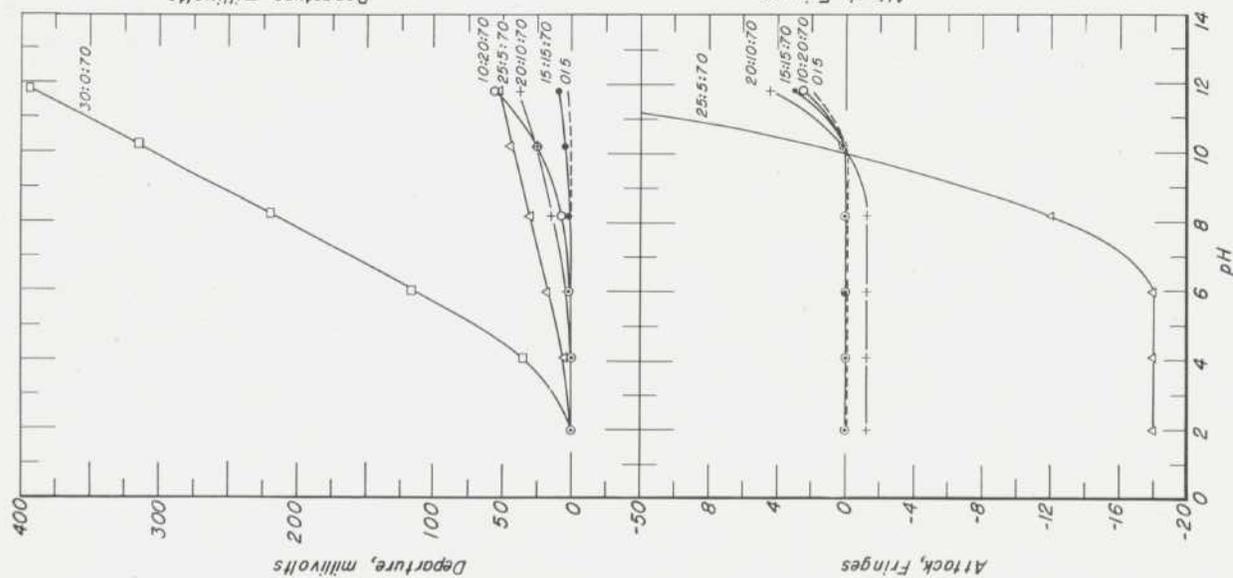


FIGURE 3. The pH-voltage departure curves for electrodes prepared from $\text{Na}_2\text{O-PbO-SiO}_2$ glasses containing 70 percent of SiO_2 compared with the chemical durability curves of the glasses.

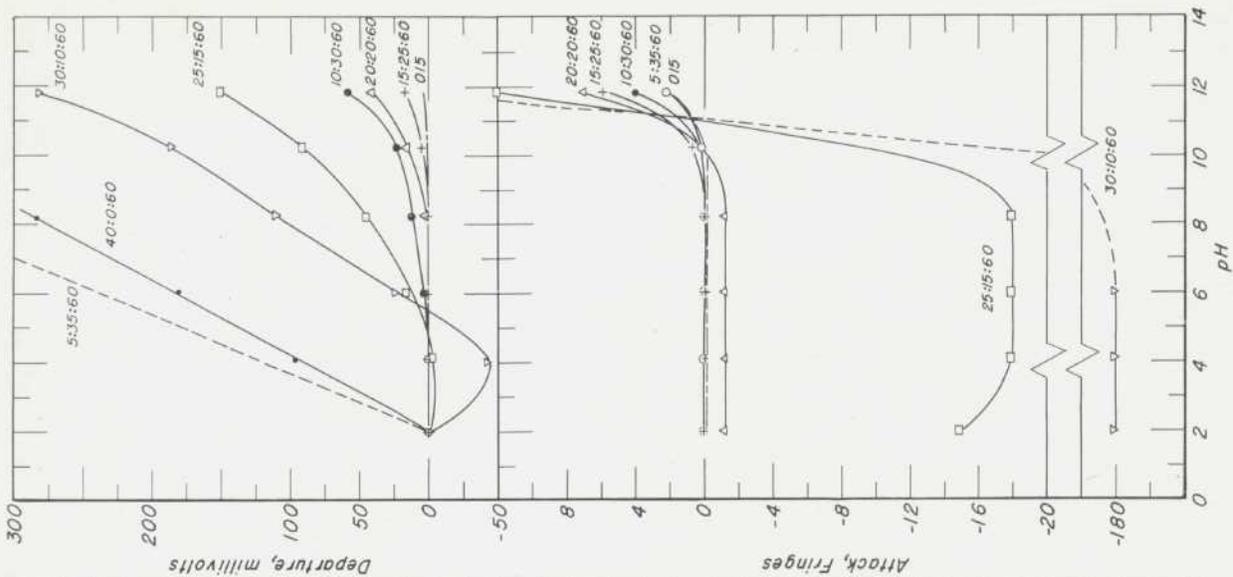


FIGURE 4. pH-voltage departure curves for electrodes prepared from $\text{Na}_2\text{O-PbO-SiO}_2$ glasses containing 60 percent of SiO_2 compared with the chemical durability curves of the glasses.

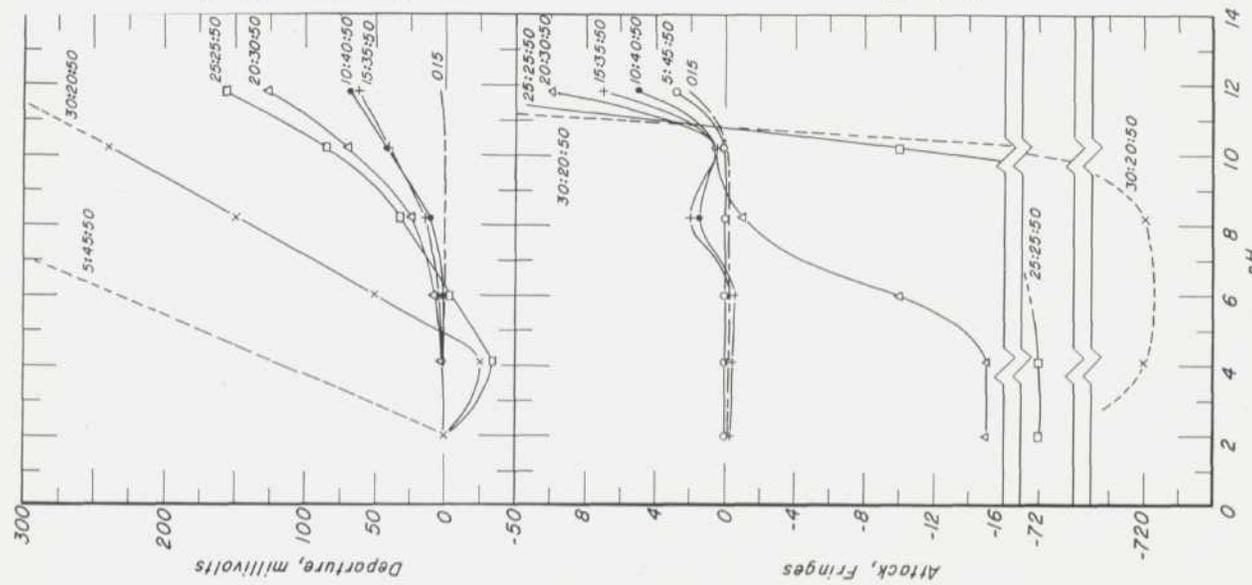


FIGURE 5. pH-voltage departure curves for electrodes prepared from $\text{Na}_2\text{O-PbO-SiO}_2$ glasses containing 50% of SiO_2 , compared with chemical durability curves of the glasses.

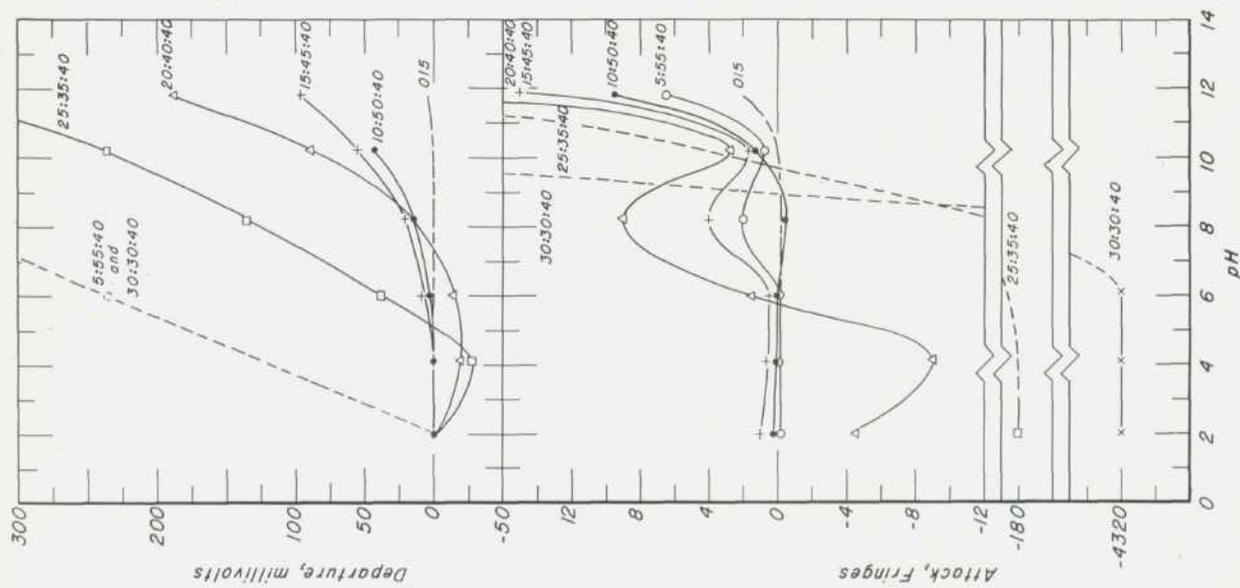


FIGURE 6. pH voltage departure curves for electrodes prepared from $\text{Na}_2\text{O-PbO-SiO}_2$ glasses containing 40% of SiO_2 , compared with chemical durability curves of the glasses.

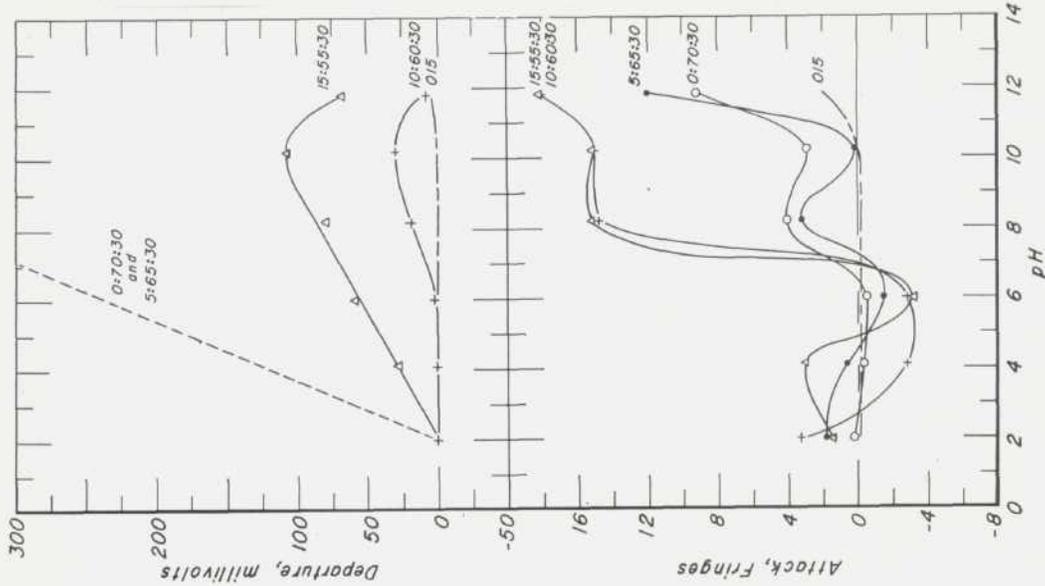


FIGURE 7. The pH-voltage departure curves for electrodes prepared from $\text{Na}_2\text{O-Pb-SiO}_2$ glasses containing 30 percent of SiO_2 , compared with the chemical durability curves for the glasses.

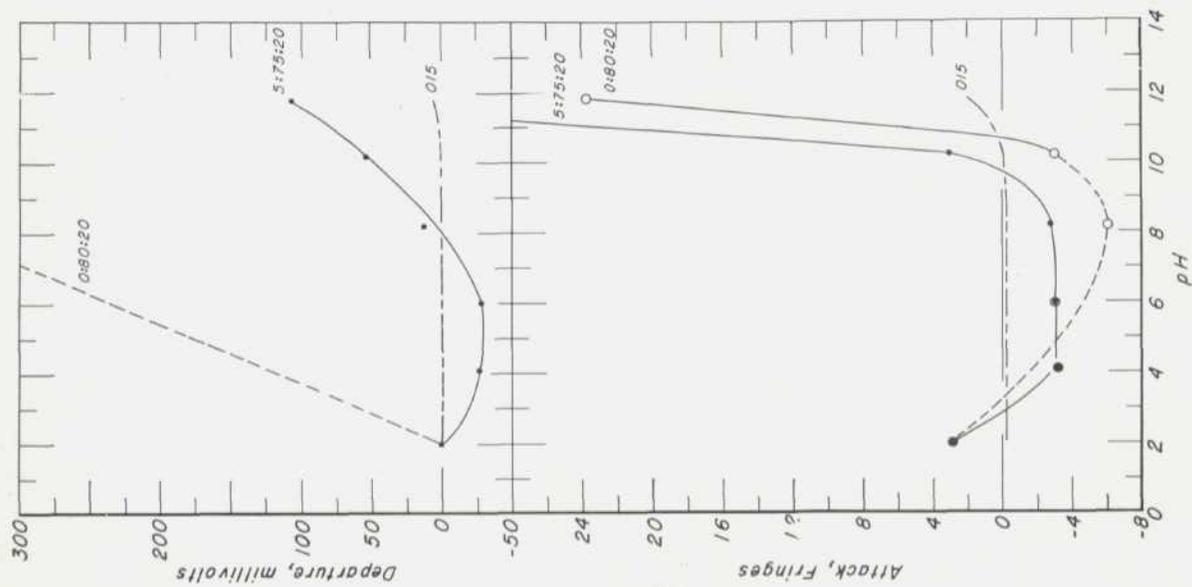


FIGURE 8. The pH-voltage departure curves for electrodes prepared from $\text{Na}_2\text{O-PbO-SiO}_2$ glasses containing 20 percent of SiO_2 compared with the chemical durability curves of the glasses.

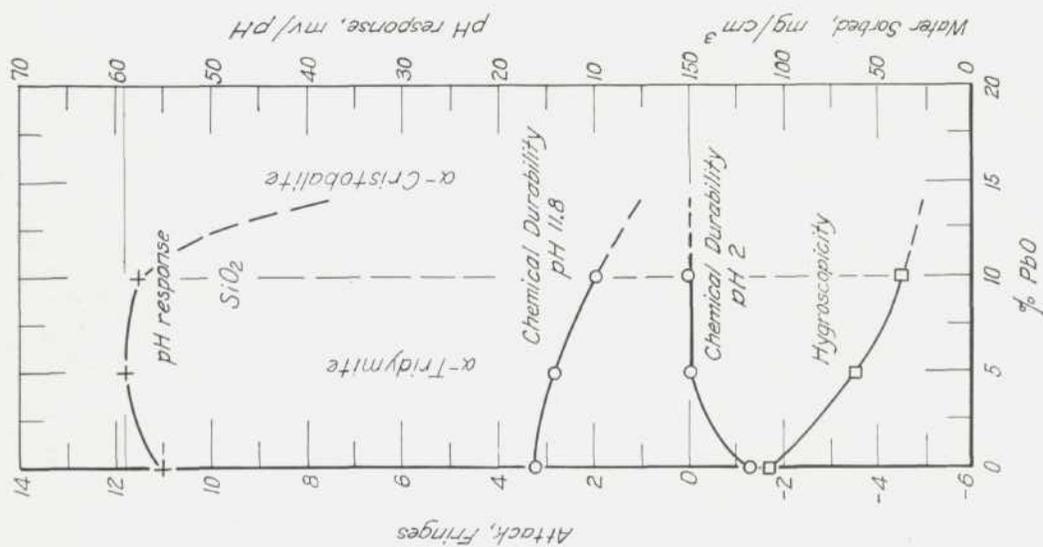


FIGURE 9. Values for pH-response, hygroscopicity, and chemical durability at pH 2 and 11.8 plotted against the percentage of PbO for $\text{Na}_2\text{O-PbO-SiO}_2$ glasses containing 80 percent of SiO_2 .

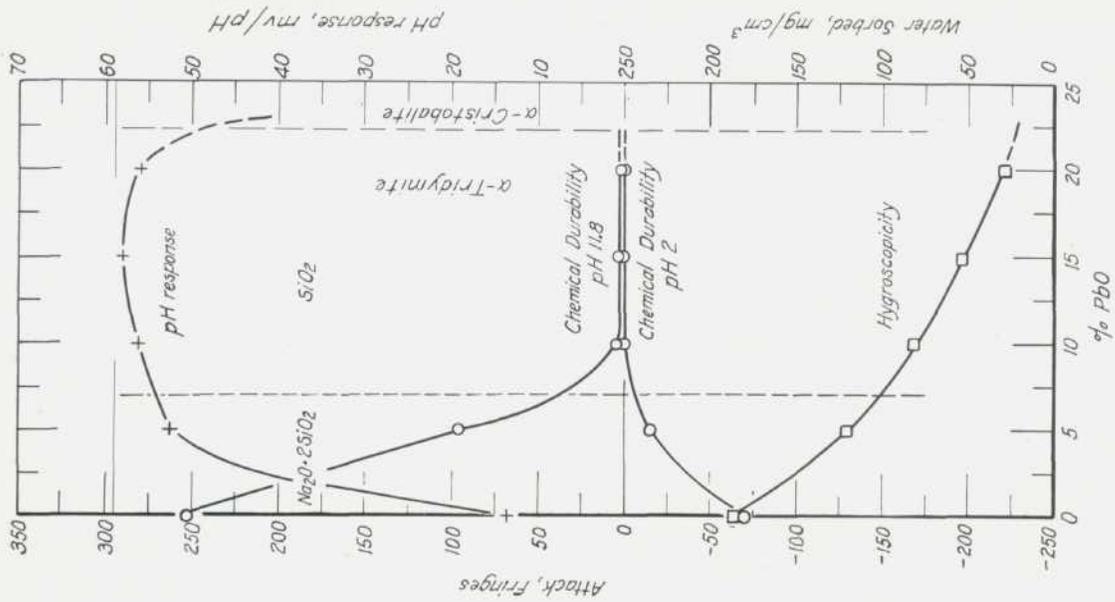


FIGURE 10. Values for pH-response, hygroscopicity, and chemical durability at pH 2 and 11.8 plotted against the percentage of PbO for $\text{Na}_2\text{O-PbO-SiO}_2$ glasses containing 70 percent of SiO_2 .

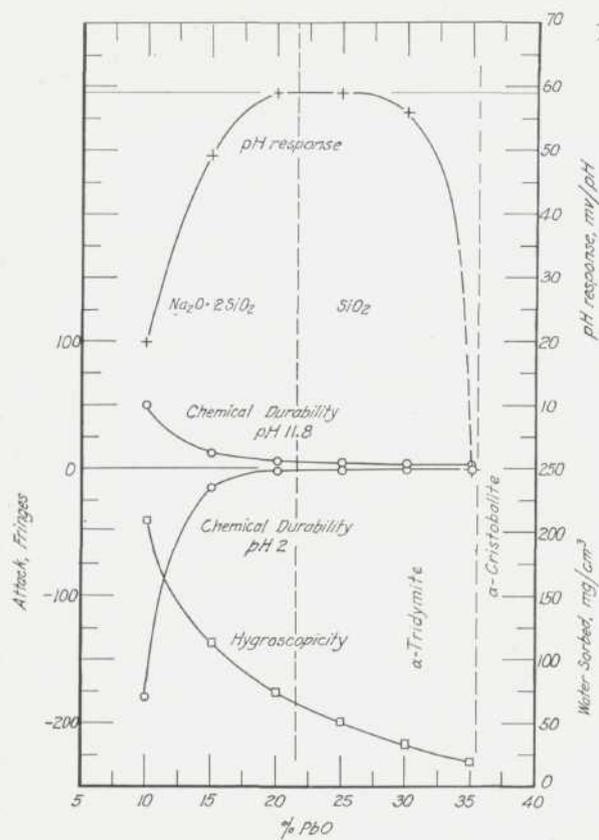


FIGURE 11. Values for pH-response, hygroscopicity, and chemical durability at pH 2 and 11.8 plotted against the percentage of PbO for Na₂O-PbO-SiO₂ glasses containing 60 percent of SiO₂.

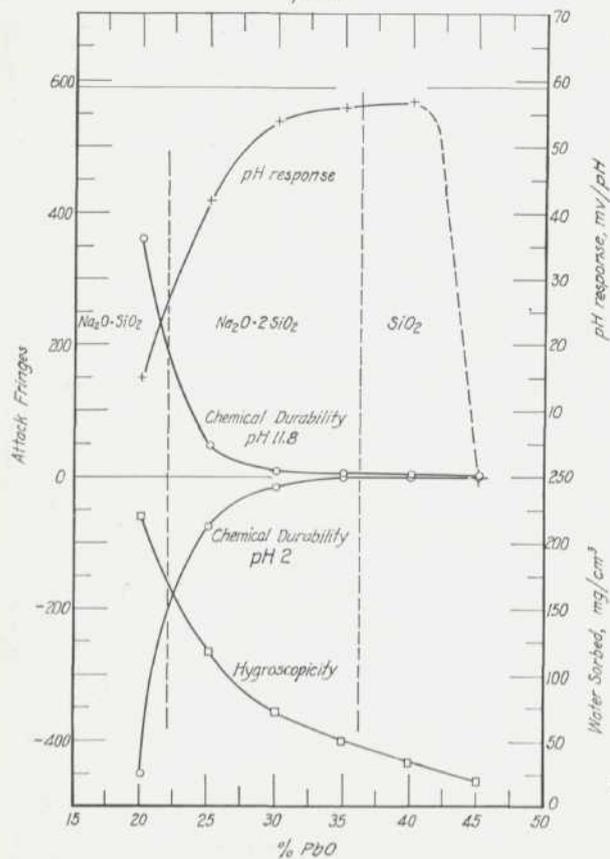


FIGURE 12. Values for pH-response, hygroscopicity, and chemical durability at pH 2 and 11.8 plotted against the percentage of PbO for Na₂O-PbO-SiO₂ glasses containing 50 percent of SiO₂.

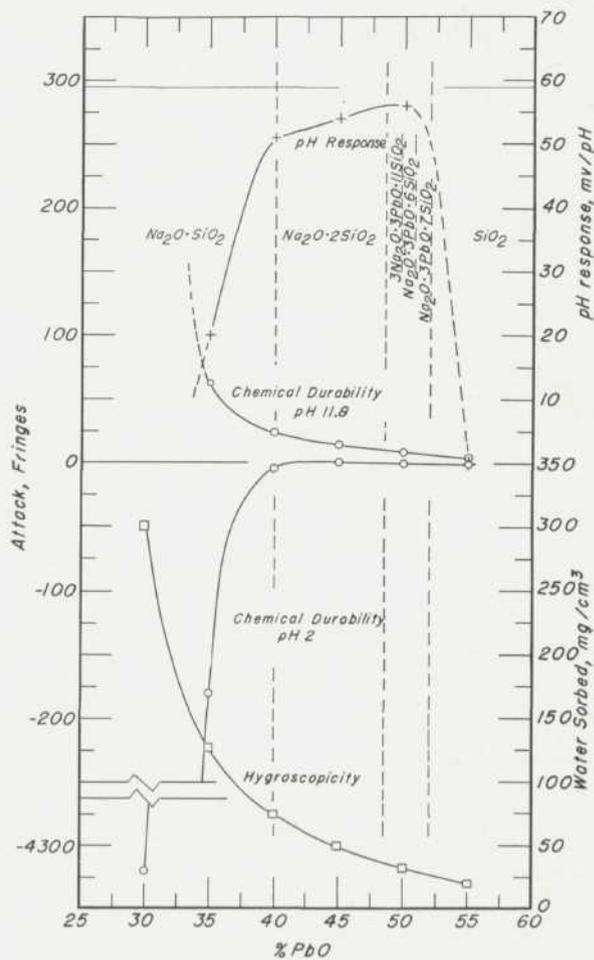


FIGURE 13. Values for pH-response, hygroscopicity, and chemical durability at pH 2 and 11.8 plotted against the percentage of PbO for Na₂O-PbO-SiO₂ glasses containing 40 percent of SiO₂.

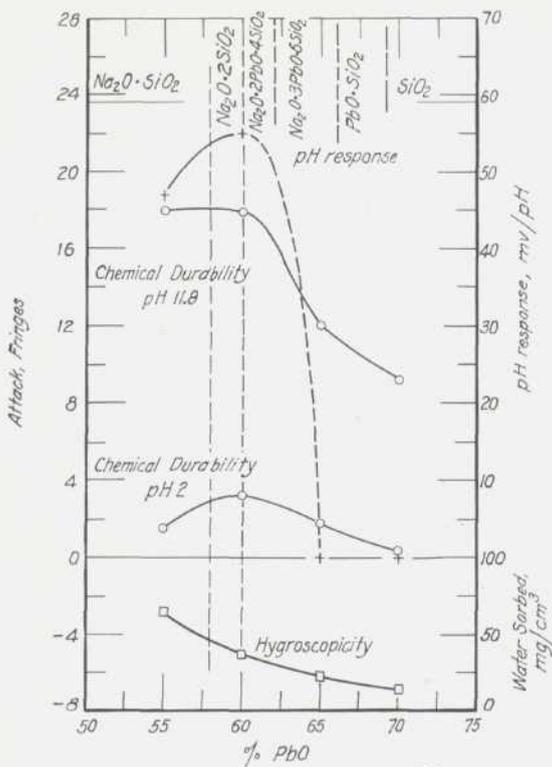


FIGURE 14. Values for pH-response, hygroscopicity, and chemical durability at pH 2 and 11.8 plotted against the percentage of PbO for Na₂O-PbO-SiO₂ glasses containing 30 percent of SiO₂.

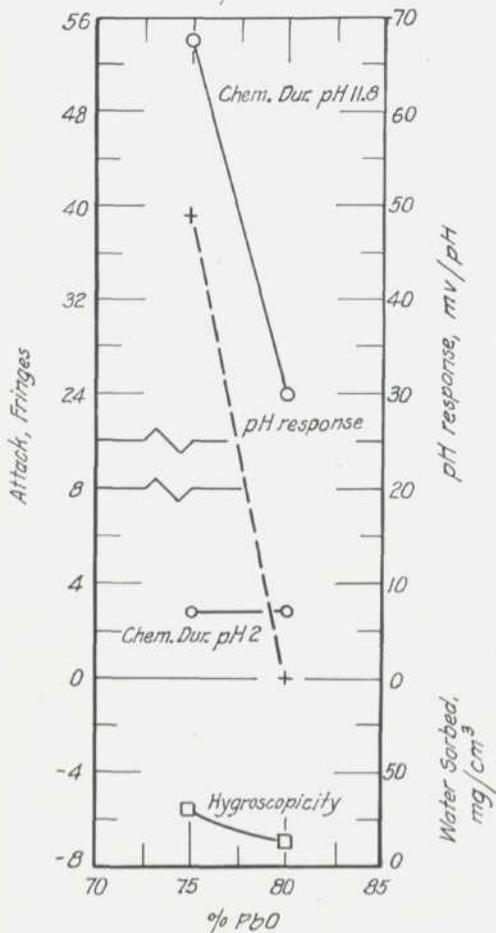


FIGURE 15. Values for pH-response, hygroscopicity, and chemical durability at pH 2 and 11.8 plotted against the percentage of PbO for Na₂O-PbO-SiO₂ glasses containing 20 percent of SiO₂.

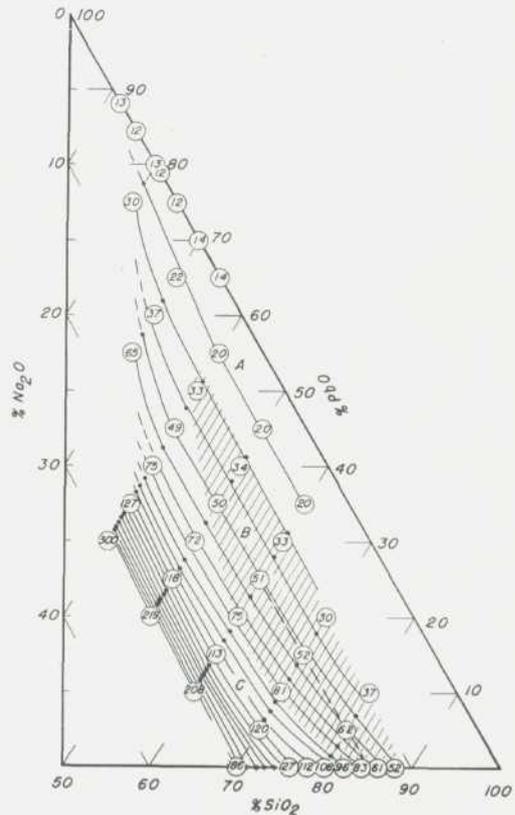


FIGURE 16. Hygroscopicity of Na₂O-PbO-SiO₂ glasses for 1-hr exposure showing lines of equal hygroscopicity (iso-sorbs for intervals of 10 mg/cm³) and the shaded area over which electrodes prepared from these glasses developed as high as 56 mv/pH.

The heavy dashed line links the only three glasses of the series that developed the theoretical 59 mv/pH at 25° C.

FIGURE 15. Values for pH-response, hygroscopicity, and chemical durability at pH 2 and 11.8 plotted against the percentage of PbO for Na₂O-PbO-SiO₂ glasses containing 20 percent of SiO₂.

WASHINGTON, MAY 24, 1950.