

NAT'L INST. OF STAND & TECH R.I.C.



A11104 142032

NATIONAL INSTITUTE OF STANDARDS &
TECHNOLOGY
Research Information Center
Gaithersburg, MD 20899

A11100 988606

NBS

PUBLICATIONS

NAT'L INST OF STANDARDS & TECH R.I.C.



A11100988606

/NBS monograph
QC100 .U556 V25-12;1975 C.1 NBS-PUB-C 19



NBS MONOGRAPH 25 – SECTION 12

U.S. DEPARTMENT OF COMMERCE / National Bureau of Standards

Standard X-ray Diffraction Powder Patterns

QG
100
.U556
no. 25-12
1975
c.2

NATIONAL BUREAU OF STANDARDS

The National Bureau of Standards¹ was established by an act of Congress March 3, 1901. The Bureau's overall goal is to strengthen and advance the Nation's science and technology and facilitate their effective application for public benefit. To this end, the Bureau conducts research and provides: (1) a basis for the Nation's physical measurement system, (2) scientific and technological services for industry and government, (3) a technical basis for equity in trade, and (4) technical services to promote public safety. The Bureau consists of the Institute for Basic Standards, the Institute for Materials Research, the Institute for Applied Technology, the Institute for Computer Sciences and Technology, and the Office for Information Programs.

THE INSTITUTE FOR BASIC STANDARDS provides the central basis within the United States of a complete and consistent system of physical measurement; coordinates that system with measurement systems of other nations; and furnishes essential services leading to accurate and uniform physical measurements throughout the Nation's scientific community, industry, and commerce. The Institute consists of a Center for Radiation Research, an Office of Measurement Services and the following divisions:

Applied Mathematics — Electricity — Mechanics — Heat — Optical Physics — Nuclear Sciences² — Applied Radiation² — Quantum Electronics³ — Electromagnetics³ — Time and Frequency³ — Laboratory Astrophysics³ — Cryogenics³.

THE INSTITUTE FOR MATERIALS RESEARCH conducts materials research leading to improved methods of measurement, standards, and data on the properties of well-characterized materials needed by industry, commerce, educational institutions, and Government; provides advisory and research services to other Government agencies; and develops, produces, and distributes standard reference materials. The Institute consists of the Office of Standard Reference Materials and the following divisions:

Analytical Chemistry — Polymers — Metallurgy — Inorganic Materials — Reactor Radiation — Physical Chemistry.

THE INSTITUTE FOR APPLIED TECHNOLOGY provides technical services to promote the use of available technology and to facilitate technological innovation in industry and Government; cooperates with public and private organizations leading to the development of technological standards (including mandatory safety standards), codes and methods of test; and provides technical advice and services to Government agencies upon request. The Institute consists of a Center for Building Technology and the following divisions and offices:

Engineering and Product Standards — Weights and Measures — Invention and Innovation — Product Evaluation Technology — Electronic Technology — Technical Analysis — Measurement Engineering — Structures, Materials, and Life Safety⁴ — Building Environment⁴ — Technical Evaluation and Application⁴ — Fire Technology.

THE INSTITUTE FOR COMPUTER SCIENCES AND TECHNOLOGY conducts research and provides technical services designed to aid Government agencies in improving cost effectiveness in the conduct of their programs through the selection, acquisition, and effective utilization of automatic data processing equipment; and serves as the principal focus within the executive branch for the development of Federal standards for automatic data processing equipment, techniques, and computer languages. The Institute consists of the following divisions:

Computer Services — Systems and Software — Computer Systems Engineering — Information Technology.

THE OFFICE FOR INFORMATION PROGRAMS promotes optimum dissemination and accessibility of scientific information generated within NBS and other agencies of the Federal Government; promotes the development of the National Standard Reference Data System and a system of information analysis centers dealing with the broader aspects of the National Measurement System; provides appropriate services to ensure that the NBS staff has optimum accessibility to the scientific information of the world. The Office consists of the following organizational units:

Office of Standard Reference Data — Office of Information Activities — Office of Technical Publications — Library — Office of International Relations.

¹ Headquarters and Laboratories at Gaithersburg, Maryland, unless otherwise noted; mailing address Washington, D.C. 20234.

² Part of the Center for Radiation Research.

³ Located at Boulder, Colorado 80302.

⁴ Part of the Center for Building Technology.

AUG 25 1975

not acc.

Standard X-ray Diffraction Powder Patterns

100

556

25¹² Section 12—Data for 57 Substances

Monograph No. 25-12

75

2

Howard F. McMurdie, Marlene C. Morris, Eloise H. Evans,
Boris Paretzkin, Johan H. de Groot,
Camden R. Hubbard and Simon J. Carmel

Institute for Materials Research
National Bureau of Standards
Washington, D.C. 20234



U.S. DEPARTMENT OF COMMERCE, Frederick B. Dent, Secretary

NATIONAL BUREAU OF STANDARDS, Richard W. Roberts, Director

Issued February 1975

Library of Congress Catalog Card Number: 53-61386

National Bureau of Standards Monograph 25

Section 12—Data for 57 Substances

Nat. Bur. Stand. (U.S.), Monogr. 25—Sec. 12, 90 pages (Feb. 1975)

CODEN: NBSMA6

**U.S. GOVERNMENT PRINTING OFFICE
WASHINGTON: 1975**

**For sale by the Superintendent of Documents, U.S. Government Printing Office, Washington, D.C. 20402
(Order by SD Catalog No. C13.44:25/Sec. 12). Price \$1.50**

CONTENTS

	Page		Page
Introduction.....	1		
Experimental patterns:			
Aluminum nitride, AlN.....	5	Lithium silver bromide, solid solution series	
Ammonium copper chloride hydrate, $(\text{NH}_4)_2\text{CuCl}_4 \cdot 2\text{H}_2\text{O}$	6	Li. ₈ Ag. ₂ Br.....	55
Barium aluminum oxide, Ba ₃ Al ₂ O ₆	7	Li. ₆ Ag. ₄ Br.....	55
Barium chloride hydrate, BaCl ₂ ·2H ₂ O.....	9	Li. ₄ Ag. ₆ Br.....	55
Barium molybdenum oxide, Ba ₂ MoO ₅	10	Li. ₂ Ag. ₈ Br.....	55
Barium phosphate, Ba ₃ (PO ₄) ₂	12	Phosphoric acid hydrate, H ₃ PO ₄ ·½H ₂ O.....	56
Barium tungsten oxide, Ba ₂ WO ₅	14	Potassium cerium fluoride, β-KCeF ₄	59
Calcium chloride hydrate (antarcticite), CaCl ₂ ·6H ₂ O.....	16	Potassium sodium bromide, solid solution series	
Calcium oxide phosphate, Ca ₄ O(PO ₄) ₂	17	K. ₈ Na. ₂ Br.....	62
Cobalt acetate hydrate, Co(C ₂ H ₃ O ₂) ₂ ·4H ₂ O.....	19	K. ₆ Na. ₄ Br.....	62
Cobalt borate, Co ₃ (BO ₃) ₂	20	K. ₄ Na. ₆ Br.....	62
Cobalt bromide hydrate, CoBr ₂ ·6H ₂ O.....	21	K. ₂ Na. ₈ Br.....	62
Cobalt nitrate hydrate, α-Co(NO ₃) ₂ ·6H ₂ O.....	22	Potassium sodium chloride, solid solution series	
Lead chloride (cotunnite), PbCl ₂	23	K. ₈ Na. ₂ Cl.....	63
Magnesium titanium oxide, MgTiO ₄	25	K. ₆ Na. ₄ Cl.....	63
Nickel nitrate hydrate, Ni(NO ₃) ₂ ·6H ₂ O.....	26	K. ₄ Na. ₆ Cl.....	63
Potassium chromium oxide sulfate, K ₂ (CrO ₄). ₆₇ (SO ₄). ₃₃	27	K. ₂ Na. ₈ Cl.....	63
Potassium chromium oxide sulfate, K ₂ (CrO ₄). ₃₃ (SO ₄). ₆₇	28	Thorium cobalt, Th ₂ Co ₁₇	64
Potassium rubidium chromium oxide, KRbCrO ₄	29	Thorium iron, Th ₂ Fe ₁₇	67
Silver chromium oxide, Ag ₂ CrO ₄	30	Cumulative indices	
Strontium nitrate, Sr(NO ₃) ₂	31	(Circular 539, Volumes 1-10 and Monograph 25, Sections 1-12 inclusive)	
Strontium tungsten oxide, Sr ₂ WO ₅	32		
Telluric acid, H ₆ TeO ₆	34	1. Inorganic.....	70
Zinc nitrate hydrate, α-Zn(NO ₃) ₂ ·6H ₂ O.....	36	2. Organic.....	83
Zinc titanium oxide, Zn ₂ TiO ₄	37	3. Mineral.....	84
Calculated patterns:			
Barium calcium nitrate, solid solution series			
Ba. _{.75} Ca. _{.25} (NO ₃) ₂	38		
Ba. _{.50} Ca. _{.50} (NO ₃) ₂	38		
Ba. _{.25} Ca. _{.75} (NO ₃) ₂	38		
Barium lead nitrate, solid solution series			
Ba. _{.67} Pb. _{.33} (NO ₃) ₂	40		
Ba. _{.33} Pb. _{.67} (NO ₃) ₂	40		
Barium strontium nitrate, solid solution series			
Ba. _{.75} Sr. _{.25} (NO ₃) ₂	42		
Ba. _{.50} Sr. _{.50} (NO ₃) ₂	42		
Ba. _{.25} Sr. _{.75} (NO ₃) ₂	42		
Calcium lead nitrate, solid solution series			
Ca. _{.67} Pb. _{.33} (NO ₃) ₂	44		
Ca. _{.33} Pb. _{.67} (NO ₃) ₂	44		
Calcium strontium nitrate, solid solution series			
Ca. _{.67} Sr. _{.33} (NO ₃) ₂	46		
Ca. _{.33} Sr. _{.67} (NO ₃) ₂	46		
Gallium magnesium, Ga ₂ Mg.....	48		
Gallium magnesium, Ga ₅ Mg ₂	51		
Lead strontium nitrate, solid solution series			
Pb. _{.67} Sr. _{.33} (NO ₃) ₂	53		
Pb. _{.33} Sr. _{.67} (NO ₃) ₂	53		

STANDARD X-RAY DIFFRACTION POWDER PATTERNS

The following copies may be obtained from the National Technical Information Service, 5285 Port Royal Road, Springfield, Virginia 22151. Where these publications are identified with a number, it must be used in ordering. They are available in hardcopy or microfiche; the price is not fixed and will be furnished on request.

NBS Publication	Number	NBS Publication	Number
Circular 539, Volume 1.....	PB 178 902	Monograph 25, Section 1.....	PB 178 429
Volume 2.....	PB 178 903	Section 2.....	PB 178 430
Volume 3.....	PB 178 904	Section 3.....	PB 178 431
Volume 4.....	PB 178 905	Section 4	
Volume 5.....	PB 178 906	Section 5	
Volume 6.....	PB 178 907	Section 6	
Volume 7.....	PB 178 908	Section 7	
Volume 8.....	PB 178 909	Section 8.....	PB 194 872
Volume 9.....	PB 178 910	Section 9.....	COM 72-50002
Volume 10.....	PB 178 911	Section 10.....	COM 72-51079
		Section 11.....	COM 74-50183

STANDARD X-RAY DIFFRACTION POWDER PATTERNS

Section 12. --- Data for 57 Substances

by

Howard F. McMurdie, Marlene C. Morris, Eloise H. Evans,
Boris Paretzkin, and Johan H. de Groot
Joint Committee on Powder Diffraction Standards

and

Camden R. Hubbard and Simon J. Carmel
National Bureau of Standards

Standard x-ray diffraction patterns are presented for 57 substances. Twenty-five of these patterns represent experimental data and 32 are calculated. The experimental x-ray powder diffraction patterns were obtained with an x-ray diffractometer. All d-values were assigned Miller indices determined by comparison with computed interplanar spacings consistent with space group extinctions. The densities and lattice constants were calculated and the refractive indices were measured whenever possible. The calculated x-ray powder diffraction patterns were computed from published crystal structure data. Both peak height and integrated intensities are reported for the calculated patterns.

Key words: Crystal structure; integrated intensities; lattice constants; peak intensities; powder patterns; reference intensities; standard; x-ray diffraction.

INTRODUCTION

The Powder Diffraction File is a continuing compilation of diffraction patterns gathered from many sources. Produced and published by the Joint Committee on Powder Diffraction Standards,¹ the File is used for identification of crystalline materials by matching d-spacings and diffraction intensity measurements. Under the partial sponsorship of the Joint Committee, the program at the National Bureau of Standards contributes new data to this File. Our work also aids in the evaluation and revision of published x-ray data and in the development of diffraction techniques. This report presents information for 57 compounds (25 experimental and 32 calculated patterns), and is the twenty-second of the series of "Standard X-ray Diffraction Powder Patterns."²

EXPERIMENTAL POWDER PATTERNS

Sample. The samples used to make NBS patterns were obtained from a variety of sources or were prepared in small quantities in our laboratory. Appropriate annealing or recrystallization of the sample improved the quality of most of the patterns. A check of phase purity was provided by indexing the x-ray pattern. Unless otherwise noted, the spectrographic analyses were done at NBS after preparation of the sample was completed; the limit of detection for the alkali elements was 0.05 weight percent.

Optical data, color. A microscopic inspection for phase purity was also made on the non-opaque materials during the refractive index determination. The latter was done by grain-immersion methods in white light, using oils standardized in sodium light, in the refractive index range 1.40 to 2.1 [Hartshorne and Stuart, 1970].

The names of the sample colors were selected from the ISCC-NBS Centroid Color Charts [1965].

Interplanar spacings. For spacing determinations, a shallow holder was packed with a sample mixed with an internal standard (approximately 5 wt. percent tungsten powder). If tungsten lines were found to interfere with sample lines, silver or silicon was used in place of tungsten. If the internal standard correction varied along the length of the pattern, linear interpolations were used. To avoid errors associated with aberrations at the very top of peaks, the readings of 2θ were taken at positions about 20 percent of the way down from the top, and in the center of the peak width. The internal standard correction for each region was then applied to the measured value of 2θ . We have reported all data as $K\alpha_1$ peaks because the internal standard corrections for all regions were established in terms of the $K\alpha_1$ wavelength.

¹Joint Committee on Powder Diffraction Standards, 1601 Park Lane, Swarthmore, PA. 19081. This Pennsylvania non-profit corporation functions in cooperation with the American Ceramic Society, the American Crystallographic Association, the American Society for Testing and Materials, The Clay Minerals Society, The Institute of Physics, the Mineralogical Association of Canada, the Mineralogical Society of America, The Mineralogical Society of Great Britain and Ireland, the National Association of Corrosion Engineers, and the Société Française de Minéralogie et de Cristallographie.

²See previous page for other published volumes.

The internal standards used were of high purity (99.99%). The lattice constants used for them at 25 °C are given in the table below; the 2θ angles were computed using cell dimensions uncorrected for index of refraction.

Calculated 2θ Angles, $\text{CuK}\alpha_1 \lambda = 1.540598\text{\AA}^\circ$			
hkl	W $a=3.16524\text{\AA}$ $\pm .00004$	Ag $a=4.08651\text{\AA}$ $\pm .00002$	Si $a=5.43088\text{\AA}$ $\pm .00004$
110	40.262		
111		38.112	28.443
200	58.251	44.295	
211	73.184		
220	86.996	64.437	47.303
310	100.632		
311		77.390	56.123
222	114.923	81.533	
321	131.171		
400	153.535	97.875	69.131
331		110.499	76.377
420		114.914	
422		134.871	88.032
511/333		156.737	94.954
440			106.710
531			114.094
620			127.547
533			136.897
444			158.638

The new internal standard Si powder is available as Standard Reference Material 640 [1974]. The lattice constant for the Si was refined from multiple powder data measurements made with tungsten as an internal standard [Swanson et al., 1966]. Cell parameter data were also collected for a single crystal from the boules ground to prepare the powder. The lattice parameters from the two methods agreed within 3 parts in 10^5 [Hubbard et al.]. D-spacing results using SRM 640 will be in agreement with patterns recorded in this series of monographs since 1966.

All of our spacing measurements were recorded at 25 ± 1 °C on a diffractometer equipped with a focusing graphite or lithium fluoride crystal monochromator located between the sample and the scintillation counter. Pulse height discrimination was used as well. All measurements were performed using copper radiation: $\lambda(\text{CuK}\alpha_1, \text{peak}) = 1.540598\text{\AA}$ [Deslattes and Henins, 1973].

Structure, lattice constants. The space groups were listed with short Hermann-Mauguin symbols as well as the space group numbers given in the *International Tables for X-ray Crystallography, Vol. I* [1952].


Orthorhombic cell dimensions were arranged according to the Dana convention $b > a > c$ [Palache et al., 1944]. Monoclinic and triclinic lattice constants were transformed if necessary in order to follow the convention of *Crystal Data* [1973]. For primitive cells, the transformed cell axes are an alternate labelling of the reduced cell

axes. For centered monoclinic cells, the transformed cell is the centered cell with the three shortest non-coplanar vectors.

A computer program [Evans et al., 1963] assigned hkl 's and refined the lattice constants. Cell refinement was based only upon $2\theta_{\text{obs}}$ values which could be indexed without ambiguity. The program minimized the value $\Sigma (\theta_{\text{obs}} - \theta_{\text{calc}})^2$. The estimated standard deviations (e.s.d.'s) of the reciprocal cell parameters were determined from the inverse matrix of the normal equations. The program calculated the e.s.d.'s of the direct cell constants by the method of propagation of errors. Since 1973, the e.s.d.'s derived by the computer program have been increased by 50% in order to reflect more truly the uncertainty in the lattice constants. A similar increase should also be applied to all lattice constants in earlier publications of this series. In indexing cubic patterns, multiple hkl 's were not utilized in the refinement or reported. Instead, the single appropriate index having the largest h was listed. The number of significant figures reported for d-values varied with the symmetry and crystallinity of each sample.

Densities. These were calculated from the specified lattice constants, the Avogadro number 6.0220943×10^{23} [Deslattes et al., 1974] and atomic weights based on carbon 12 [International Union, 1961].

Intensity measurements. It was found that samples which gave satisfactory intensity patterns usually had an average particle size smaller than $10 \mu\text{m}$, as recommended by Alexander et al. [1948]. In order to avoid the orientation effects which occur when powdered samples are packed or pressed, a sample holder was made that had in its top face a rectangular cavity which extended to one end of the holder. To prepare the sample, a glass slide was clamped over the top face to form a temporary cavity wall (see Figure 1), and the powdered sample was allowed to drift into the end opening while the holder was held in a vertical

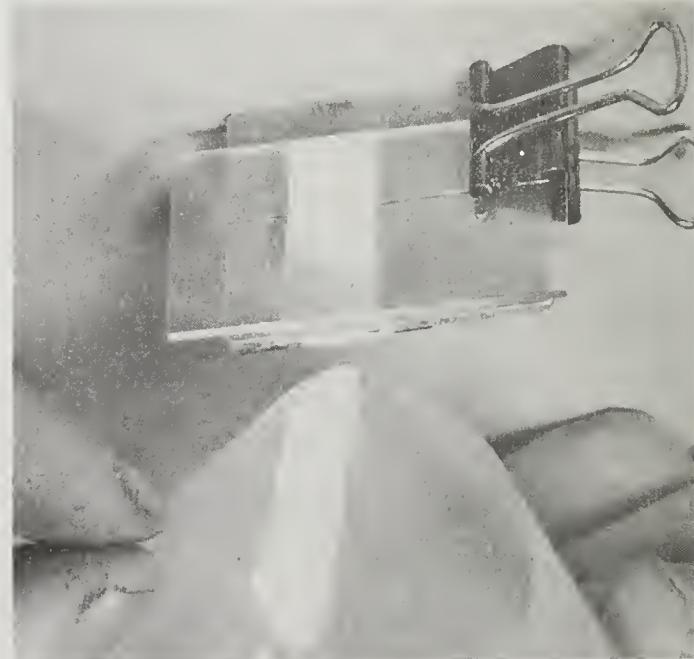



position. With the sample holder returned to a horizontal position, the glass slide was carefully removed so that the sample could be exposed to the x-ray beam (as shown in Figure 2). If the sample powder did not flow readily, or was prone to orient excessively, approximately 50 volume percent of finely ground silica-gel was added as a diluent. The intensities of the diffraction lines were measured as peak heights above background and were expressed in percentages of the strongest line. At least three patterns for intensity measurements were prepared for each sample to check reproducibility.

Reference intensity, I/I_{corundum} . For reference intensity measurements, $\alpha\text{-Al}_2\text{O}_3$ (corundum) was chosen as an internal standard to be mixed 1:1 by weight with the sample. This mixture of two components was mounted in our regular intensity sample holder (see Figures 1 and 2), and the pattern was taken. The reference intensity was then calculated as the direct ratio of the strongest line of the sample to the strongest line of corundum (hexagonal reflection (113)). In a few instances, the strongest line of one of the components coincided with a line of the other. In that case, the second strongest line was measured, and the value for the strongest line was then calculated.

CALCULATED POWDER PATTERNS

Since some substances of interest are not readily available for experimental work, powder patterns were calculated from published crystal structure data. The FORTRAN program used for the computations was developed by Smith [1967] and modified at NBS.

Lattice parameters. Before the computations of the patterns, any necessary changes were made in the lattice constants in order to make them consistent with the revised value of the copper wavelength [Deslattes and Henins, 1973]. Both the altered and the original published values are given. Monoclinic and triclinic lattice constants

were transformed if necessary, to follow the convention of *Crystal Data* [1973]. For primitive cells, the transformed cell axes are an alternate labelling of the reduced cell axes. For centered monoclinic cells, the transformed cell is the centered cell with the three shortest non-coplanar vectors.

Scattering factors. Whenever possible, the same scattering factors were used which the author of the reference article specified. Otherwise, the factors were taken directly from the *International Tables for X-ray Crystallography*, Vol. III, [1962]. The factors were corrected for dispersion if the author had done so.

Thermal parameters. The computer program used thermal parameter data of only two forms, the isotropic B 's or the anisotropic β_{ij} 's in the following expressions:

$$e^{(-B \sin^2 \theta)/\lambda^2}$$

or

$$e^{-(h^2\beta_{11}+k^2\beta_{22}+\ell^2\beta_{33}+2hk\beta_{12}+2h\ell\beta_{13}+2k\ell\beta_{23})}.$$

Other thermal parameters were converted to one of these two forms. The isotropic parameters were used directly, if given by the structure reference. In a few of our patterns, anisotropic parameters were also used directly as given by the structure reference; in other work, instead of using given anisotropic parameters, approximately equivalent isotropic values were substituted as defined by:

$$B = 4 \left[\frac{\beta_{11}\beta_{22}\beta_{33}}{a^2 b^2 c^2} \right]^{\frac{1}{3}}$$

Integrated intensities. Intensity calculations were based on the copper $K\alpha_1$ wavelength, 1.540598 Å, determined by Deslattes and Henins [1973]. The integrated intensities were computed from formula (1):

$$(1) \quad I = F^2 (L_p) (FAC)$$

where F is the standard structure factor

FAC is the powder multiplicity

$$L_p = \frac{1+\cos^2 2\theta}{\sin^2 \theta \cos \theta}$$

The intensities were scaled to the strongest line which was assigned a value of 100. Reflections were not reported which had scaled intensities of 0.1 or less.

Scale factor. For each compound, this factor multiplied by the reported integrated intensities will reproduce the unscaled intensities which were calculated from equation (1).

Peak intensities. The integrated intensities can be transformed to a Cauchy profile with an appropriate variable half-width designated to simulate a diffractometer tracing [Smith, 1967]. The term half-width as used here is defined as the full width at half maximum and was assigned a value of 0.075° at 40° (2θ , $\text{CuK}\alpha_1$). Then the intensities were summed for the overlapping peak profiles, and the resulting new peak intensities were scaled to the strongest peak height which was assigned a value of 100. Reflections were not reported which had scaled peak heights of 0.1 or less. Adjacent peaks with nearly equal 2θ values usually cannot be experimentally resolved; therefore one composite peak was calculated in such instances. The 2θ angle of this peak was assigned the hkl of the reflection having the greatest integrated intensity; a plus sign (+) was used to indicate additional hkl 's.

REFERENCES

- Alexander, L., Klug, H. P. and Kummer, E. (1948). *J. Appl. Phys.*, **19**, No. 8, 742.
- Crystal Data (1973). (3rd. Ed. Published jointly by the U. S. Department of Commerce, National Bureau of Standards, Washington, D. C. 20234, and the Joint Committee on Powder Diffraction Standards, Swarthmore, PA 19081).
- Deslattes, R.D. and Henins, A. (1973). *Phys. Rev. Lett.* **31**, 972.
- Deslattes, R. D., Henins, A., Bowman, H. A., Schoonover, R.M., Carroll, C.L., Barnes, I.L., Machlan, L.A., Moore, L. J., and Shields, W.R. (1974). *Phys. Rev. Lett.* **33**, 463.
- Evans, H.T., Jr., Appleman, D. E. and Handwerker, D.S. (1963). (abs.) *Am. Cryst. Assoc. Annual Meeting*, Cambridge, Mass. Program, 42.
- Hartshorne, N.H. and Stuart, A. (1970). *Crystals and the Polarizing Microscope* (Edward Arnold and Co., London, 4th Ed.)
- Hubbard, C. R., Swanson, H. E., and Mauer, F. A. *J. Appl. Cryst.* (to be published).
- International Tables for X-ray Crystallography, I (1952). (The Kynoch Press, Birmingham, Eng.), *Ibid. III* (1962). Pgs. 202, 210, 213, 214.
- International Union of Pure and Applied Chemistry (1961). *Chem. Eng. News* **39** (4), Nov. 20, 42.
- ISCC-NBS Centroid Color Charts, SRM 2106 (1965), obtainable from the Office of Standard Reference Materials, Room B311, Chemistry Building, National Bureau of Standards, Washington, D.C. 20234. \$5.00 per set.
- Palache, C., Berman, H. and Frondel, C. (1944). *Dana's System of Mineralogy* (John Wiley and Sons, New York, 7th Ed.), I, 6.
- Smith, D.K. (1967). A Revised Program for Calculating Powder Diffraction Patterns, UCRL 50264, University of California, Lawrence Radiation Laboratory, Livermore, CA. 94551.
- Standard Reference Material 640, Silicon Powder, X-ray Diffraction Standard, obtainable from the Office of Standard Reference Materials, Room B311, Chemistry Building, National Bureau of Standards, Washington, D.C. 20234. \$52.00 per 10 gram unit.
- Swanson, H. E., Morris, M. C., and Evans, E. H. (1966). *Nat'l Bur. Std. U.S. Monograph* **25**, Sec. 4, 3.

Aluminum nitride AlN

Sample

The sample was obtained from Cerac/Pure, Inc., Menomonee Falls, Wis. A small amount of metallic aluminum was sieved out.

Major impurities

0.001-0.01% each Ca, Ni
0.003-0.03% each Co, Cr, Cu, Sr, Ti
0.01-0.1% each Fe, Mg, Si

Color

Very pale gray

Optical data

Uniaxial, (+), $N_o = 2.13$, $N_e = 2.20$ [Kohn et al., 1956].

Structure

Hexagonal, P6₃mc (186), Z=2, isostructural with wurtzite, ZnS, [Ott, 1924]. The structure of AlN was refined by Jeffrey et al. [1956].

NBS lattice constants of this sample:

$$\begin{aligned} a &= 3.1114(1) \text{\AA} \\ c &= 4.9792(2) \end{aligned}$$

Density

(calculated) 3.261 g/cm³

Reference intensity

$$I/I_{\text{corundum}} = 1.6$$

Additional patterns

1. PDF card 8-262 [Paretzkin, B., Polytechnic Inst. of Brooklyn].

References

- Jeffrey, G. A., Parry, G. S., and Mozzi, R. L. (1956). J. Chem. Phys. 25, 1024.
 Kohn, J.A., Cotter, P.G., and Potter, R.A. (1956). Am. Mineralogist 41, 355.
 Ott, Z. (1924). Z. Physik 22, 201.

$\text{CuK}\alpha_1 \lambda = 1.540598 \text{\AA}$; temp. $25 \pm 1^\circ \text{C}$ Internal standard W, $a = 3.16524 \text{\AA}$			
d(A)	I	hkl	$2\theta (\circ)$
2.695	100	100	33.21
2.490	60	002	36.04
2.371	80	101	37.92
1.829	25	102	49.80
1.5559	40	110	59.35
1.4133	30	103	66.05
1.3475	5	200	69.73
1.3194	25	112	71.44
1.3007	10	201	72.63
1.2450	1	004	76.44
1.1850	4	202	81.09
1.1301	1	104	85.94
1.0461	9	203	94.84
1.0184	3	210	98.29
0.9978	7	211	101.06
.9720	2	114	104.84
.9425	3	212	109.62
.9340	6	105	111.12
.9142	<1	204	114.82
.8982	4	300	118.10
.8680	10	213	125.11
.8448	5	302	131.51
.8298	1	006	136.33
.8008	5	205	148.28
.7931	1	106	152.44
.7882	<1	214	155.49

Ammonium copper chloride hydrate, $(\text{NH}_4)_2\text{CuCl}_4 \cdot 2\text{H}_2\text{O}$

Sample

The sample was prepared by slow evaporation at room temperature of a 2:1 aqueous solution of NH_4Cl and CuCl_2 .

Major impurities:

0.001-0.01% each: Al and Mg.

Color

Brilliant greenish blue

Optical data

uniaxial (-), $N_o = 1.668$, $N_e = 1.640$

Structure

Tetragonal, $P4_2/mnm$ (136), $Z=2$. [Hendricks and Dickinson, 1927]. The structure was refined by Chrobak [1934].

NBS lattice constants of this sample:

$$a = 7.594(1)\text{\AA}$$

$$c = 7.967(1)$$

Density

(calculated) 2.005 g/cm^3 at 25°C .

Reference intensity

$$\frac{I}{I_{\text{corundum}}} = 1.8$$

Additional patterns

1. PDF card 1-211 [Hanawalt et al., 1938].
2. Greenberg and Walden [1940].
3. Chrobak [1934].
4. PDF card 23-1010 [Swanson et al., 1971].
5. PDF card 25-262 [Technisch Physische Dienst].

References

- Chrobak, L. (1934). Z. Krist. 88, 35.
 Greenberg, A. L. and Walden, G. H., Jr. (1940).
Jour. Chem. Phys. 8, 645.
 Hanawalt, J. D., Rinn, H. W. and Frevel, L. K.
 (1938). Ind. Eng. Chem. Anal. Ed. 10, 457.
 Hendricks, S. B. and Dickinson, R. G. (1927). J.
Am. Chem. Soc. 49, 2149.
 Swanson, H. E., McMurdie, H.F., Morris, M. C.,
 Evans, E. H., Paretzkin, B. (1971). Natl. Bur.
 Std. U. S. Mono. 25, 9, 8.

$\text{CuK}\alpha_1 \lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1^\circ\text{C}$ Internal standard w, $a = 3.16524 \text{ \AA}$			
$d(\text{\AA})$	I	hkl	$2\theta (\text{)}^\circ$
5.49	100	101	16.12
5.37	50	110	16.48
3.982	50	002	22.31
3.395	20	210	26.23
3.200	25	112	27.86
3.124	30	211	28.55
2.745	70	202	32.59
2.685	90	220	33.35
2.585	17	212	34.68
2.506	12	103	35.80
2.411	8	301	37.26
2.404	8	310	37.38
2.228	20	222	40.46
2.093	9	213	43.18
2.058	6	312	43.97
2.037	12	321	44.45
1.992	20	004	45.50
1.899	14	400	47.85
1.867	9	114	48.74
1.843	8	410	49.42
1.794	8	411	50.87
1.790	7	330	50.99
1.718	5	214	53.27
1.713	8	402	53.43
1.672	8	412	54.87
1.650	4	323	55.67
1.632	5	332	56.32
1.599	18	224	57.60
1.560	5	105	59.18

Barium aluminum oxide, $\text{Ba}_3\text{Al}_2\text{O}_6$

Sample

The sample was prepared by A. E. Moore of the Cement and Concrete Association by heating BaCO_3 and Al_2O_3 in a Pt crucible at 1400 °C.

Color

Colorless

Structure

Cubic, $\text{Pa}3$ (205), $Z = 24$, isostructural with $\text{Ca}_3\text{Al}_2\text{O}_6$.

NBS lattice constant of this sample:

$$a = 16.4750(6) \text{\AA}$$

Density

(calculated) 5.008 g/cm^3

Reference intensity

$I/I_{\text{corundum}} = 1.2$

Additional patterns

1. PDF card 14-106 [Planz and Müller-Hesse, 1961].
2. PDF card 15-331 [Brisi, 1962].

References

- Brisi, C. (1962). Ann. Chim. (Rome) 52, 785.
 Planz, E. and Müller-Hesse, H. (1961). Ber. Deut. Keram. Ges. 38, 440.

$\text{CuK}\alpha_1 \lambda = 1.540598 \text{ \AA}; \text{ temp. } 25 \pm 1 \text{ }^\circ\text{C}$			
Internal standard W, $a = 3.16524 \text{ \AA}$			
$d(\text{\AA})$	I	hkl	$2\theta (\text{ }^\circ)$
5.82	3	220	15.21
4.965	3	311	17.85
4.407	1	321	20.13
4.120	35	400	21.55
3.994	1	410	22.24
3.778	9	331	23.53
3.594	2	421	24.75
3.513	2	332	25.33
3.362	3	422	26.49
3.169	13	511	28.14
3.057	6	432	29.19
3.007	14	521	29.69
2.911	100	440	30.69
2.870	3	522	31.14
2.784	2	531	32.13
2.673	2	611	33.50
2.574	1	621	34.82
2.543	2	541	35.27
2.512	2	533	35.71
2.457	2	630	36.54
2.377	20	444	37.82
2.306	7	551	39.02
2.286	1	640	39.38
2.263	4	641	39.81
2.201	5	642	40.97
2.145	5	731	42.09
2.110	1	650	42.83
2.059	30	800	43.94
2.028	1	811	44.64
2.012	6	733	45.02
1.982	1	821	45.73
1.969	2	653	46.05
1.941	5	822	46.76
1.916	2	831	47.41
1.902	3	751	47.77
1.878	3	832	48.44
1.842	15	840	49.43
1.808	5	753	50.42
1.788	2	670	51.05
1.776	2	921	51.40
1.746	1	922	52.36
1.727	3	931	52.97
1.708	1	852	53.62
1.681	20	844	54.56
1.6638	2	941	55.16
1.6557	4	933	55.45
1.6397	4	10·1·0	56.04
1.6151	2	10·2·0	56.97
1.5926	6	951	57.85
1.5706	3	10·3·1	58.74

Barium aluminum oxide, $\text{Ba}_3\text{Al}_2\text{O}_6$ (continued)

$d(\text{\AA})$	I	hkl	$2\theta (\text{\\circ})$
1.5367	2	953	60.17
1.5234	3	10·4·1	60.75
1.5039	2	10·4·2	61.62
1.4855	2	11·1·1	62.47
1.4736	2	10·5·0	63.03
1.4680	2	11·2·1	63.30
1.4561	9	880	63.88
1.4392	4	11·3·1	64.72
1.4239	2	11·3·2	65.50
1.4128	3	10·6·0	66.08
1.4075	3	11·4·1	66.36
1.3977	2	11·3·3	66.89
1.3878	2	11·4·2	67.43
1.3825	3	965	67.72
1.3731	4	12·0·0	68.25
1.3591	4	11·5·1	69.05
1.3497	3	12·2·1	69.60
1.3362	4	12·2·2	70.41
1.3233	2	11·5·3	71.20
1.3105	3	11·6·1	72.00
1.3025	6	12·4·0	72.51
1.2906	4	991	73.29
1.2825	3	10·8·1	73.83
1.2598	6	13·1·1	75.39
1.2524	4	12·5·2	75.91
1.2491	4	13·2·1	76.15
1.2418	5	12·4·4	76.68
1.2315	4	13·3·1	77.44
1.2246	4	12·6·1	77.96
1.2146	3	12·6·2	78.72
1.2049	5	13·3·3	79.48
1.1890	4	888	80.76
1.1798	4	13·5·1	81.52
1.1706	3	14·1·1	82.30

Barium chloride hydrate, BaCl₂·2H₂O

Sample

The sample was prepared by slow evaporation at room temperature of an aqueous solution of BaCl₂.

Major impurities:

0.001 to 0.1% each Al, Ca, Si, Sr

0.0003 to 0.003% Mg

Color

Colorless.

Optical data

Biaxial (+), N_α = 1.631, N_β = 1.639, N_γ = 1.658.

Structure

Monoclinic P2₁/n (14), Z=4 [Naray-Szabo and Sasvari, 1937]. The structure was determined by Jensen [1946] and refined by electron diffraction by Padmanabhan et al. [1963].

NBS lattice constants of this sample:

$$\begin{aligned} a &= 6.720(1) \text{\AA} \\ b &= 10.907(2) \\ c &= 7.135(1) \\ \beta &= 91.10(2)^\circ \end{aligned}$$

Density

(calculated) 3.103 g/cm³

Reference intensity

I/I_{corundum} = 1.6

Additional patterns

1. Jensen [1946].
2. PDF card 11-137 [Amendola, Polytech. Inst. of Brooklyn].
3. PDF card 1-0342 [Hanawalt et al., 1938].

References

- Hanawalt, J. D., Rinn, H. W., and Frevel, L. K. (1938). Ind. Eng. Chem. Anal. Ed. 10, 457.
 Jensen, A. T. (1946). Kgl. Danske Videnskab. Selskab Mat. fys. Medd. 22, No. 3.
 Naray-Szabo, S. V., and Sasvari, K. (1937). Z. Krist. 97A, 255.
 Padmanabhan, V.M., Jakkal, V.S., and Shankar, J. (1963). Indian J. Pure Appl. Phys. 1, 293.

CuK α_1 $\lambda = 1.540598 \text{\AA}$; temp. 25±1 °C

Internal standard W, a = 3.16524 Å

d (Å)	I	hkl	2θ (°)
4.50	55	111	19.72
4.42	100	111	20.05
4.33	17	021	20.49
4.23	2	120	20.99
3.661	45	121	24.29
3.622	17	121	24.56
3.569	15	002	24.93
3.390	55	012	26.27
3.359	25	200	26.51
3.240	12	031	27.51
3.213	30	210	27.74
3.200	25	130	27.86
3.048	3	112	29.28
3.003	10	112	29.73
2.948	50	211	30.29
2.928	65	131	30.51
2.908	90	131, 211	30.72
2.861	45	220	31.24
2.712	50	122	33.00
2.671	15	221	33.52
2.547	75	041, 032	35.21
2.527	18	140	35.49
2.469	10	202, 230	36.36
2.423	18	202	37.08
2.409	42	212	37.29
2.388	18	141	37.64
2.365	19	212	38.01
2.343	20	231	38.39
2.324	3	013, 231	38.72
2.256	25	103	39.93
2.229	25	103	40.44
2.214	20	222	40.72
2.209	30	113	40.82
2.148	13	301	42.02
2.116	13	240	42.68
2.085	50	311, 123	43.37
2.073	30	150, 320	43.62
2.068	35	142	43.74
2.061	25	123, 142	43.90
2.042	13	232	44.33
2.0226	12	241	44.77
1.9985	19	321	45.34
1.9886	12	033, 151	45.58
1.9069	4	330	47.65
1.8610	4	052	48.90
1.8343	3	331	49.66
1.8182	4	060	50.13
1.7834	3	004	51.18

d (Å)	I	hkl	2θ (°)
5.96	7	011	14.84
5.72	12	110	15.49
5.45	85	020	16.26
4.94	60	101	17.95
4.84	20	101	18.30

Barium molybdenum oxide, Ba₂MoO₅

Sample

The sample was prepared at NBS by T. Negas by heating BaCO₃ and MoO₃ in stoichiometric proportions at 900 °C in a gold envelope for 4 days. Fine grained material was unstable when exposed to air.

Color

Colorless

Structure

Orthorhombic, Pnam(62), Z=4, isostructural with K₂VO₂F₃. The structure of Ba₂MoO₅ was determined by Negas and Roth [1974].

NBS lattice constants of this sample:

$$a = 7.4097(7) \text{ Å}$$

$$b = 11.3906(8)$$

$$c = 5.7603(6)$$

Density

(calculated) 6.156 g/cm³

Reference intensity

I/I_{corundum} = 2.4

Additional patterns

1. Yanushkevich and Zhukovskii [1972].

References

Negas, T. and Roth, R.S. (1974). (Private communication, to be published.)

Yanushkevich, T. M. and Zhukovskii, V. M. (1972). Inorg. Materials 8, 1794.

CuKα ₁ λ = 1.540598 Å; temp. 25±1 °C Internal standard Ag, a = 4.08651 Å			
d (Å)	I	hkl	2θ (°)
6.21	6	110	14.26
5.69	3	020	15.57
5.142	2	011	17.23
4.516	2	120	19.64
4.227	2	111	21.00
3.703	2	200	24.01
3.556	16	121	25.02
3.521	19	210	25.27
3.378	7	130	26.36
3.168	100	031	28.14
3.114	45	201	28.64
3.105	65	220	28.73
3.005	60	211	29.71
2.914	4	131	30.66
2.880	45	002	31.03
2.847	1	040	31.39
2.731	20	221	32.76
2.652	13	230	33.77
2.428	7	122	36.99
2.413	18	310,141	37.23
2.258	17	240	39.90
2.230	15	212	40.42
2.191	11	132	41.16
2.176	17	150	41.46
2.111	40	222	42.80
2.101	9	241	43.01
2.070	6	330	43.70
1.950	13	232	46.53
1.941	7	250	46.77
1.898	8	060	47.88
1.866	1	340	48.76
1.852	3	400	49.15
1.839	10	251,160	49.52
1.777	9	242	51.38
1.764	16	401	51.78
1.752	6	161	52.15
1.7428	7	411	52.46
1.7373	6	152	52.64
1.7134	15	033	53.43
1.7049	4	203	53.72
1.6895	10	260	54.25
1.6860	15	213	54.37
1.6809	6	332	54.55
1.6654	12	430	55.10
1.6335	4	223	56.27
1.6214	6	261	56.73
1.6094	4	252	57.19
1.5997	1	431	57.57
1.5891	4	170	57.99
1.5848	10	062	58.16

Barium molybdenum oxide, Ba₂MoO₅ (continued)

d (Å)	I	hkl	2θ (°)
1.5660	1	342,071	58.93
1.5578	4	402	59.27
1.5559	4	143,233	59.35
1.5495	3	162	59.62
1.5028	4	422	61.67
1.4686	2	053	63.27
1.4626	2	243	63.56
1.4572	8	262,361	63.82
1.4476	3	352	64.29
1.4417	19	432	64.59
1.4372	4	450	64.82
1.4239	2	511,080	65.50
1.3984	2	180	66.85
1.3943	2	451	67.07
1.3917	5	521,172	67.21
1.3653	3	253	68.69
1.3589	5	370,181	69.06
1.3424	1	531,204	70.03
1.3384	2	343	70.27
1.3338	6	362,403	70.55
1.3283	1	163	70.89
1.3244	3	413,272	71.13
1.3144	1	540	71.75
1.3064	4	224	72.26
1.2980	1	423	72.80
1.2947	2	281	73.02
1.2919	7	461	73.20
1.2860	2	452	73.59
1.2764	3	082	74.24
1.2684	3	263	74.79
1.2656	3	234	74.98
1.2582	2	433,182	75.50
1.2474	1	190	76.27
1.2423	2	550	76.64
1.2363	3	314,091	77.08
1.2348	3	600	77.19
1.2280	4	610	77.70
1.2227	1	470	78.10
1.2194	1	191	78.35
1.2143	3	551,244	78.74
1.2069	1	620,282	79.32
1.2013	3	154,611	79.76
1.1976	3	290	80.06
1.1960	2	542,471	80.19
1.1850	2	363	81.09
1.1817	4	334,621	81.36
1.1726	4	291	82.13

Barium phosphate, $\text{Ba}_3(\text{PO}_4)_2$

Sample

The sample was prepared at NBS by heating a 3:2 molar mixture of BaCO_3 and $(\text{NH}_4)_2\text{HPO}_4$ at 950°C for one hour; after regrinding it was heated overnight at 800°C .

Color

Colorless

Structure

Hexagonal, $\bar{R}\bar{3}m$ (166), $Z=3$. The structure of $\text{Ba}_3(\text{PO}_4)_2$ was determined by Zachariasen [1948].

NBS lattice constants of this sample:

$$\begin{aligned} a &= 5.6033(1) \text{\AA} \\ c &= 20.9951(7) \end{aligned}$$

Density

(calculated) 5.253 g/cm^3

Reference intensity

$$I/I_{\text{corundum}} = 5.0$$

Additional patterns

1. PDF card 4-582 [Zachariasen, 1948].

References

Zachariasen, W. H. (1948). *Acta Cryst.* 1, 263.

$\text{CuK}\alpha_1 \lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1^\circ\text{C}$ Internal standard w, $a = 3.16524 \text{ \AA}$			
$d (\text{\AA})$	I	hkl	$2\theta (\circ)$
7.00	2	003	12.63
4.726	15	101	18.76
4.403	4	012	20.15
3.565	20	104	24.96
3.177	100	015	28.06
2.801	75	110	31.92
2.552	2	107	35.14
2.411	5	021	37.26
2.364	7	202	38.03
2.334	13	009	38.55
2.309	1	018	38.98
2.202	16	024	40.95
2.187	6	116	41.24
2.1008	35	205	43.02
1.9268	18	1·0·10	47.13
1.8865	4	027	48.20
1.8271	4	211	49.87
1.8071	1	122	50.46
1.7929	16	119	50.89
1.7318	4	214	52.82
1.6806	24	125	54.56
1.6175	13	300	56.88
1.5876	8	0·2·10	58.05
1.5645	1	217	58.99
1.5000	<1	2·0·11	61.80
1.4840	1	1·1·12	62.54
1.4682	1	306	63.29
1.4327	5	0·1·14	65.05
1.4006	12	220	66.73
1.3811	12	2·1·10	67.80
1.3431	1	131	69.99
1.3348	1	312	70.49
1.3293	5	309	70.83
1.3038	2	134	72.43
1.2814	11	315	73.90
1.2755	4	2·0·14	74.30
1.2520	8	1·1·15	75.94
1.2281	<1	137	77.69
1.2113	1	401	78.98
1.2050	1	042	79.47
1.2008	6	229	79.81
1.1878	<1	3·0·12	80.86
1.1820	1	404	81.34
1.1655	5	045	82.74
1.1610	5	1·2·14	83.13
1.1329	5	1·3·10	85.68
1.1117	<1	321	87.72
1.0891	2	324	90.03
1.0774	4	1·0·19	91.28
1.0762	8	235	91.41

Barium phosphate, $\text{Ba}_3(\text{PO}_4)_2$ (continued)

$d (\text{\AA})$	I	hkl	$2\theta (\text{\\circ})$
1.0673	<1	2·1·16	92.40
1.0589	10	410	93.35
1.0505	3	4·0·10	94.32
1.0261	2	0·1·20	97.30
1.0136	2	416	98.92
1.0056	3	0·2·19	99.99
1.0017	4	3·1·14	100.53
0.9902	5	2·2·15	102.14
.9836	4	3·2·10	103.10
.9698	2	4·0·13	105.17
.9642	5	419	106.05
.9544	2	054	107.63
.9464	7	2·1·19	108.96
.9457	3	505	109.09
.9432	4	0·4·14	109.51
.9339	3	330	111.14
.9163	2	241	114.43
.9136	2	422	114.95
.9111	3	1·2·20	115.45
.9060	<1	4·1·12	116.48
.9034	2	244	117.00
.8959	4	425	118.58
.8938	5	2·3·14	119.05
.8810	4	0·5·10	121.94
.8770	1	247	122.89
.8749	1	0·0·24	123.40
.8709	<1	511	124.39
.8685	2	152	124.98
.8670	3	339	125.36
.8597	1	514	127.27
.8540	5	1·3·19	128.84
.8533	6	155	129.03
.8444	5	4·1·15	131.63
.8404	4	2·4·10	132.88

Barium tungsten oxide, Ba₂WO₅

Sample

The sample was prepared at NBS by T. Negas by heating BaCO₃ and WO₃ in stoichiometric proportions at 900 °C in a gold envelope for 4 days.

Major impurities

0.01-0.1% Ca, Si, Sr
0.001-0.01% Cr, Mg

Color

Colorless

Structure

Orthorhombic, Pnam(62), Z=4, isostructural with K₂VO₂F₃. The structure of Ba₂WO₅ was determined by Negas and Roth [1974].

NBS lattice constants of this sample

$$a = 7.4066(6) \text{ Å}^\circ$$

$$b = 11.4785(8)$$

$$c = 5.7313(4)$$

Density

(calculated) 7.341 g/cm³

Reference intensity

I/I_{corundum} = 4.0

Additional patterns

1. PDF card 15-176 [Zhmud' and Ostapchenko, 1961].

References

Negas, T. and Roth, R.S. (1974) (private communication, to be published).

Zhmud', S. and Ostapchenko, E. P. (1961). J. Struct. Chem. (Eng. Transl.) 2, 27.

CuKα ₁ λ = 1.540598 Å; temp. 25±1 °C Internal standard Ag, a = 4.08651 Å			
d(Å)	I	hkl	2θ(°)
6.223	9	110	14.22
5.738	7	020	15.43
4.535	2	120	19.56
4.219	8	111	21.04
3.702	3	200	24.02
3.557	5	121	25.01
3.523	16	210	25.26
3.401	3	130	26.18
3.184	100	031	28.00
3.111	65	220, 201	28.67
3.002	45	211	29.74
2.924	4	131	30.55
2.864	45	002	31.20
2.735	25	221	32.72
2.661	17	230	33.65
2.603	2	112	34.42
2.565	<1	022	34.95
2.426	10	141	37.03
2.414	6	231	37.22
2.268	11	240, 202	39.70
2.223	15	311, 212	40.54
2.193	12	150, 132	41.13
2.131	6	051	42.37
2.107	35	241, 222	42.88
2.074	5	330	43.61
1.950	25	250, 232	46.54
1.913	7	060	47.48
1.852	3	160, 400	49.15
1.847	11	251	49.29
1.827	1	113	49.88
1.779	4	242	51.32
1.762	18	161, 401	51.84
1.742	8	411, 152	52.49
1.709	16	033	53.59
1.699	6	260	53.91
1.698	7	203	53.96
1.684	5	421	54.45
1.6795	12	332, 213	54.60
1.6668	12	430	55.05
1.6290	10	261	56.44
1.6277	9	223	56.49
1.6128	5	252	57.06
1.6012	2	170, 431	57.51
1.5913	8	062	57.90
1.5669	<1	342	58.89
1.5554	6	162, 402+	59.37
1.5415	1	171, 412	59.96
1.5008	4	441, 422	61.76
1.4686	2	510, 053	63.27
1.4620	9	361, 262+	63.59

Barium tungsten oxide, Ba_2WO_5 (continued)

$d(\text{\AA})$	I	hkl	$2\theta (\text{\\circ})$
1.4501	2	271,352	64.17
1.4407	17	450,432	64.64
1.4346	4	080	64.95
1.4328	8	004	65.04
1.3976	5	172	66.89
1.3676	3	181	68.56
1.3650	5	253	68.71
1.3376	1	280,362	70.32
1.3296	5	403	70.81
1.3207	1	413,134	71.36
1.3028	4	281	72.49
1.3014	4	224	72.58
1.2962	7	461	72.92
1.2877	2	452	73.48
1.2832	5	082,541	73.78
1.2700	3	263	74.68
1.2615	3	234	75.27
1.2449	2	091	76.45
1.2345	3	600	77.21
1.2278	2	191,610	77.71
1.2164	<1	551	78.58
1.2114	2	244	78.97
1.2059	1	290	79.40
1.1995	1	154	79.91
1.1961	1	542	80.18
1.1857	2	363	81.03

Calcium chloride hydrate (antarcticite), $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$

Sample

The sample was prepared by slow evaporation at room temperature of an aqueous solution of CaCl_2 . Because the sample was somewhat unstable and hygroscopic, the intensity measurements varied up to 15% in reproducibility.

Color

Colorless

Optical data

Uniaxial (-), $N_o = 1.550$, $N_e = 1.492$.

Structure

Hexagonal, $P321(150)$, $Z = 1$, isostructural with $\text{SrCl}_2 \cdot 6\text{H}_2\text{O}$, and other hexahydrates of alkaline earth halides. The structure of $\text{SrCl}_2 \cdot 6\text{H}_2\text{O}$ was determined by Jensen [1940].

NBS lattice constants of this sample:

$$a = 7.876(1)\text{\AA}$$

$$c = 3.9555(6)$$

Density

(calculated) 1.712 g/cm^3

Additional patterns

1. Herrmann [1931].
2. PDF card 1-1220 [Hanawalt et al., 1938].
3. Torii and Ossaka [1965].

References

- Hanawalt, J. D., Rinn, H. W. and Frevel, L. K. (1938). Ind. Eng. Chem. Anal. Ed. 10, 457.
 Herrmann, Z. (1931). Z. anorg. u. allgem. Chem. 197, 212.
 Jensen, A. T. (1940). Kgl. Danske Videnskab. Selskab Mat. Fys. Medd. 17, No. 9.
 Torii, T. and Ossaka, J. (1965). Science 149, 975.

$d(\text{\AA})$	I	CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1^\circ \text{C}$	
		hkl	$2\theta (\text{)}^\circ$
6.80	35	100	13.00
3.93	90	110	22.60
3.420	65	101	26.03
2.792	75	111	32.03
2.582	60	201	34.71
2.273	60	300	39.61
2.159	100	211	41.81
1.977	20	002	45.86
1.899	12	102	47.87
1.767	8	112	51.68
1.711	10	202	53.53
1.706	25	311,400	53.68
1.569	12	212	58.81
1.566	12	401,320	58.95
1.492	20	302	62.18
1.488	25	410	62.34
1.455	10	321	63.93
1.396	9	222	66.99
1.3929	9	411	67.15
1.3675	5	312	68.57
1.3129	3	330	71.85
1.2946	5	103	73.03
1.2915	4	402	73.23
1.2505	2	113	76.05
1.2295	7	203	77.59
1.2256	5	421,510	77.88
1.1895	5	412	80.71
1.1743	4	213	81.99

Calcium oxide phosphate, $\text{Ca}_4\text{O}(\text{PO}_4)_2$

Sample

The sample was prepared at NBS by E. Carlson by heating an equimolar mixture of CaHPO_4 and CaCO_3 at 1500 °C for 24 hours in platinum foil.

Major impurities

0.003 to 0.03% each Mg, Sr
0.001 to 0.1% each Ba, Fe, Pt

Color

Colorless

Structure

Monoclinic, $P2_1$ (4), $Z=4$, [Brown and Epstein, 1965]. The structure was determined by Dickens et al. [1973]. Earlier work by Trömel and Zaminer [1959] reported this phase to be orthorhombic in space group $P2_122$ (17).

NBS lattice constants of this sample:

$$\begin{aligned} a &= 7.018(1) \text{\AA} \\ b &= 11.980(2) \\ c &= 9.469(2) \\ \beta &= 90.88(2)^\circ \end{aligned}$$

Density

(calculated) 3.056 g/cm³

Reference intensity

$I/I_{\text{corundum}} = 7.3$

Additional patterns

1. PDF card 11-232 [Sarver, J.F., Penn. State Univ., University Park, Pa.]
2. Bauer and Balz [1965].

References

- Bauer, H., and Balz, W. (1965). Z. Anorg. u. allgem. Chem., 340, 225.
 Brown, W.E., and Epstein, E.F. (1965). J. Res. NBS 69A, 547.
 Dickens, B., Brown, W. E., Kruger, G. J., and Stewart, J.M. (1973). Acta Cryst. B29, 2046.
 Trömel, G., and Zaminer, C. (1959). Arch. Eisen-huettenw. 30, 205.

$\text{CuK}\alpha_1 \lambda = 1.540598 \text{\AA}; \text{ temp. } 25 \pm 1 \text{ }^\circ\text{C}$			
Internal standard W, $a = 3.16524 \text{\AA}$			
$d(\text{\AA})$	I	hkl	$2\theta (^\circ)$
6.06	4	110	14.61
5.99	5	020	14.77
5.69	4	101	15.57
4.739	3	002	18.71
4.558	5	120	19.46
4.405	2	012	20.14
4.122	14	121	21.54
4.092	20	121	21.70
3.959	2	102	22.44
3.897	3	102	22.80
3.754	4	112	23.68
3.711	8	022,112	23.96
3.684	10	031	24.14
3.511	45	200	25.35
3.473	20	130	25.63
3.366	3	210	26.46
3.302	7	201,122	26.98
3.268	16	131,122	27.27
3.190	30	211	27.95
3.160	20	211,003	28.22
3.053	80	032,013	29.23
2.995	100	040	29.80
2.895	30	103,221	30.86
2.872	45	221	31.11
2.811	25	113,132	31.81
2.789	35	023,132	32.06
2.784	35	113	32.12
2.763	50	212	32.38
2.724	40	212	32.85
2.649	14	141	33.81
2.642	18	141	33.90
2.607	12	123	34.37
2.583	6	123	34.70
2.567	5	222	34.93
2.545	9	231	35.23
2.534	16	222,231+	35.39
2.476	16	033	36.25
2.387	2	142	37.66
2.367	7	004,203	37.99
2.322	15	051,014+	38.75
2.314	12	232	38.88
2.292	12	232	39.28
2.268	5	150	39.71
2.237	7	311	40.29
2.207	12	151	40.85

Calcium oxide phosphate $\text{Ca}_4\text{O}(\text{PO}_4)_2$ (continued)

d (Å)	I	hkl	2θ (°)
2.204	9	151,024	40.92
2.173	9	043	41.53
2.137	5	052	42.26
2.130	6	321	42.40
2.109	4	302,124	42.84
2.092	3	124	43.22
2.082	4	143	43.42
2.077	10	312	43.53
2.061	3	242	43.90
2.050	9	152	44.15
2.035	3	034,233	44.49
2.018	6	330	44.88
2.012	6	233	45.03
1.990	4	322	45.55
1.976	25	204	45.88
1.963	3	134	46.22
1.948	19	134,204	46.58
1.934	6	251	46.93
1.922	4	214	47.24
1.908	20	053	47.62
1.881	6	161	48.36
1.869	11	015,313	48.67
1.865	15	303,332	48.79
1.846	8	153	49.32
1.842	10	340,313	49.43
1.837	9	243,153	49.57
1.831	13	252	49.76
1.820	12	252	50.09
1.804	13	323	50.55
1.780	4	323	51.28
1.753	25	400	52.13
1.735	8	410,260	52.72
1.724	3	342	53.07
1.708	15	261	53.59
1.7046	17	261	53.73
1.6877	5	063	54.31
1.6837	8	054,420+	54.45
1.6696	3	253	54.95
1.6624	2	170,421	55.21
1.6497	7	244	55.67
1.6327	6	262,244+	56.30
1.6221	1	412	56.70

Cobalt acetate hydrate, $\text{Co}(\text{C}_2\text{H}_3\text{O}_2)_2 \cdot 4\text{H}_2\text{O}$

Sample

The sample was prepared by slow evaporation at room temperature of an aqueous solution of $\text{Co}(\text{C}_2\text{H}_3\text{O}_2)_2$.

Color

Deep red

Structure

Monoclinic, $P2_1/c$, (14), $Z = 2$, isostructural with $\text{Ni}(\text{C}_2\text{H}_3\text{O}_2)_2 \cdot 4\text{H}_2\text{O}$. The structure of $\text{Ni}(\text{C}_2\text{H}_3\text{O}_2)_2 \cdot 4\text{H}_2\text{O}$ was determined by van Niekerk and Schoening [1953].

NBS lattice constants of this sample:

$$\begin{aligned} a &= 4.8084(9)\text{\AA} \\ b &= 11.924(2) \\ c &= 8.464(1) \\ \beta &= 94.33(1)^\circ \end{aligned}$$

Density

(calculated) 1.709 g/cm^3

Reference intensity

$I/I_{\text{corundum}} = 3.3$

Additional pattern

1. PDF card 14-718 [Hanawalt et al., 1938].

References

Hanawalt, J. D., Rinn, H. W., and Frevel, L. K. (1938). Ind. Eng. Chem. Anal. Ed. 10, 457.

van Niekerk, J. N. and Schoening, F. R. (1953). Acta Cryst. 6, 609.

$d(\text{\AA})$	$^\circ$	I	$h\bar{k}\ell$	$2\theta (\circ)$
2.980		<1	040	29.96
2.962		<1	112	30.15
2.922		3	131	30.57
2.892		4	032	30.89
2.882		3	122	31.00
2.737		<1	013	32.69
2.721		2	122	32.89
2.543		1	023	35.26
2.532		3	140	35.43
2.456		<1	113	36.56
2.451		<1	141	36.63
2.423		1	132	37.08
2.399		1	141, 200	37.46
2.306		5	211, 113	39.02
2.295		2	033, 051	39.23
2.210		1	142	40.79
2.187		1	123	41.25
2.156		<1	202	41.87
2.135		1	150, 142	42.30
2.122		<1	133, 212	42.58
2.111		<1	004	42.81
2.087		1	151	43.32
2.076		<1	014, 052	43.55
2.053		<1	151, 230	44.07
2.047		<1	043	44.21
2.026		2	222, 231	44.69
1.989		<1	024	45.57
1.965		<1	231	46.15
1.961		<1	114	46.26
1.934		<1	061	46.94
1.912		1	222	47.51
1.885		1	124	48.23
1.880		1	152, 104	48.38
1.873		1	213	48.57
1.868		2	240	48.71
1.819		<1	053	50.12
1.798		1	062	50.74
1.747		1	242	52.34
1.741		1	213	52.51
1.729		<1	153	52.91
1.722		<1	044	53.15
1.712		1	233	53.49
1.701		1	162	53.84
1.670		2	015, 071	54.92
1.6408		<1	251	56.00
1.6232		<1	025, 063	56.66
1.6162		<1	115	56.93
1.6100		1	233	57.17
1.5787		1	072, 311	58.41
1.5699		<1	171	58.77
1.5533		<1	035	59.46
1.5425		<1	115	59.92

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1^\circ \text{C}$

Internal standard W, $a = 3.16524 \text{ \AA}$

$d(\text{\AA})$	$^\circ$	I	$h\bar{k}\ell$	$2\theta (\circ)$
6.89		100	011	12.84
5.97		1	020	14.82
4.870		1	021	18.20
4.795		9	100	18.49
4.451		1	110	19.93
4.221		9	002	21.03
4.055		5	111	21.90
3.978		4	012	22.33
3.828		4	111	23.22
3.599		4	031	24.72
3.446		<1	022	25.83
3.347		<1	121	26.61
3.295		<1	102	27.04
3.175		10	112	28.08
3.058		3	130, 102	29.18

Cobalt borate, $\text{Co}_3(\text{BO}_3)_2$

Sample

Cobalt oxide (CoO) and B_2O_3 in a 3:1 molar ratio were melted together and quenched.

Major impurities:

0.1 to 1.0% each Fe, Ni
0.01 to 0.1% each Ca, Cu

Color

Strong purple

Structure

Orthorhombic, Pnmn (58), $Z=2$. The structure was determined by Berger [1949].

NBS lattice constants of this sample:

$$\begin{aligned} a &= 5.465(1) \text{\AA} \\ b &= 8.442(1) \\ c &= 4.531(1) \end{aligned}$$

Density

(calculated) 4.678 g/cm^3

Reference intensity

$$\frac{I}{I_{\text{corundum}}} = 1.4$$

Additional Patterns

1. PDF card 5-647 [Berger, 1949]

References

Berger, S. V. (1949). Acta. Chem. Scand. 3, 660.

$\text{CuK}\alpha_1 \lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1 \text{ }^\circ\text{C}$ Internal standard Ag, $a = 4.08651 \text{ \AA}$			
$d (\text{\AA})$	I	hkl	$2\theta (^\circ)$
4.223	4	020	21.02
3.994	40	011	22.24
3.489	25	101	25.51
3.226	3	111	27.63
2.734	9	200	32.73
2.689	100	121	33.29
2.503	40	130	35.85
2.391	6	031	37.58
2.341	8	201	38.42
2.295	6	220	39.23
2.255	50	211	39.95
2.190	16	131	41.19
2.093	4	102	43.19
1.805	7	141	50.52
1.800	8	321	50.68
1.744	30	202	52.43
1.678	35	132	54.64
1.613	5	150	57.04
1.582	12	051	58.26
1.569	13	321	58.81
1.544	4	042	59.85
1.529	18	330	60.52
1.4863	6	013, 142	62.43
1.4068	7	060	66.40
1.3759	10	123	68.09
1.3689	14	251	68.49
1.3661	12	400	68.65
1.3311	3	033	70.72
1.3058	5	213	72.30
1.2927	4	133, 411	73.15
1.2677	5	332	74.84

Cobalt bromide hydrate, $\text{CoBr}_2 \cdot 6\text{H}_2\text{O}$

Sample

The sample was prepared by adding HBr to CoCO_3 in water, and evaporating the solution slowly at room temperature.

Major impurities:

0.01 to 0.1% each Ca, Fe, Mg
 0.003 to 0.03% Cu
 0.001 to 0.01% each Al, Mn, Ni

Color

Very dark purplish red

Structure

Monoclinic, $P2_1$ (4), $Z=2$. The structure was determined by Stroganov et al. [1961].

NBS lattice constants of this sample:

$$\begin{aligned} a &= 9.074(2)\text{\AA} \\ b &= 7.173(1) \\ c &= 6.905(2) \\ \beta &= 94.11(2)^\circ \end{aligned}$$

Density

(calculated) 2.421 g/cm^3

Additional patterns

1. PDF card 23-184 [Mauret and Girou, 1969].

References

- Mauret, P., and Girou, A. (1969). Bull. Soc. Chim. France 1969, 2238.
 Stroganov, E. V., Andreev, S. N., Kozhina, I. I., and Solov'ev, V. E. (1961). Vestn. Leningr. Univ. Ser. Fiz. i Khim. 16, No. 3, 114.

d (Å)	I	CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1^\circ \text{C}$	
		Internal standard Ag, $a = 4.08651 \text{ \AA}$	$^\circ$
d (Å)	I	hkl	2θ ($^\circ$)
5.679	100	$\bar{1}01$	15.59
4.971	40	011	17.83
4.525	4	200	19.60
3.589	7	020	24.79
3.436	7	211	25.91
3.031	6	$\bar{1}21$	29.44
2.997	50	$\bar{1}12$	29.79
2.881	14	112	31.02
2.840	35	$\bar{2}02, \bar{3}01$	31.47
2.810	11	220	31.82
2.781	18	310	32.16
2.693	10	301	33.24
2.485	9	212, 022	36.11
2.262	15	$\bar{1}03, 400$	39.81
2.238	4	312	40.27
2.225	2	$\bar{3}21$	40.51
2.191	2	302	41.16
2.154	3	321	41.91
2.132	2	222	42.35
2.098	19	312	43.09
2.025	2	$\bar{2}13$	44.72
2.021	3	411	44.82
1.956	8	$\bar{4}02$	46.38
1.936	7	$\bar{1}32$	46.90
1.914	11	$\bar{1}23, 420$	47.46
1.893	2	$\bar{3}03$	48.01
1.873	2	$\bar{4}21$	48.57
1.793	2	040	50.88
1.755	1	510	52.06
1.716	10	313	53.33
1.667	6	$\bar{1}14, 240$	55.05
1.649	5	$\bar{2}04$	55.71
1.628	3	$\bar{4}13$	56.47
1.616	5	332	56.93

Cobalt nitrate hydrate, $\alpha\text{-Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$

Sample

The sample was prepared by slow evaporation at room temperature of an aqueous solution of $\text{Co}(\text{NO}_3)_2$ over concentrated H_2SO_4 in a desiccator.

Color

Strong reddish brown

Optical data

Biaxial (-) $N_\alpha = 1.40$, $N_\gamma = 1.549$. 2 V is medium. N_β could not be determined.

Structure

Monoclinic, I2/a(15), $Z=4$ [Jayaraman, 1958].

NBS lattice constants of this sample:

$$\begin{aligned} a &= 14.295(5)\text{\AA} \\ b &= 6.139(2) \\ c &= 12.661(2) \\ \beta &= 112.79^\circ(3) \end{aligned}$$

Density

(calculated) 1.887 g/cm^3

Reference intensity

$I/I_{\text{corundum}} = 0.7$

Polymorphism

Pouillon et al. [1965] report that three forms of $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ exist. The form reported here is stable above -18°C ; the β form, stable between -18°C and -34°C is isostructural with the room temperature form of $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$. The γ form is stable below -34°C .

Additional patterns

1. PDF card 1-317 [Hanawalt et al.].
2. PDF card 12-572 [University of Cardiff].
3. PDF card 19-357 [Weigel et al., 1964].
4. PDF card 24-335 [Weigel et al., 1964].
(Partially indexed by NBS).
5. Pouillon et al. [1965].

References

- Hanwalt, J. D., Rinn, H. W. and Frevel, L. K. (1938). Ind. Eng. Chem. Anal. Ed. 10, 457.
 Jayaraman, A. (1958). Proc. Indian Acad. Sci. A47, 147.
 Pouillon, P., Bernard, M. J. and Massaux, M. (1965). Compt. Rend. 260, 6861.
 Weigel, D., Imelik, B. and Prettre, M. (1964). Bull. Soc. Chim. France 1964, 836.

CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1^\circ\text{C}$			
Internal standard Ag, $a = 4.08651 \text{ \AA}$			
d (Å)	I	hkl	$2\theta (\circ)$
5.84	30	002	15.17
5.57	19	$\bar{2}02$	15.90
5.44	11	011	16.28
4.621	100	$\bar{2}11$	19.19
3.864	15	211	23.00
3.712	10	202	23.95
3.509	10	402	25.36
3.424	2	$\bar{2}13$	26.00
3.285	60	013	27.12
3.160	30	$\bar{2}04$	28.22
3.067	5	020	29.09
2.918	20	004	30.61
2.837	5	121	31.51
2.781	10	220	32.16
2.716	12	022	32.95
2.688	14	$\bar{2}22$	33.30
2.615	6	411	34.26
2.341	3	$\bar{2}15$	38.42
2.310	5	$\bar{4}22$	38.95
2.228	7	415	40.46
2.202	16	$\bar{2}24$	40.96
2.196	30	600	41.06
2.183	8	015	41.33
2.112	5	024	42.75
2.099	2	$\bar{2}06$	43.05
2.058	3	406	43.93
2.042	2	$\bar{5}23$	44.32
1.945	3	006	46.66
1.879	5	215	48.40
1.867	3	224	48.73
1.834	3	602	49.67
1.721	8	417	53.19
1.5796	4	408	58.37
1.4589	2	008	63.74

Lead chloride (cotunnite), PbCl_2

Sample

The sample was obtained from the National Lead Co.

Major impurities:

<0.01% each Bi and Fe
traces of Ag, Al, Ca, Cu, Mg, and Si

Structure

Orthorhombic, Pnam(62), Z=4, isostructural with PbBr_2 . The structure of PbCl_2 was determined by Bräkken and Harang [1928], and refined by Sahl and Zemann [1961].

NBS lattice constants of this sample:

$$\begin{aligned} a &= 7.6222(5) \text{\AA} \\ b &= 9.0448(7) \\ c &= 4.5348(4) \end{aligned}$$

Density

(calculated) 5.908 g/cm³

Reference intensity

$$\frac{I}{I_{\text{corundum}}} = 4.3$$

Additional patterns

1. Bräkken and Harang [1928].
2. Döll and Klemm [1939].
3. PDF card 5-0416 [Swanson et al., 1953].

References

- Bräkken, H., and Harang, L. (1928). *Z. Krist.* **68**, 123.
 Döll, W., and Klemm, W. (1939). *Z. anorg. u. allgem. Chem.* **241**, 239.
 Sahl, K., and Zemann, J. (1961). *Naturwissenschaften* **48**, 641.
 Swanson, H. E., and Fuyat, R. K. (1953). *Nat'l Bur. Std., U. S. Circ.* 539, Vol. II, 45.

$\text{CuK}\alpha_1 \lambda = 1.540598 \text{\AA}; \text{ temp. } 25 \pm 1^\circ \text{C}$			
$\text{Internal standard Ag, } a = 4.08651 \text{\AA}$			
$d (\text{\AA})$	I	hkl	$2\theta (\circ)$
5.84	1	110	15.17
4.523	14	020	19.61
4.057	35	011	21.89
3.890	75	120	22.84
3.810	40	200	23.33
3.579	100	111	24.86
3.512	2	210	25.34
2.953	6	121	30.24
2.915	20	201, 220	30.64
2.802	5	130	31.91
2.776	55	211	32.22
2.510	45	031	35.74
2.453	2	221	36.61
2.446	2	310	36.71
2.385	5	131	37.69
2.364	4	230	38.03
2.267	25	002	39.73
2.261	25	040	39.84
2.214	25	320	40.72
2.168	8	140	41.63
2.152	35	311	41.95
2.096	40	231	43.12
2.027	2	022	44.67
1.992	2	321	45.51
1.959	18	122	46.31
1.948	14	202	46.58
1.944	13	240, 330	46.69
1.905	6	400, 212	47.69
1.865	1	410	48.80
1.789	5	222	51.01
1.7629	1	132	51.82
1.7566	1	401, 420	52.02
1.7243	2	411	53.07
1.6889	3	340	54.27
1.6806	2	051	54.56
1.6405	12	151	56.01
1.6365	8	232	56.16
1.6105	1	430	57.15
1.6010	6	042	57.52
1.5844	13	322	58.18
1.5667	4	142	58.90
1.5179	5	431	60.99
1.5077	3	060	61.45
1.5035	2	510	61.64
1.4911	1	013	62.21
1.4787	2	160	62.79
1.4759	4	242, 332	62.92
1.4634	4	113	63.52
1.4591	6	402	63.73
1.4573	4	440	63.82

Lead chloride (cotunnite), PbCl_2 - continued

$d (\text{\AA})$	I	hkl	$2\theta (\text{\\circ})$
1.4450	3	520	64.43
1.4272	7	511	65.33
1.4017	11	260, 351	66.67
1.3889	3	213, 422	67.37
1.3545	4	342	69.32
1.3514	4	033	69.50
1.3395	1	261	70.21
1.3304	1	133	70.76
1.3130	1	432	71.84
1.3027	1	531	72.50
1.2964	1	360	72.91
1.2858	3	313	73.61
1.2736	4	170, 233	74.43
1.2703	3	600	74.66
1.2641	2	540	75.09
1.2554	2	062	75.70
1.2529	2	512	75.88
1.2427	2	071	76.61
1.2386	2	162	76.91
1.2261	2	171, 442	77.84
1.2232	2	601, 620	78.06
1.2184	4	522	78.43
1.2123	2	611	78.90

Magnesium titanium oxide, Mg_2TiO_4

Sample

The sample was prepared by heating together TiO_2 and $MgCO_3$ at $1380^\circ C$, grinding and re-heating.

Color

Colorless

Optical data

Isotropic, $N = 1.95$

Structure

Cubic, $Fd\bar{3}m$ (227), $Z=8$, inverse spinel type [Barth and Posnjak, 1932].

NBS lattice constants of this sample:

$$a = 8.4409(3)\text{\AA}$$

Density

(calculated) 3.546 g/cm^3

Reference intensity

$I/I_{\text{corundum}} = 2.1$

Additional patterns

1. PDF card 3-858 [Hanawalt et al., 1938].
2. Holgersson and Herrlin [1931].
3. Barth and Posnjak [1932].

$d(\text{\AA})$	I	CuK α_1 $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1^\circ C$	
		hkl	$2\theta (\circ)$
4.876	45	111	18.18
2.986	20	220	29.90
2.544	100	311	35.25
2.435	2	222	36.88
2.110	60	400	42.82
1.936	<1	331	46.88
1.722	6	422	53.13
1.624	30	511	56.62
1.492	50	440	62.18
1.4268	3	531	65.35
1.3346	1	620	70.50
1.2874	6	533	73.50
1.2724	2	622	74.51
1.2185	5	444	78.42
1.1820	2	551	81.34
1.1280	1	642	86.14
1.0989	9	731	89.01
1.0551	5	800	93.78
0.9948	1	822	101.49
.9747	6	751	104.43
.9682	1	662	105.42
.9438	3	840	109.41
.9265	1	911	112.48
.8997	1	664	117.77

References

- Barth, T.F.W. and Posnjak, E. (1932). Z. Krist. 82, 325.
 Hanawalt, J. D., Rinn, H. W., and Frevel, L. K. (1938). Ind. Eng. Chem., Anal. Ed. 10, 457.
 Holgersson, S. and Herrlin, A. (1931). Z. anorg. u. allgem. Chem. 198, 69.

Nickel nitrate hydrate, $\text{Ni}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$

Sample

The sample was prepared by slow evaporation of an aqueous solution of $\text{Ni}(\text{NO}_3)_2$.

Color

strong brilliant green

Structure

Triclinic, $Z = 2$ [Weigel et al., 1962].

NBS lattice constants of this sample:

$$a = 7.699(4)\text{\AA}$$

$$b = 11.677(2)$$

$$c = 5.799(2)$$

$$\alpha = 98.56(3)^\circ$$

$$\beta = 102.22(3)$$

$$\gamma = 105.80(2)$$

Density

(calculated) 2.019 g/cm^3

Reference intensity

$$I/I_{\text{corundum}} = 2.2$$

Additional pattern

1. PDF card 14-452 [Weigel et al., 1962].

Reference

Weigel, D.A., Imelick, B. and Lafitte, P. (1962).
Bull. Soc. Chim. France 1962, 544.

$$\text{CuK}\alpha_1 \lambda = 1.540598 \text{ \AA}; \text{ temp. } 25 \pm 1 \text{ }^\circ\text{C}$$

$$\text{Internal standard Si, } a = 5.43088 \text{ \AA}$$

$d(\text{\AA})$	I	$h\bar{k}\ell$	$2\theta (^\circ)$
10.93	7	010	8.08
7.11	2	110	12.44
5.48	100	020	16.16
5.27	6	110	16.81
5.07	20	101	17.48
4.65	2	111	19.09
4.56	1	111,011	19.47
4.405	6	021	20.14
4.124	6	111	21.53
3.901	3	101	22.78
3.808	12	120	23.34
3.761	25	121,210	23.64
3.652	4	030	24.35
3.546	1	220	25.09
3.526	1	021	25.24

$d(\text{\AA})$	I	$h\bar{k}\ell$	$2\theta (^\circ)$
3.413	16	031	26.09
3.348	4	111	26.60
3.141	3	211	28.39
3.084	3	230	28.93
2.931	2	131	30.47
2.905	14	130	30.75
2.882	5	140	31.01
2.832	5	221,012	31.57
2.741	65	040	32.64
2.691	4	201	33.27
2.606	2	240	34.39
2.552	13	012	35.14
2.483	2	032,212	36.14
2.455	1	122	36.57
2.435	<1	321	36.88
2.430	1	211,122	36.96
2.390	3	141	37.61
2.375	4	102	37.85
2.322	2	231	38.75
2.319	2	222,131	38.80
2.282	5	222	39.46
2.212	3	051	40.75
2.200	2	042,250	40.99
2.166	4	340	41.66
2.146	2	221,132	42.08
2.063	3	341,222	43.84
2.030	1	151	44.60
2.006	2	251	45.16
1.996	2	151	45.40
1.991	2	241	45.52
1.980	4	122	45.78
1.931	1	150,113	47.01
1.912	3	161,103	47.52
1.903	2	240,411 +	47.76
1.884	3	260	48.27
1.863	1	061,311	48.86
1.843	5	331,003 +	49.41
1.828	2	152,060	49.85
1.807	<1	213	50.46
1.736	<1	360	52.67
1.733	<1	113	52.79
1.714	2	043	53.42
1.708	4	161,062	53.62

Potassium chromium oxide sulfate, $K_2(CrO_4)_{0.67}(SO_4)_{0.33}$

Sample

The sample was prepared by melting together a 1:2 molar mixture of K_2SO_4 and K_2CrO_4 and annealing at about 600 °C for 18 hours.

Major impurities

0.001-0.01% each Al, Ba

0.003-0.03% Si

0.01-0.1% Ca

Color

Brilliant yellow

Structure

Orthorhombic, Pnam(62), Z=4. There is a complete solid solution series between K_2SO_4 and K_2CrO_4 [Groschuff, 1908], isostructural with low K_2SO_4 . The structure of low K_2SO_4 was determined by Ehrenberg and Hermann [1929].

NBS lattice constants of this sample

$$a = 7.6095(9)\text{ Å}$$

$$b = 10.300(1)$$

$$c = 5.8737(8)$$

Density

(calculated) 2.707 g/cm³

Reference intensity

$$I/I_{\text{corundum}} = 1.2$$

Polymorphism

This composition inverts at about 650 °C to a hexagonal form [Groschuff, 1908].

References

Ehrenberg, W. and Hermann, C. (1929). Z. Krist. 70, 163.

Groschuff, E. (1908). Z. anorg. Chem. 58, 107.

CuKα₁ λ = 1.540598 Å; temp. 25±1 °C

Internal standard W, a = 3.16524 Å

d (Å)	°	I	hkl	2θ (°)
3.060		55	220	29.16
3.050		70	211	29.26
2.963		100	031	30.14
2.937		60	002	30.41
2.763		1	131	32.38
2.714		6	221	32.98
2.647		2	112	33.83
2.575		14	040	34.81
2.549		18	022, 230	35.18
2.462		20	310	36.46
2.440		4	140	36.80
2.419		6	122	37.14
2.339		2	231	38.46
2.268		25	212	39.70
2.253		12	141	39.99
2.141		9	132	42.17
2.133		10	240	42.34
2.120		20	321, 222	42.61
2.040		6	330	44.37
2.004		2	241	45.20
1.988		3	150	45.59
1.944		2	051	46.68
1.925		9	232	47.17
1.903		8	400	47.75
1.888		5	312	48.16
1.865		<1	113	48.80
1.810		5	250, 401	50.37
1.808		4	340	50.45
1.783		2	411	51.20
1.779		1	123	51.32
1.741		2	203	52.53
1.7272		6	341	52.97
1.7170		8	060, 213	53.31
1.7008		10	033	53.86
1.6646		4	430	55.13
1.6601		3	133	55.29
1.6470		2	152	55.77
1.6099		2	161	57.17
1.6004		5	431	57.54
1.5966		6	402	57.69
1.5779		2	412	58.44
1.5643		2	260	59.00
1.5530		<1	233	59.47
1.5391		3	342	60.06
1.5327		2	313	60.34
1.5270		2	143	60.59
1.5119		2	261	61.26
1.4820		7	062	62.63
1.4682		7	004	63.29
1.4593		8	520	63.72

Potassium chromium oxide sulfate, $K_2(CrO_4)_{.33}(SO_4)_{.67}$

Sample

The sample was prepared by melting together a 2:1 molar mixture of K_2SO_4 and K_2CrO_4 , and annealing at 600 °C for 18 hours.

Color

Brilliant yellow

Major impurities

0.001-0.01% each Al, Ba
0.003-0.03% Si
0.01-0.1% Ca

Structure

Orthorhombic, Pnam (62), Z=4. There is a complete solid solution series between K_2SO_4 and K_2CrO_4 [Groschuff, 1908], isostructural with low K_2SO_4 . The structure of low K_2SO_4 was determined by Ehrenberg and Hermann [1929].

NBS lattice constants of this sample:

$$\begin{aligned} a &= 7.551(2)\text{\AA} \\ b &= 10.195(2) \\ c &= 5.825(1) \end{aligned}$$

Density

(calculated) 2.679 g/cm³

Reference intensity

$I/I_{\text{corundum}} = 1.1$

Polymorphism

This composition inverts at about 620 °C to a hexagonal form. [Groschuff, 1908].

References

Ehrenberg, W. and Hermann, C. (1929). Z. Krist. 70, 163.
Groschuff, E. (1908). Z. anorg. Chem. 58, 107.

CuK α_1 $\lambda = 1.540598 \text{\AA}$; temp. 25±1 °C Internal standard Ag, $a = 4.08651 \text{\AA}$			
$d(\text{\AA})$	I	hkl	$2\theta (\text{°})$
5.10	10	020	17.38
5.06	5	011	17.50
4.221	30	120	21.03
4.203	30	111	21.12
3.778	25	200	23.53
3.538	6	210	25.15
3.420	10	121	26.03
3.168	8	201	28.14
3.099	5	130	28.78
3.027	75	211	29.48
2.935	100	031	30.43
2.912	60	002	30.68
2.691	6	221	33.27
2.626	2	112	34.11
2.548	13	040	35.19
2.527	15	022, 230	35.49
2.443	30	310	36.76
2.413	4	140	37.23
2.398	8	122	37.48
2.249	18	212	40.05
2.230	12	141	40.42
2.122	8	132	42.57
2.112	10	240	42.78
2.100	20	222	43.03
2.022	5	330	44.79
1.986	2	241	45.64
1.969	3	150	46.07
1.908	9	232	47.61
1.888	6	400	48.15
1.871	4	312	48.61
1.794	4	250	50.84
1.769	2	411	51.64
1.727	2	203	52.98
1.710	5	242	53.53
1.700	6	060	53.89
1.685	10	033	54.39

Potassium rubidium chromium oxide, $KRbCrO_4$

Sample

The sample was prepared by melting together a 1:1 molar mixture of K_2CrO_4 and Rb_2CrO_4 and annealing the product at 600 °C for 18 hours.

Major impurities

0.001-0.01% Ag
0.003-0.03% Mg
0.01-0.1% each Al, Ba, Ca
0.03-0.3% Si

Color

Brilliant yellow

Structure

Orthorhombic, Pnam(62), Z=4, isostructural with low K_2SO_4 . The structure of low K_2SO_4 was determined by Glossner [1928]. $KRbCrO_4$ is the midpoint in the complete solid solution series between K_2CrO_4 and Rb_2CrO_4 [Samuseva et al. 1967].

NBS lattice constants of this sample:

$$\begin{aligned} a &= 7.853(1) \text{\AA} \\ b &= 10.517(1) \\ c &= 5.9969(9) \end{aligned}$$

Density

(calculated) 3.226 g/cm³

Reference intensity

$I/I_{\text{corundum}} = 2.3$

Polymorphism

This composition inverts at about 630 °C to a high temperature crystal modification, presumably isostructural with high K_2SO_4 [Samuseva et al. 1967].

References

- Glossner, B. (1928). Neues Jahrb. Mineral. Geol. Beilage B. 57A, 89.
 Samuseva, R.G., Okunev, Y.A., and Plyushcheyev, V.E. (1967). Russ. J. Inorg. Chem. (English Transl.), 12, 1489.

CuK α $\lambda = 1.540598 \text{\AA}$; temp. 25±1 °C

Internal standard W, $a = 3.16524 \text{\AA}$

d(Å)	°	I	hkl	2θ(°)
3.136		85	211	28.44
3.026		100	031	29.49
2.997		70	002	29.79
2.785		10	221	32.11
2.706		1	112	33.08
2.629		13	040	34.08
2.614		20	230	34.27
2.539		30	310	35.32
2.493		4	140	36.00
2.472		11	122	36.31
2.396		4	231	37.51
2.339		14	311	38.45
2.324		18	212	38.71
2.302		9	141	39.09
2.184		14	240, 321	41.30
2.171		25	222	41.57
2.098		6	330	43.09
2.053		4	241	44.07
2.031		5	150	44.57
1.984		2	051	45.68
1.971		18	232	46.02
1.938		9	312	46.83
1.866		6	401	48.75
1.854		4	340, 250	49.09
1.837		4	411	49.59
1.818		2	123	50.15
1.781		4	203	51.26
1.772		10	341, 251	51.52
1.756		9	213	52.03
1.753		7	060	52.14
1.737		14	033	52.66
1.713		5	430	53.46
1.696		1	133	54.02
1.682		5	152	54.52
1.646		4	431, 161	55.80
1.643		4	402	55.93
1.623		3	412	56.68
1.600		3	260	57.54
1.578		3	342, 252	58.43
1.5713		2	313	58.71
1.5466		4	261	59.74
1.5132		6	062	61.20
1.5041		10	511	61.61
1.4995		10	004	61.82
1.4874		8	432	62.38
1.4753		2	170, 243	62.95
1.4581		3	114, 071	63.78
1.4356		1	450	64.90
1.4126		7	262	66.09
1.4010		3	403, 204	66.71
1.3886		2	413, 214	67.38

Silver chromium oxide, Ag_2CrO_4

Sample

The sample was prepared at NBS by adding AgNO_3 in aqueous solution to one of K_2CrO_4 . The precipitate was washed and dried.

Color

Dark grayish brown

Optical data

Opaque

Structure

Orthorhombic, $\text{Pmnb}(62)$, $Z = 4$. The structure of Ag_2CrO_4 was determined by Hackert and Jacobson [1971].

NBS lattice constants of this sample:

$$a = 7.0220(9)\text{\AA}$$

$$b = 10.065(2)$$

$$c = 5.5380(7)$$

Density

(calculated) 5.629 g/cm^3

Reference intensity

$I/I_{\text{corundum}} = 3.8$

Polymorphism

Pistorius [1967] reports that Ag_2CrO_4 inverts to a hexagonal form above 479°C .

Additional pattern

1. PDF card 20-1055 [Kloberstein and Backmann, Degussa Forschung Chemie, Frankfurt-am-Main, Germany, 1967].

References

Hackert, M.L. and Jacobson, R.A. (1971). J. Solid State Chem. 3, 364.

Pistorius, C. W. F. T. (1967). J. Chem. Phys. 46, 2167.

$$\text{CuK}\alpha_1 \lambda = 1.540598 \text{ \AA}; \text{ temp. } 25 \pm 1^\circ\text{C}$$

$$\text{Internal standard W, } a = 3.16524 \text{ \AA}$$

$d(\text{\AA})$	I	hkl	$2\theta (\text{)}^\circ$
5.03	8	020	17.62
4.86	1	011	18.24
4.087	12	120	21.73
3.994	3	111	22.24
3.512	5	200	25.34
2.879	75	220	31.04
2.870	100	031	31.14
2.844	90	211	31.43
2.769	40	002	32.30
2.671	4	021	33.53

$d(\text{\AA})$	I	hkl	$2\theta (\text{)}^\circ$
2.657	11	131	33.70
2.557	3	221	35.07
2.516	2	040	35.65
2.426	3	022	37.02
2.369	1	140	37.95
2.293	13	122	39.26
2.174	1	202	41.51
2.157	1	301	41.85
2.136	1	032	42.28
2.122	5	320	42.56
2.109	1	311	42.85
2.045	19	240, 132	44.26
1.996	19	222	45.41
1.892	5	051	48.06
1.827	1	151	49.86
1.814	5	331	50.25
1.785	1	103	51.12
1.755	11	400	52.06
1.684	3	322	54.43
1.677	5	060	54.69
1.665	5	251	55.10
1.645	16	242	55.86
1.631	4	160	56.37
1.6172	11	033	56.89
1.6125	20	213	57.07
1.5757	2	133	58.53
1.4971	12	431	61.93
1.4827	8	402	62.60
1.4348	3	062	64.94
1.4218	<1	422	65.61
1.4053	3	162	66.48
1.3847	3	004	67.60
1.3639	2	360	68.77
1.3607	2	053	68.96
1.3311	1	333	70.72
1.2938	3	271	73.08
1.2878	2	204	73.48
1.2690	1	253	74.75
1.2581	1	080	75.50
1.2477	2	224	76.25
1.2226	1	163	78.11
1.2124	2	460	78.89
1.1952	<1	144	80.25
1.1895	1	433	80.72
1.1463	4	244	84.44
1.1376	3	611	85.24
1.1107	2	513	87.82

Strontium nitrate, Sr(NO₃)₂

Sample

The sample was specially purified material from the Mallinckrodt Chemical Works, New York.

Color

Colorless

Optical data

Isotropic N = 1.587

Structure

Cubic, P2₁3 (198), Z = 4, isostructural with Ba(NO₃)₂. The structure of Ba(NO₃)₂ was determined by Birnstock [1967]. Previously the space group for Sr(NO₃)₂ was considered to be Pa3 (205).

NBS lattice constants of this sample:

$$a = 7.7813(2) \text{ \AA}^{\circ}$$

Density

(calculated) 2.984 g/cm³

Reference intensity

I/I_{corundum} = 3.5

Additional patterns

1. Vegard [1922].
2. PDF card 4-310 [Swanson and Tatge, 1953].

References

- Birnstock, R., (1967). Z. Krist. 124, 310.
 Swanson, H. E. and Tatge, E. (1953). Natl. Bur. Std. U. S. Circ. 539, 1, 80.
 Vegard, L. (1922). Z. Phys. 9, 395.

d (Å)	°	I	hkl	2θ (°)
1.887		1	410	48.18
1.834		1	411	49.68
1.786		12	331	51.10
1.740		10	420	52.54
1.698		<1	421	53.94
1.660		<1	332	55.31
1.588		6	422	58.02
1.556		<1	430	59.34
1.527		1	510	60.61
1.497		9	511	61.92
1.445		1	520	64.44
1.421		<1	521	65.64
1.3752		6	440	68.13
1.3342		1	530	70.53
1.3156		10	531	71.68
1.2968		4	600	72.88
1.2792		1	610	74.05
1.2625		<1	611	75.20
1.2303		2	620	77.53
1.2155		<1	621	78.65
1.1866		3	533	80.96
1.1731		4	622	82.09
1.1599		1	630	83.23
1.1473		<1	631	84.35
1.1232		1	444	86.60
1.0896		2	711	89.98
1.0791		1	640	91.10
1.0688		<1	720	92.23
1.0588		<1	721	93.36
1.0398		2	642	95.60
1.0307		<1	722	96.72
1.0131		4	731	98.99
0.9962		<1	650	101.29
.9884		<1	732	102.40
.9728		<1	800	104.72
.9652		<1	810	105.90
.9506		<1	733	108.25
.9437		2	820	109.43
.9368		<1	821	110.63
.9170		2	822	114.29
.9044		1	831	116.79
.8985		2	751	118.03
.8925		1	662	119.32
.8867		<1	832	120.62
.8700		1	840	124.61
.8541		3	911	128.81
.8490		1	842	130.28

CuKα₁ λ = 1.540598 Å; temp. 25±1 °C

Internal standard Si, a = 5.43088 Å

d (Å)	°	I	hkl	2θ (°)
4.494		100	111	19.74
3.890		15	200	22.84
3.480		25	210	25.58
3.177		16	211	28.06
2.753		20	220	32.50
2.595		1	221	34.54
2.346		65	311	38.33
2.245		55	222	40.13
2.081		1	321	43.46
1.947		14	400	46.62

Strontium tungsten oxide, Sr_2WO_5

Sample

The sample was prepared at NBS by T. Negas by heating SrCO_3 and WO_3 in stoichiometric proportions at 950°C in a gold envelope for 2 weeks.

Color

Colorless

Structure

Orthorhombic, Pnam (62), $Z = 4$, isostructural with $\text{K}_2\text{VO}_2\text{F}_3$. The structure of Sr_2WO_5 was determined by Negas and Roth [1974].

NBS lattice constants of this sample:

$$\begin{aligned} a &= 7.2506(4)\text{\AA} \\ b &= 10.8963(7) \\ c &= 5.5480(4) \end{aligned}$$

Density

(calculated) 6.654 g/cm^3

Reference intensity

$I/I_{\text{corundum}} = 5.7$

Reference

Negas, T. and Roth, R. S. (1974). Private communication (to be published).

$\text{CuK}\alpha_1 \lambda = 1.540598 \text{ \AA}; \text{ temp. } 25 \pm 1^\circ\text{C}$

Internal standard Si, $a = 5.43088 \text{ \AA}$

$d(\text{\AA})$	I	hkl	$2\theta (\text{)}^\circ$
6.04	11	110	14.66
5.45	13	020	16.26
4.95	3	011	17.91
4.356	9	120	20.37
4.085	30	111	21.74
3.626	5	200	24.53
3.440	10	210	25.88
3.037	100	031, 201	29.39
3.020	30	220	29.56
2.923	30	211	30.56
2.804	4	131	31.89
2.774	35	002	32.24
2.652	17	221	33.77
2.567	11	230	34.93
2.551	4	140	35.15

$d(\text{\AA})$	I	hkl	$2\theta (\text{)}^\circ$
2.521	2	112	35.58
2.473	1	022	36.30
2.329	7	231	38.63
2.318	6	141	38.82
2.204	4	202	40.92
2.178	7	240	41.42
2.172	6	311	41.55
2.159	11	212	41.80
2.109	2	132	42.84
2.088	4	150	43.30
2.052	5	321	44.09
2.043	25	222	44.31
2.028	7	051, 241	44.64
2.013	3	330	45.00
1.954	<1	151	46.43
1.884	14	232	48.28
1.868	4	250	48.71
1.817	6	060	50.18
1.812	4	400	50.31
1.798	3	312	50.74
1.789	1	410	51.02
1.7699	12	251	51.60
1.7616	3	160	51.86
1.7231	12	401	53.11
1.7135	3	242	53.43
1.7023	2	123, 411	53.81
1.6680	1	152	55.01
1.6473	16	033, 203	55.76
1.6429	12	421	55.92
1.6285	8	213, 332	56.46
1.6227	10	260, 430	56.68
1.6066	1	133	57.30
1.5767	4	223	58.49
1.5583	4	261	59.25
1.5493	4	252	59.63
1.5191	8	062	60.94
1.5026	2	412	61.68
1.4998	3	233	61.81
1.4971	3	143	61.93
1.4870	3	162	62.40
1.4676	1	171	63.32
1.4618	1	422	63.60
1.4520	<1	360	64.08
1.4376	1	510	64.80
1.4181	1	323	65.80
1.4101	2	053, 243	66.22
1.4047	5	361	66.51
1.3999	14	432	66.77
1.3973	7	352	66.91
1.3869	5	004	67.48

Strontium tungsten oxide, Sr_2W_5 - continued

$d(\text{\AA})$	I	hkl	$2\theta (\text{\\circ})$
1.3621	1	080,333	68.88
1.3586	1	521	69.08
1.3516	1	114,451	69.49
1.3442	1	024	69.93
1.3343	2	172	70.52
1.3220	1	124	71.28
1.3143	3	253	71.76
1.3013	1	181	72.59
1.2946	4	403	73.03
1.2859	1	214,362	73.60
1.2760	1	512,163	74.27
1.2751	1	134,280	74.33
1.2598	5	224,423	75.39
1.2506	4	552	76.04
1.2474	4	541	76.27
1.2458	4	452	76.39
1.2426	3	281	76.62
1.2224	3	082	78.12
1.2198	5	263,234	78.32
1.2082	1	600	79.22
1.2009	<1	610	79.80
1.1827	1	091	81.28
1.1801	1	620,551	81.50
1.1752	1	173	81.91
1.1698	1	244	82.37
1.1672	2	191	82.59
1.1623	1	542	83.02
1.1585	1	282	83.35
1.1553	2	154,471	83.63
1.1542	1	621	83.73
1.1483	1	290	84.26
1.1464	1	630	84.43
1.1422	2	363,334	84.82
1.1248	1	291	86.45
1.1230	3	631	86.62
1.1135	1	254 ..	87.54
1.1079	1	602	88.10
1.1023	3	064,612	88.66
1.0962	<1	414	89.29
1.0913	1	115,382	89.80
1.0898	1	164,0\\cdot10\\cdot0	89.95
1.0832	1	641	90.66
1.0823	1	390	90.75
1.0690	1	481	92.21
1.0679	1	373	92.33
1.0610	4	292,205	93.11
1.0558	2	215	93.70
1.0541	6	463,434	93.90
1.0499	2	135,283	94.39
1.0414	1	225	95.41

Telluric Acid, H_6TeO_6

Sample

The sample was obtained from K&K Laboratories,
Plainview, N.J.

Major impurities

0.01-0.1% Ca

0.001-0.01% Fe

Color

Colorless

Structure

Monoclinic, $P2_1/c$ (14), $Z=4$ [Gossner and Kraus, 1934]. The structure was determined by Lindqvist [1970] who confirmed this space group. Other space groups have been reported by Aviness and Petit [1968] and by Bayer [1968]. The NBS data could also be indexed on these space groups.

NBS lattice constants for this sample:

$$a = 6.4979(6) \text{ \AA}^\circ$$

$$b = 9.3223(9)$$

$$c = 8.3334(9)$$

$$\beta = 99.69(1)^\circ$$

Density

(calculated) 3.065 g/cm^3

Reference intensity

$$\frac{I}{I_{\text{corundum}}} = 5.9$$

Polymorphism

Three forms of H_6TeO_6 have been reported. The cubic phase transforms to either the monoclinic or tetragonal phase depending on conditions of humidity and temperature. It was not possible to convert the monoclinic phase into the cubic form in either dry or moist air; this suggests that the monoclinic phase is the stable modification [Bayer, 1968].

Additional patterns

1. PDF card 21-388 [Bayer, 1968]
2. PDF card 24-1266 [Lindqvist, 1970]
3. Aviness and Petit [1968]

References

- Aviness, C. and Petit, H. (1968). Compt. Rend. 266, 981.
 Bayer, G. (1968). J. Less-Common Metals 16, 215.
 Gossner, B. and Kraus, O. (1934). Z. Krist. 88, 298.
 Lindqvist, O. (1970). Acta Chem. Scand. 24, 3178.

$\text{CuK}\alpha_1 \lambda = 1.540598 \text{ \AA}; \text{ temp. } 25 \pm 1 \text{ }^\circ\text{C}$			
$\text{Internal standard Ag, } a = 4.08651 \text{ \AA}$			
$d(\text{\AA})$	I	hkl	$2\theta (^\circ)$
4.75	100	$\bar{1}11$	18.65
4.67	45	020	19.00
4.183	65	111	21.22
4.107	30	002	21.62
3.485	1	$\bar{1}12$	25.54
3.203	7	200	27.83
3.083	11	022	28.94
2.761	4	$\bar{2}02$	32.40
2.708	7	$\bar{1}31, 211$	33.05
2.639	20	220	33.94
2.622	4	$\bar{2}21$	34.17
2.589	25	131	34.62
2.582	30	$\bar{1}13$	34.72
2.376	5	$\bar{2}22$	37.83
2.331	3	040	38.60
2.303	2	113	39.08
2.243	2	041	40.18
2.2361	1	$\bar{1}32$	40.30
2.1013	5	$\bar{3}11$	43.01
2.0925	8	222, 231	43.20
2.0536	2	033, 004	44.06
2.0475	4	$\bar{2}23$	44.20
2.0322	5	133	44.55
2.0274	4	042	44.66
1.9932	<1	$\bar{3}12$	45.47
1.9431	6	311	46.71
1.8879	13	133, 142	48.16
1.8839	16	240, $\bar{1}24$	48.27
1.8791	16	024, $\bar{2}04$	48.40
1.8055	4	$\bar{3}13$	50.51
1.7808	5	223, $\bar{2}42$	51.26
1.7718	6	$\bar{3}31$	51.54
1.7667	6	$\bar{1}51$	51.70
1.7422	4	$\bar{2}24$	52.48
1.7321	3	124, 151	52.81
1.6738	4	331	54.80
1.6525	4	242	55.57
1.6346	4	$\bar{1}15$	56.23
1.6133	1	152	57.04
1.6102	1	204	57.16
1.6007	1	400, 134	57.53
1.5839	3	$\bar{3}33, \bar{3}41$	58.20
1.5535	1	060	59.45
1.5399	4	044, 313	60.03
1.5320	2	$\bar{3}24, \bar{1}53$	60.37
1.5216	2	224	60.83
1.5146	2	420	61.14
1.5121	3	341	61.25
1.5106	3	115, 160	61.32
1.5002	2	422	61.79

Telluric Acid, H_6TeO_6 (continued)

$d(\text{\AA})$	I	hkl	$2\theta (\text{\\circ})$
1.4665	3	153	63.37
1.4626	4	244	63.56
1.4534	1	062,035	64.01
1.4247	<1	423	65.46
1.4136	1	402	66.04
1.4102	2	351	66.22
1.4064	2	315	66.42
1.3977	1	260,412	66.89
1.3949	1	261,333	67.04
1.3800	1	404,054	67.86
1.3765	1	352	68.06
1.3731	2	135	68.25
1.3595	1	351	69.03
1.3540	3	016,262	69.35
1.3426	<1	206,045	70.02
1.3234	2	424,254	71.19
1.3099	3	353	72.04
1.2946	2	262,171	73.03
1.2868	1	511,432	73.54
1.2809	<1	500,171	73.94
1.2396	1	155,522	76.84
1.2325	1	055,513	77.36
1.2236	1	361,511	78.03
1.2086	<1	442	79.19
1.1973	3	264,353	80.09
1.1934	2	521,173	80.40
1.1878	1	532,444	80.86
1.1808	1	117,344	81.44
1.1710	<1	404	82.27

Zinc nitrate hydrate, $\alpha\text{-Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$

Sample

The sample was prepared by slow evaporation at room temperature of an aqueous solution of $\text{Zn}(\text{NO}_3)_2$. Because of instability and strong cleavage the intensities are subject to some error.

Major impurities:

0.001-0.01% each Ag, Ba, Cr, Si, Sr
0.003-0.03% Fe
0.01-0.1% Ca

Color

Colorless

Structure

Orthorhombic, $\text{Pn}2_1\text{a}$ (33), $Z=4$. The structure was determined by Ferrari et al. [1967]. It is isostructural with $\beta\text{-Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ [Pouillon et al., 1965].

NBS lattice constants of this sample:

$$\begin{aligned} a &= 12.372(3)\text{\AA} \\ b &= 12.902(3) \\ c &= 6.302(2) \end{aligned}$$

Density

(calculated) 1.964 g/cm^3

Polymorphism

Pouillon [1960] reports polymorphic transformations of $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ at $+19^\circ$ and -13°C ; however Weigel et al [1964] did not find a transition at -13°C .

Additional patterns

1. PDF card 19-1465 [Weigel et al., 1964].
2. Pouillon et al., [1965].

References

- Ferrari, A., Braibanti, A., Manotti-Lanfredi, A.N. and Tirificchio, A. (1967). Acta Cryst. 22, 240.
 Pouillon, P. (1960). Compt. Rend. 250, 3318.
 Pouillon, P., Bernard, M. J., and Massaux, M. (1965). Compt. Rend. 260, 6861.
 Weigel, D., Imelik, B., and Prettre, M. (1964). Bull. Soc. Chem. France 1964, 836.

CuK α $\lambda = 1.540598 \text{ \AA}$; temp. $25 \pm 1^\circ\text{C}$			
Internal standard W, $a = 3.16524 \text{ \AA}$			
d (Å)	I	hkl	$2\theta (\circ)$
6.449	6	020	13.72
5.580	100	210	15.87
5.145	75	111	17.22
4.235	85	121	20.96
3.646	15	221	24.39
3.532	20	230	25.19
3.415	4	131	26.07
3.336	30	311	26.70
3.228	30	040	27.61
3.154	2	002	28.27
3.095	40	400	28.82
3.042	30	321	29.34
2.971	8	112	30.05
2.832	5	022	31.57
2.788	35	420	32.08
2.744	30	212	32.61
2.715	4	411	32.97
2.551	3	421	35.15
2.504	9	302	35.83
2.457	10	312	36.54
2.380	3	250	37.77
2.344	12	151	38.37
2.302	3	501	39.09
2.267	4	511	39.73
2.208	20	402	40.84
2.169	16	521	41.61
2.149	25	060	42.00
2.088	9	422	43.29
2.071	8	103	43.67
2.067	10	351	43.75
2.036	4	610	44.45
2.008	6	161	45.12
1.990	4	203	45.54
1.946	4	502	46.64

Zinc titanium oxide, Zn_2TiO_4

Sample

The sample was prepared at NBS by heating a 2:1 mixture of ZnO and TiO_2 (anatase) at $1300\text{ }^{\circ}\text{C}$ for 45 minutes, followed by heating at $1450\text{ }^{\circ}\text{C}$ for 10 minutes.

Color

Colorless

Structure

Cubic, $Fd\bar{3}m$ (227), $Z = 8$. Verwey and Heilmann [1947] found Zn_2TiO_4 to be an inverse spinel structure. Billiet and Poix [1963] found that at high temperatures there was some randomness of the cation occupation. The structure was also studied by Bartram and Stepety [1961] who also noted some departure from perfect inverse spinel structure.

NBS lattice constant of this sample:

$$a = 8.4602(5)\text{ \AA}$$

Density

(calculated) 5.323 g/cm^3

Reference intensity

$$\frac{I}{I_{corundum}} = 4.5$$

Polymorphism

Besides the order-disorder of the spinel type, Billiet and Poix [1963] reported a tetragonal, distorted spinel form below about $500\text{ }^{\circ}\text{C}$.

Additional patterns

1. Bartram and Stepety [1961].
2. Dulin and Rase [1960].

References

- Bartram, S. F. and Stepety, R. A. (1961). J. Am. Cer. Soc. 44, 493.
 Billiet, Y. and Poix, P. (1963). Bull. Soc. Chem. France 1963, 477.
 Dulin, F. H. and Rase, D. E. (1960). J. Am. Cer. Soc. 43, 125.
 Verwey, E. J. W. and Heilmann, E. L. (1947). J. Chem. Phys. 15, 174.

$\text{CuK}\alpha_1 \lambda = 1.540598\text{ \AA}; \text{ temp. } 25 \pm 1\text{ }^{\circ}\text{C}$ $\text{Internal standard Ag, } a = 4.08651\text{ \AA}$			
$d(\text{\AA})$	I	hkl	$2\theta (\text{ }^{\circ})$
4.89	4	111	18.11
2.993	35	220	29.83
2.552	100	311	35.13
2.444	4	222	36.74
2.115	13	400	42.72
1.727	11	422	52.98
1.627	30	511	56.50
1.4958	30	440	61.99
1.4305	<1	531	65.16
1.3377	3	620	70.32
1.2901	6	533	73.32
1.2758	2	622	74.28
1.2214	1	444	78.20
1.1306	4	642	85.89
1.1013	9	731	88.77
1.0576	2	800	93.50
0.9971	2	822	101.17
.9769	5	751	104.10
.9706	1	662	105.06
.9457	1	840	109.07
.9019	1	664	117.32
.8868	4	931	120.61
.8634	7	844	126.30

Barium calcium nitrate, $\text{Ba}(\text{NO}_3)_2\text{-Ca}(\text{NO}_3)_2$, calculated solid solution series

Structure

Cubic, $P2_13$ (198), $Z = 4$. The structure of $\text{Ca}(\text{NO}_3)_2$ was determined by Vegard and Bilberg [1931], and the space group was given as $\text{Pa}3$. However, later work by Birnstock [1967] on the isomorph $\text{Ba}(\text{NO}_3)_2$ indicated that the space group is $P2_13$. In the present calculated patterns, the atomic positions given by Vegard and Bilberg have been modified for the change in space group. The system $\text{Ba}(\text{NO}_3)_2\text{-Ca}(\text{NO}_3)_2$ forms a complete solid solution series [Protsenko and Belova, 1957].

Lattice constants

The constants were derived by interpolation on a molar ratio using the following: for $\text{Ba}(\text{NO}_3)_2$ $a = 8.1148\text{\AA}$ [Swanson et al., 1973]; for $\text{Ca}(\text{NO}_3)_2$, $a = 7.6005\text{\AA}$ [Swanson et al., 1957, modified to conform to new wavelength measurements].

Thermal parameters

Isotropic: barium $B = 0.93$; calcium $B = 1.0$; nitrogen $B = 1.2$; oxygen $B = 1.2$.

Scattering factors

Ca^{2+} , N^0 , O^- [International Tables, 1962].

Ba^{2+} [Cromer and Waber, 1965].

The factors used were proportional to the molar ratio, assuming random distribution of the cations.

References

- Birnstock, R. (1967). *Z. Krist.* 124, 310.
 Cromer, D. T. and Waber, J. T. (1965). *Acta Cryst.* 18, 104.
 International Tables for X-ray Crystallography III (1962), 202, 210.
 Protsenko, P. I. and Belova, Z. I. (1957). *Zhur. Neorg. Khim.* 2, 2619.
 Swanson, H. E., Gilfrich, N. T., and Cook, M. I. (1957). *Nat'l. Bur. Std. U.S. Circ.* 539, VII, 14.
 Swanson, H. E., McMurdie, H. F., Morris, M. C., Evans, E. H., and Paretzkin, B. (1973). *Nat'l. Bur. Std. U.S. Monograph* 25, 11, 14.
 Vegard, L. and Bilberg, L. (1931). *Avhandl. Norske Videnskaps Mat.-Nat. Kl.* 1931 No. 12.

	$\text{Ba}_{.75}\text{Ca}_{.25}(\text{NO}_3)_2$			$\text{Ba}_{.5}\text{Ca}_{.5}(\text{NO}_3)_2$			$\text{Ba}_{.25}\text{Ca}_{.75}(\text{NO}_3)_2$		
hkl	$d(\text{\AA})$	I	$2\theta (\text{^\circ})$	$d(\text{\AA})$	I	$2\theta (\text{^\circ})$	$d(\text{\AA})$	I	$2\theta (\text{^\circ})$
	$\lambda=1.540598$			$\lambda=1.540598$			$\lambda=1.540598$		
111	4.610	100	19.24	4.535	100	19.56	4.463	100	19.88
200	3.994	25	22.24	3.928	15	22.62	3.864	5	23.00
210	3.573	17	24.90	3.515	28	25.32	3.456	42	25.76
211	3.262	13	27.32	3.209	20	27.78	3.155	31	28.26
220	2.824	26	31.66	2.779	22	32.18	2.733	17	32.74
221	2.664	<1	33.62	2.620	2	34.20	2.576	5	34.80
311	2.409	75	37.30	2.370	75	37.94	2.331	71	38.60
222	2.306	44	39.02	2.268	53	39.70	2.232	64	40.38
321 +	2.135	<1	42.30	2.101	1	43.02	2.066	2	43.78
400	1.997	13	45.38	1.965	16	46.16	1.933	19	46.98
410	1.937	<1	46.86	1.906	<1	47.68	1.875	<1	48.52
411	1.883	2	48.30	1.853	3	49.14	1.822	5	50.02
331	1.833	15	49.70	1.803	14	50.58	1.773	11	51.50
024 +	1.787	14	51.08	1.757	13	52.00	1.728	11	52.94
124	1.744	1	52.44	1.715	1	53.38	1.687	1	54.34
332	1.703	<1	53.78	1.676	<1	54.74	1.648	1	55.74
422	1.631	10	56.38	1.604	8	57.40	1.5780	6	58.44
430	1.598	<1	57.64	1.5721	<1	58.68	1.5462	1	59.76
134 +	1.567	<1	58.90	1.5415	<1	59.96	1.5159	1	61.08
511 +	1.537	11	60.14	1.5123	11	61.24	1.4878	10	62.36
432	1.4836	1	62.56	1.4593	1	63.72	1.4352	2	64.92
125	1.4585	<1	63.76	1.4348	<1	64.94	1.4113	<1	66.16
440	1.4124	6	66.10	1.3894	7	67.34	1.3666	8	68.62
522 +	1.3909	--	67.26	1.3680	--	68.54	1.3457	<1	69.84
433	1.3701	<1	68.42	1.3480	<1	69.70	1.3255	1	71.06

Barium calcium nitrate, $\text{Ba}(\text{NO}_3)_2\text{-Ca}(\text{NO}_3)_2$, calculated solid solution series - Continued

	$\text{Ba}_{.75}\text{Ca}_{.25}(\text{NO}_3)_2$			$\text{Ba}_{.5}\text{Ca}_{.5}(\text{NO}_3)_2$			$\text{Ba}_{.25}\text{Ca}_{.75}(\text{NO}_3)_2$		
hkl	$d(\text{\AA})$	I	$2\theta (\text{\\circ})$	$d(\text{\AA})$	I	$2\theta (\text{\\circ})$	$d(\text{\AA})$	I	$2\theta (\text{\\circ})$
	$\lambda=1.540598$			$\lambda=1.540598$			$\lambda=1.540598$		
531 +	1.3504	13	69.56	1.3284	12	70.88	1.3067	11	72.24
442 +	1.3314	6	70.70	1.3099	5	72.04	1.2883	4	73.44
610	1.3134	<1	71.82	1.2920	<1	73.20	1.2709	<1	74.62
235 +	1.2959	<1	72.94	1.2749	<1	74.34	1.2540	1	75.80
620 +	1.2631	3	75.16	1.2426	3	76.62	1.2222	2	78.14
126 +	1.2476	--	76.26	1.2275	<1	77.74	1.2072	<1	79.30
145 +	1.2328	--	77.34	1.2128	--	78.86	1.1927	<1	80.46
533	1.2182	4	78.44	1.1986	4	79.98	1.1789	3	81.60
622	1.2044	4	79.52	1.1849	5	81.10	1.1653	5	82.76
542	1.1910	<1	80.60	1.1715	<1	82.22	1.1523	<1	83.90
136 +	1.1779	<1	81.68	1.1589	<1	83.32	1.1398	<1	85.04
444	1.1532	1	83.82	1.1344	1	85.54	1.1158	1	87.32
543	1.1297	--	85.98	1.1115	<1	87.74	1.0932	<1	89.60
711 +	1.1186	4	87.04	1.1006	4	88.84	1.0824	3	90.74
640 +	1.1079	2	88.10	1.0899	2	89.94	1.0719	1	91.88
146	1.0974	<1	89.16	1.0796	<1	91.04	1.0618	<1	93.02
633	1.0871	--	90.24	1.0696	--	92.14	1.0519	<1	94.16
246 +	1.0676	4	92.36	1.0502	4	94.36	1.0330	3	96.44
544	1.0583	--	93.42	1.0410	--	95.46	1.0239	<1	97.58
137 +	1.0401	6	95.56	1.0231	5	97.68	1.0063	5	99.90
650	1.0228	<1	97.72	1.0063	<1	99.90	0.9898	<1	102.20
156 +	1.0145	<1	98.80	0.9981	<1	101.02	.9817	<1	103.38
800	0.9986	<1	100.96	.9824	<1	103.28	.9663	<1	105.72
652 +	.9909	<1	102.04	.9749	<1	104.40	.9587	1	106.92
147	.9833	--	103.14	.9675	--	105.54	.9515	<1	108.10
733	.9761	1	104.22	.9601	1	106.70	.9444	1	109.30
644 +	.9687	3	105.34	.9531	3	107.84	.9374	3	110.52
247 +	.9617	<1	106.44	.9462	<1	109.00	.9306	<1	111.74
822 +	.9415	2	109.80	.9262	2	112.54	.9110	2	115.46
831 +	.9287	<1	112.08	.9136	<1	114.94	.8986	<1	118.02
751 +	.9225	3	113.24	.9075	3	116.16	.8925	3	119.32
662	.9164	1	114.40	.9015	1	117.40	.8867	1	120.62
832 +	.9104	<1	115.58	.8957	<1	118.64	.8809	<1	121.96
048 +	.8932	1	119.18	.8787	1	122.48	.8642	1	126.08
744 +	.8877	--	120.40	.8732	--	123.80	.8589	<1	127.50
753 +	.8769	4	122.90	.8627	4	126.48	.8485	4	130.42
842 +	.8717	2	124.18	.8575	2	127.86	.8434	2	131.94
761 +	.8615	--	126.80	.8475	--	130.70	.8335	<1	135.08
664	.8516	1	129.52	.8378	1	133.68	.8240	1	138.40
922 +	.8469	--	130.90	.8331	--	135.22	.8194	<1	140.14
158	.8421	--	132.34	.8285	--	136.80	.8148	<1	141.94
931 +	.8374	2	133.80	.8239	2	138.44	.8103	2	143.84
844	.8154	1	141.72	.8021	1	147.60	.7889	1	155.04
933 +	.8029	4	147.22	.7899	4	154.42			
068 +	.7989	2	149.24	.7859	1	157.10			
249 +	.7949	<1	151.40						
862 +	.7834	4	159.04						
Lattice constant	7.9889 \AA			7.8594 \AA			7.7300 \AA		
Density (calc.)	3.088 g/cm ³			2.910 g/cm ³			2.709 g/cm ³		

Barium lead nitrate, $\text{Ba}(\text{NO}_3)_2\text{-Pb}(\text{NO}_3)_2$, calculated solid solution series

Structure

Cubic, $P2_13$ (198), $Z=4$. The structure of $\text{Pb}(\text{NO}_3)_2$ was determined by Hamilton [1957] and the space group given as $\text{Pa}3$. However, later work on the isomorph $\text{Ba}(\text{NO}_3)_2$ [Birnstock, 1967] indicated that the space group is $P2_13$. In the present calculated patterns the atom positions given by Hamilton were modified for the change in space group. The system $\text{Ba}(\text{NO}_3)_2\text{-Pb}(\text{NO}_3)_2$ forms a complete solid solution series [Laybourn, et al., 1934].

Lattice constants

The constants were derived by interpolation on a molar ratio using the following: for $\text{Ba}(\text{NO}_3)_2$, $a = 8.1148\text{\AA}$ [Swanson et al., 1974]; for $\text{Pb}(\text{NO}_3)_2$, $a = 7.8573$ [Swanson et al., 1955, modified to conform to new wavelength measurements].

Thermal parameters

Isotropic: barium $B = .93$, lead $B = 1.0$, nitrogen $B = 1.21$, oxygen $B = 1.16$.

Scattering factors

N^0 , O^- [International Tables, 1962].
 Ba^{2+} , Pb^{2+} [Cromer and Waber, 1965].

The factors used were proportional to the molar ratio, assuming random distribution of the cations.

References

- Birnstock, R. (1967). *Z. Krist.* 124, 310.
- Cromer, D. T. and Waber, J. T. (1965). *Acta Cryst.* 18, 104.
- Hamilton, W. C. (1957). *Acta Cryst.* 10, 103.
- International Tables for X-ray Crystallography III (1962), 202.
- Laybourn, K., Madgin, M. W., and Freeman, D. (1934). *J. Chem. Soc.* 1934, 139.
- Swanson, H. E., Gilfrich, N. T., and Ugrinic, G. (1955). *Nat'l. Bur. Std. U.S. Circ.* 539, V, 36.
- Swanson, H. E., McMurdie, H. F., Morris, M. C., Evans, E. H., and Paretzkin, B. (1974). *Nat'l Bur. Std. U.S. Mono.* 25, 11, 14.

$\text{Ba}_{.67}\text{Pb}_{.33}(\text{NO}_3)_2$				$\text{Ba}_{.33}\text{Pb}_{.67}(\text{NO}_3)_2$			
hkl	$d(\text{\AA})$	I	$2\theta (\text{^\circ})$	$d(\text{\AA})$	I	$2\theta (\text{^\circ})$	
		$\lambda=1.540598$			$\lambda=1.540598$		
111	4.638	100	19.12	4.586	100	19.34	
200	4.015	35	22.12	3.973	35	22.36	
210 +	3.593	9	24.76	3.553	6	25.04	
211	3.278	6	27.18	3.243	4	27.48	
220	2.840	30	31.48	2.808	30	31.84	
311	2.421	67	37.10	2.395	64	37.52	
222	2.319	33	38.80	2.293	30	39.26	
123	2.146	<1	42.06	2.123	<1	42.54	
400	2.008	11	45.12	1.986	10	45.64	
410 +	1.948	<1	46.58	1.926	<1	47.14	
411	1.893	1	48.02	1.873	<1	48.58	
331	1.843	17	49.42	1.823	16	50.00	
024 +	1.796	15	50.80	1.776	15	51.40	
124	1.753	<1	52.14	1.734	<1	52.76	
332	1.713	<1	53.46	1.694	<1	54.10	
422	1.640	11	56.04	1.622	11	56.72	
431	1.575	<1	58.56	1.558	<1	59.26	
511 +	1.546	11	59.78	1.529	11	60.52	
432	1.4917	<1	62.18	1.4751	<1	62.96	
440	1.4201	5	65.70	1.4042	5	66.54	

Barium lead nitrate, $\text{Ba}(\text{NO}_3)_2\text{-Pb}(\text{NO}_3)_2$, calculated solid solution series - continued

Ba _{0.67} Pb _{0.33} (NO ₃) ₂				Ba _{0.33} Pb _{0.67} (NO ₃) ₂		
hkl	d (Å)	I	2θ (°) $\lambda=1.540598$	d (Å)	I	2θ (°) $\lambda=1.540598$
433	1.3775	<1	68.00	1.3624	<1	68.86
531 +	1.3576	13	69.14	1.3426	12	70.02
442 +	1.3386	6	70.26	1.3239	6	71.16
610	1.3204	<1	71.38	1.3058	--	72.30
611	1.3030	<1	72.48	1.2886	--	73.42
620 +	1.2700	3	74.68	1.2559	3	75.66
533	1.2248	4	77.94	1.2113	4	78.98
622	1.2110	4	79.00	1.1976	4	80.06
444	1.1593	1	83.28	1.1465	1	84.42
711 +	1.1246	4	86.46	1.1123	4	87.66
640 +	1.1139	2	87.50	1.1015	2	88.74
146	1.1033	<1	88.56	1.0911	<1	89.82
246 +	1.0734	4	91.72	1.0614	4	93.06
553 +	1.0456	6	94.90	1.0341	5	96.30
800	1.0041	<1	100.20	0.9929	<1	101.76
733	0.9813	1	103.44	.9704	1	105.08
644 +	.9741	3	104.52	.9633	3	106.20
822 +	.9467	2	108.92	.9361	2	110.74
831	.9337	<1	111.18	.9234	--	113.06
751 +	.9275	3	112.30	.9172	3	114.24
662	.9213	1	113.46	.9112	1	115.42
840 +	.8980	1	118.14	.8881	1	120.30
753 +	.8817	4	121.78	.8719	4	124.12
842 +	.8764	2	123.04	.8667	2	125.44
664	.8562	1	128.22	.8468	1	130.92
931 +	.8420	2	132.36	.8327	2	135.36
844	.8198	1	139.98	.8107	1	143.66
933 +	.8073	4	145.18	.7983	4	149.54
068 +	.8032	2	147.08	.7944	2	151.72
862 +	.7876	4	155.92			
Lattice constant	8.0322 $^{\circ}$ Å			7.9435 $^{\circ}$ Å		
Density (calc.)	3.645 g/cm ³			4.083 g/cm ³		

Barium strontium nitrate, $\text{Ba}(\text{NO}_3)_2\text{-Sr}(\text{NO}_3)_2$, calculated solid solution series

Structure

Cubic, $P2_13$ (198), $Z = 4$. The structures of both $\text{Ba}(\text{NO}_3)_2$ and $\text{Sr}(\text{NO}_3)_2$ were originally determined by Vegard and Bilberg [1931]; they found the compounds isostructural and assigned the space group $\text{Pa}3(205)$. Later work on $\text{Ba}(\text{NO}_3)_2$ by Birnstock [1967] indicated instead that the space group is $P2_13(198)$ which is used here. The system $\text{Ba}(\text{NO}_3)_2\text{-Sr}(\text{NO}_3)_2$ forms a complete solid solution series [Ringdal, 1932].

Lattice constants

The constants were derived by interpolation on a molar ratio using the following; for $\text{Ba}(\text{NO}_3)_2$, $a = 8.1184\text{\AA}$ [Swanson et al., 1974] and for $\text{Sr}(\text{NO}_3)_2$, $a = 7.7813\text{\AA}$ [McMurdie et al., 1974].

Thermal parameters

Isotropic: barium $B = 0.93$; strontium $B = 1.0$; nitrogen $B = 1.21$; oxygen $B = 1.16$.

Scattering factors

N^0 , O^- [International Tables, 1962].

Ba^{2+} , Sr^{2+} [Cromer and Waber, 1965].

The factors used were proportional to the molar ratio, assuming random distribution of the cations.

References

- Birnstock (1967). Z. Krist. 124, 310.
 Cromer, D. T. and Waber, J. T. (1965). Acta Cryst. 18, 104.
 International Tables for X-ray Crystallography III (1962), 202.
 McMurdie, et al: (1974). This publication, pg. 31.
 Ringdal, H. Th. (1932). Z. Krist. 82, 50.
 Swanson, H. E., McMurdie, H. F., Morris, M. C., Evans, E. H. and Paretzkin, B. (1974). Nat'l. Bur. Std. U. S. Mono. 25, 11, 14.
 Vegard, L. and Bilberg, L. (1931). Avhandl. Norske Videnskaps Mat.-Nat. Kl. 1931, No. 12.

	$\text{Ba}_{.75}\text{Sr}_{.25}(\text{NO}_3)_2$			$\text{Ba}_{.5}\text{Sr}_{.5}(\text{NO}_3)_2$			$\text{Ba}_{.25}\text{Sr}_{.75}(\text{NO}_3)_2$		
hkl	$d(\text{\AA})$	I	$2\theta (\text{\\circ})$	$d(\text{\AA})$	I	$2\theta (\text{\\circ})$	$d(\text{\AA})$	I	$2\theta (\text{\\circ})$
	$\lambda=1.540598$			$\lambda=1.540598$			$\lambda=1.540598$		
111	4.638	100	19.12	4.590	100	19.32	4.539	100	19.54
200	4.015	26	22.12	3.973	21	22.36	3.931	17	22.60
210	3.593	16	24.76	3.556	18	25.02	3.517	22	25.30
211	3.281	10	27.16	3.246	12	27.46	3.211	14	27.76
220	2.840	26	31.48	2.810	26	31.82	2.781	25	32.16
221	2.678	<1	33.44	2.650	1	33.80	2.621	2	34.18
311	2.423	69	37.08	2.396	67	37.50	2.372	65	37.90
222	2.319	39	38.80	2.295	42	39.22	2.271	46	39.66
321 +	2.148	<1	42.04	2.124	1	42.52	2.102	1	43.00
400	2.009	12	45.10	1.988	13	45.60	1.967	14	46.12
410 +	1.948	<1	46.58	1.928	<1	47.10	1.907	<1	47.64
411	1.894	1	48.00	1.874	2	48.54	1.854	2	49.10
331	1.843	15	49.40	1.824	14	49.96	1.804	14	50.54
024 +	1.796	14	50.78	1.778	14	51.36	1.759	13	51.94
124	1.753	1	52.12	1.735	1	52.72	1.716	1	53.34
332	1.713	<1	53.46	1.695	<1	54.06	1.677	<1	54.70
422	1.640	10	56.04	1.623	9	56.68	1.606	8	57.34
430	1.607	<1	57.30	1.590	<1	57.96	1.573	<1	58.64
134 +	1.576	<1	58.54	1.559	<1	59.22	1.542	<1	59.92
511 +	1.546	11	59.76	1.530	11	60.46	1.514	11	61.18
432	1.4917	1	62.18	1.4764	1	62.90	1.4606	1	63.66
125	1.4667	<1	63.36	1.4516	<1	64.10	1.4360	<1	64.80
440	1.4201	6	65.70	1.4053	6	66.48	1.3905	6	67.28
433	1.3779	<1	67.98	1.3634	<1	68.80	1.3490	<1	69.64
531 +	1.3579	12	69.12	1.3436	12	69.96	1.3294	12	70.82

Barium strontium nitrate, $\text{Ba}(\text{NO}_3)_2 \cdot \text{Sr}(\text{NO}_3)_2$ - continued

	Ba _{0.75} Sr _{0.25} (NO ₃) ₂			Ba _{0.5} Sr _{0.5} (NO ₃) ₂			Ba _{0.25} Sr _{0.75} (NO ₃) ₂		
hkl	d (Å)	I	2θ (°) λ=1.540598	d (Å)	I	2θ (°) λ=1.540598	d (Å)	I	2θ (°) λ=1.540598
442 +	1.3390	6	70.24	1.3249	5	71.10	1.3108	5	71.98
610	1.3207	<1	71.36	1.3071	<1	72.22	1.2932	<1	73.12
611 +	1.3033	<1	72.46	1.2895	<1	73.36	1.2758	<1	74.28
620 +	1.2703	3	74.66	1.2571	3	75.58	1.2437	3	76.54
621	1.2548	<1	75.74	1.2415	<1	76.70	1.2285	<1	77.66
533	1.2251	4	77.92	1.2123	4	78.90	1.1994	3	79.92
622	1.2113	4	78.98	1.1984	4	80.00	1.1858	4	81.02
542	1.1976	<1	80.06	1.1851	<1	81.08	1.1725	<1	82.14
136 +	1.1846	<1	81.12	1.1720	<1	82.18	1.1598	<1	83.24
444	1.1595	1	83.26	1.1474	1	84.34	1.1362	1	85.46
543	1.1361	--	85.38	1.1242	--	86.50	1.1123	<1	87.66
711 +	1.1251	4	86.42	1.1131	4	87.58	1.1013	4	88.76
640 +	1.1141	2	87.48	1.1025	2	88.64	1.0907	2	89.86
146	1.1035	<1	88.54	1.0920	<1	89.72	1.0804	<1	90.96
246 +	1.0736	4	91.70	1.0623	4	92.96	1.0510	4	94.26
137 +	1.0460	5	94.86	1.0349	5	96.20	1.0241	5	97.56
650	1.0287	--	96.98	1.0179	<1	98.36	1.0070	<1	99.80
651 +	1.0203	<1	98.04	1.0096	<1	99.46	0.9990	<1	100.90
800	1.0042	<1	100.18	0.9937	<1	101.64	.9832	<1	103.16
652 +	0.9966	<1	101.24	.9861	<1	102.74	.9751	<1	104.28
733	.9816	1	103.40	.9712	1	104.96	.9610	1	106.56
644 +	.9742	3	104.50	.9640	3	106.08	.9538	1	107.72
128 +	.9672	<1	105.58	.9570	<1	107.20	.9469	<1	108.88
822 +	.9468	2	108.90	.9369	2	110.60	.9270	2	112.40
831 +	.9339	<1	111.14	.9242	<1	112.92	.9144	<1	114.80
751 +	.9277	3	112.26	.9180	3	114.10	.9082	3	116.02
662	.9216	1	113.40	.9119	1	115.28	.9023	1	117.24
832 +	.9156	--	114.56	.9060	<1	116.48	.8964	<1	118.48
048 +	.8983	1	118.08	.8888	1	120.14	.8794	1	122.32
753 +	.8818	4	121.74	.8726	4	123.96	.8634	4	126.30
842 +	.8766	2	122.98	.8674	2	125.26	.8582	2	127.68
664	.8565	1	128.16	.8475	1	130.72	.8384	1	133.48
931 +	.8422	2	132.30	.8333	2	135.14	.8246	2	138.20
844	.8200	1	139.90	.8114	1	143.38	.8028	1	147.30
933 +	.8075	4	145.10	.7990	4	149.20	.7905	4	154.02
068 +	.8034	1	146.98	.7950	1	151.38	.7866	1	156.66
10·1·0 +	.7994	<1	148.98	.7910	<1	153.70	.7827	<1	159.60
862 +	.7878	4	155.80						
Lattice constant	8.0341 ^o Å			7.9498 ^o Å			7.8656 ^o Å		
Density (calc.)	3.188 g/cm ³			3.126 g/cm ³			3.058 g/cm ³		

Calcium lead nitrate, $\text{Ca}(\text{NO}_3)_2\text{-Pb}(\text{NO}_3)_2$, calculated solid solution series

Structure

Cubic, $P2_13$ (198), $Z = 4$. The structures of $\text{Ca}(\text{NO}_3)_2$ and $\text{Pb}(\text{NO}_3)_2$ were determined respectively by Vergard and Bilberg [1931] and Hamilton [1957]. The space group was given as $\text{Pa}3$. However, later work by Birnstock [1967] on the isomorph $\text{Ba}(\text{NO}_3)_2$ indicated that the space group is $P2_13$. In the present calculated patterns, the atomic positions have been modified for the change in space group. The system $\text{Ca}(\text{NO}_3)_2\text{-Pb}(\text{NO}_3)_2$ forms a complete solid solution series [Laybourn et al., 1934].

Lattice constants

The constants were derived by interpolation on a molar ratio using the following: for $\text{Ca}(\text{NO}_3)_2$, $a = 7.6005\text{\AA}$ [Swanson et al., 1957]; for $\text{Pb}(\text{NO}_3)_2$, $a = 7.8573$ [Swanson et al., 1955]. Both constants were modified to conform to new wavelength measurements.

Thermal parameters

Isotropic: calcium $B = 1.0$; lead $B = 1.0$; nitrogen $B = 1.2$; oxygen $B = 1.2$.

Scattering factors

Ca^{2+} , N^0 , O^- [International Tables, 1962].

Pb^{2+} [Cromer and Waber, 1965].

The factors used were proportional to the molar ratio, assuming random distribution of the cations.

References

- Birnstock, R. (1967). Z. Krist. 124, 310.
 Cromer, D. T. and Waber, J. T. (1965). Acta Cryst. 18, 104.
 Hamilton, W. C. (1957). Acta Cryst. 10, 103.
 International Tables for X-ray Crystallography III (1962), 202, 210.
 Laybourn, K., Madgin, W. M. and Freeman, D. (1934). J. Chem. Soc. 1934, 144.
 Swanson, H. E., Gilfrich, N. T. and Ugrinic, G. (1955). Nat'l. Bur. Std. U.S. Circ. 539, V, 36.
 Swanson, H. E., Gilfrich, N. T. and Cook, M. I. (1957). Nat'l. Bur. Std. U.S. Circ. 529, VII, 14.
 Vegard, L. and Bilberg, L. (1931). Avhandl. Norske Videnskaps Mat.-Nat. Kl. 1931, No. 12.

	Ca _{0.67} Pb _{0.33} (NO ₃) ₂			Ca _{0.33} Pb _{0.67} (NO ₃) ₂		
hkl	d (Å)	I $\lambda=1.540598$	2θ (°)	d (Å)	I $\lambda=1.540598$	2θ (°)
111	4.436	100	20.00	4.485	100	19.78
200	3.841	15	23.14	3.887	31	22.86
210	3.437	19	25.90	3.477	8	25.60
211	3.138	14	28.42	3.173	6	28.10
220	2.717	23	32.94	2.748	30	32.56
221	2.561	2	35.00	2.590	<1	34.60
311	2.317	63	38.84	2.344	66	38.38
222	2.218	46	40.64	2.244	35	40.16
321 +	2.054	1	44.06	2.077	<1	43.54
400	1.921	14	47.28	1.944	11	46.70
410	1.864	<1	48.82	1.885	<1	48.24
411	1.811	2	50.34	1.832	1	49.72
331	1.763	14	51.82	1.783	16	51.18
024 +	1.718	13	53.26	1.738	15	52.62
124	1.677	<1	54.68	1.696	<1	54.02
332	1.639	<1	56.08	1.657	<1	55.40
422	1.569	8	58.82	1.586	10	58.10
430	1.537	<1	60.16	1.555	--	59.40
134 +	1.507	<1	61.48	1.524	<1	60.70
511 +	1.4789	11	62.78	1.4956	11	62.00

Calcium lead nitrate, $\text{Ca}(\text{NO}_3)_2\text{-Pb}(\text{NO}_3)_2$, calculated solid solution series - continued

	$\text{Ca}_{.67}\text{Pb}_{.33}(\text{NO}_3)_2$			$\text{Ca}_{.33}\text{Pb}_{.67}(\text{NO}_3)_2$		
hkl	d (Å)	I	$2\theta (\circ)$	d (Å)	I	$2\theta (\circ)$
	$\lambda=1.540598$			$\lambda=1.540598$		
432	1.4270	1	65.34	1.4432	<1	64.52
125	1.4030	<1	66.60	1.4189	--	65.76
440	1.3586	6	69.08	1.3740	6	68.20
433	1.3181	<1	71.52	1.3330	<1	70.60
531 +	1.2990	11	72.74	1.3137	12	71.80
442 +	1.2808	5	73.94	1.2953	5	72.98
610	1.2633	<1	75.14	1.2779	--	74.14
235 +	1.2467	<1	76.32	1.2608	<1	75.32
620 +	1.2151	2	78.68	1.2291	3	77.62
621	1.2001	<1	79.86	1.2138	--	78.78
533	1.1720	3	82.18	1.1854	4	81.06
622	1.1586	4	83.34	1.1718	4	82.20
542	1.1457	<1	84.50	1.1586	<1	83.34
136 +	1.1331	<1	85.66	1.1461	--	84.46
444	1.1093	1	87.96	1.1219	1	86.72
543	1.0869	<1	90.26	1.0992	--	88.98
711 +	1.0761	4	91.42	1.0884	4	90.10
640 +	1.0658	2	92.56	1.0780	2	91.22
146	1.0557	<1	93.72	1.0676	<1	92.36
246 +	1.0269	3	97.20	1.0387	4	95.74
137 +	1.0006	5	100.68	1.0120	6	99.14
650	0.9840	<1	103.04	0.9951	--	101.44
156	.9761	<1	104.22	.9872	--	102.58
800	.9606	<1	106.62	.9716	<1	104.90
652 +	.9532	<1	107.82	.9640	--	106.08
733	.9389	1	110.26	.9496	1	108.42
644 +	.9320	3	111.48	.9426	3	109.62
247 +	.9252	<1	112.72	.9357	--	110.82
822 +	.9057	2	116.54	.9160	2	114.48
831 +	.8934	<1	119.14	.9035	<1	116.98
751 +	.8874	3	120.46	.8975	3	118.24
662	.8816	1	121.80	.8915	1	119.54
832 +	.8758	<1	123.18	.8857	--	120.84
048	.8592	1	127.40	.8690	1	124.86
753 +	.8436	4	131.88	.8532	4	129.08
842 +	.8385	2	133.46	.8481	2	130.54
664	.8193	1	140.18	.8285	1	136.78
931 +	.8056	2	145.94	.8148	3	141.96
844	.7844	1	158.26	.7933	1	152.34
Lattice constant	7.6852 Å			7.7726 Å		
Density (calc.)	3.208 g/cm ³			3.905 g/cm ³		

Calcium strontium nitrate, $\text{Ca}(\text{NO}_3)_2\text{-Sr}(\text{NO}_3)_2$, calculated solid solution series

Structure

Cubic, $P2_13$ (198), $Z = 4$. The structures of both $\text{Ca}(\text{NO}_3)_2$ and $\text{Sr}(\text{NO}_3)_2$ were determined by Vegard and Bilberg [1931], and the space group was given as $\text{Pa}3$. However, later work by Birnstock [1967] on the isomorph $\text{Ba}(\text{NO}_3)_2$ indicated that the space group is $P2_13$. The atomic positions given by Vegard and Bilberg have been modified here for the change in space group. The system $\text{Ca}(\text{NO}_3)_2\text{-Sr}(\text{NO}_3)_2$ forms a complete solid solution series [Protsenko and Belova, 1957].

Lattice constants

The constants were derived by interpolation on a molar ratio, using the following: for $\text{Sr}(\text{NO}_3)_2$, $a = 7.7813\text{\AA}$ [McMurdie et al, 1974] and for $\text{Ca}(\text{NO}_3)_2$, $a = 7.6005\text{\AA}$ [Swanson et al., 1957, modified to conform to new wavelength measurements].

Thermal parameters

Isotropic: calcium B = 1.0, strontium B = 1.0, nitrogen B = 1.2, oxygen B = 1.2.

Scattering factors

Ca^{2+} , N^0 , O^{-1} [International Tables, 1962].

Sr^{2+} [Cromer and Waber, 1965].

The factors used were proportional to the molar ratio, assuming random distribution of the cations.

References

- Birnstock, R. (1967). Z. Krist. 124, 310.
- Cromer, D. T. and Waber, J. T. (1965). Acta Cryst. 18, 104.
- International Tables for X-ray Crystallography III (1962), 202, 210.
- McMurdie, et al. (1974). This publication, pg. 31.
- Protsenko, P. I. and Belova, Z. I. (1957). Zhur. Neorg. Khim. 2, 2619.
- Swanson, H. E., Gilfrich, N. T., and Cook, M. I. (1957). Nat'l. Bur. Std. U.S. Circ. 539, VII, 14.
- Vegard, L. and Bilberg, L. (1931). Avhandl. Norske Videnskaps Mat.-Nat. Kl. 1931, No. 12.

hkl	$\text{Ca}_{.67}\text{Sr}_{.33}(\text{NO}_3)_2$			$\text{Ca}_{.33}\text{Sr}_{.67}(\text{NO}_3)_2$		
	d (Å)	I	2θ (°) $\lambda=1.540598$	d (Å)	I	2θ (°) $\lambda=1.540598$
111	4.423	100	20.06	4.458	100	19.90
200	3.831	2	23.20	3.860	7	23.02
210	3.424	49	26.00	3.453	35	25.78
211	3.127	38	28.52	3.153	22	28.28
220	2.709	14	33.04	2.730	20	32.78
221	2.553	10	35.12	2.574	5	34.82
311	2.310	68	38.96	2.328	66	38.64
222	2.211	74	40.78	2.229	58	40.44
321 +	2.047	2	44.20	2.063	2	43.84
400	1.915	22	47.44	1.930	18	47.04
410	1.858	--	49.00	1.873	<1	48.58
411	1.806	6	50.50	1.820	4	50.08
331	1.757	11	52.00	1.771	12	51.56
024 +	1.713	11	53.46	1.726	12	53.00
124	1.672	<1	54.88	1.685	<1	54.40
332	1.633	1	56.28	1.646	<1	55.80
422	1.564	5	59.02	1.576	6	58.52
430	1.532	1	60.38	1.544	1	59.84
134 +	1.502	1	61.70	1.514	1	61.16
511 +	1.4743	11	63.00	1.4861	11	62.44

Calcium strontium nitrate, $\text{Ca}(\text{NO}_3)_2\text{-Sr}(\text{NO}_3)_2$, calculated solid solution series - continued

	Ca _{.67} Sr _{.33} (NO ₃) ₂			Ca _{.33} Sr _{.67} (NO ₃) ₂		
hkl	d (Å)	I $\lambda=1.540598$	2θ (°)	d (Å)	I $\lambda=1.540598$	2θ (°)
432	1.4224	2	65.58	1.4340	1	64.98
125	1.3986	<1	66.84	1.4098	<1	66.24
440	1.3541	8	69.34	1.3648	7	68.72
522 +	1.3334	<1	70.58	1.3443	<1	69.92
433	1.3137	1	71.80	1.3242	1	71.14
531 +	1.2947	10	73.02	1.3052	11	72.34
442 +	1.2767	3	74.22	1.2868	4	73.54
610	1.2593	<1	75.42	1.2694	<1	74.72
235 +	1.2426	1	76.62	1.2526	1	75.90
620 +	1.2113	2	78.98	1.2209	2	78.24
126 +	1.1964	1	80.16	1.2059	<1	79.40
541 +	1.1820	<1	81.34	1.1914	<1	80.56
533	1.1683	2	82.50	1.1774	3	81.72
622	1.1548	5	83.68	1.1641	5	82.86
542 +	1.1419	<1	84.84	1.1510	<1	84.02
136 +	1.1295	1	86.00	1.1385	<1	85.16
444	1.1057	1	88.32	1.1145	1	87.44
543	1.0833	<1	90.64	1.0920	<1	89.72
711 +	1.0727	3	91.80	1.0813	3	90.86
640 +	1.0623	1	92.96	1.0708	1	92.00
146 +	1.0522	<1	94.12	1.0607	<1	93.14
633	1.0425	<1	95.28	1.0509	<1	94.28
246 +	1.0236	3	97.62	1.0319	3	96.58
544	1.0147	<1	98.78	1.0228	<1	97.72
137 +	0.9973	5	101.14	1.0053	5	100.04
650	.9807	<1	103.52	0.9887	<1	102.36
156 +	.9729	<1	104.70	0.9806	<1	103.54
800	.9575	<1	107.12	0.9652	<1	105.90
652 +	.9501	1	108.34	0.9578	1	107.08
147	.9429	<1	109.56	0.9505	<1	108.28
733	.9358	1	110.80	.9434	1	109.48
028 +	.9289	3	112.04	.9364	3	110.70
247 +	.9222	1	113.30	.9296	<1	111.92
822 +	.9028	2	117.14	.9100	2	115.66
830	.8966	<1	118.44	.9037	--	116.94
831 +	.8905	1	119.78	.8976	<1	118.22
751 +	.8845	3	121.12	.8916	3	119.52
662	.8787	1	122.48	.8857	1	120.84
832 +	.8730	1	123.86	.8800	<1	122.18
048 +	.8565	1	128.16	.8633	1	126.32
744 +	.8511	<1	129.66	.8580	<1	127.74
753 +	.8408	4	132.74	.8475	4	130.70
842 +	.8358	2	134.34	.8425	2	132.22
761 +	.8260	<1	137.66	.8326	<1	135.38
664	.8166	1	141.24	.8231	1	138.72
922 +	.8120	<1	143.12	.8185	<1	140.48
158	.8075	<1	145.10	.8139	<1	142.32
931 +	.8030	2	147.18	.8094	2	144.22
844				.7881	1	155.62
Lattice constant	7.6602 Å			7.7216 Å		
Density (calc.)	2.657 g/cm ³			2.827 g/cm ³		

Gallium magnesium, Ga_2Mg

Structure

Orthorhombic, Pbam (55), $Z=8$. The structure was determined by Smith, Mucker, Johnson and Wood [1969].

Lattice constants: [ibid.]

$$a = 6.802(13)\text{\AA}$$

$$b = 16.347(33)$$

(published value: $b = 16.346$)

$$c = 4.111(8)$$

Density

(calculated) 4.76 g/cm^3 [ibid.]

Thermal parameters

Isotropic [Smith et. al., 1969]

Scattering factors

Ga^0 , Mg^0 [International Tables, 1962], corrected for dispersion [Cromer, 1965].

Scale factor

(integrated intensities) 8.184×10^4

References

- Cromer, D. T. (1965). Acta Cryst. 18, 17.
 International Tables for X-ray Crystallography III (1962), 202.
 Smith, G. S., Mucker, K.F., Johnson, Q. and Wood, D. H. (1969). Acta Cryst. B25, 549.

$d(\text{\AA})$	I	hkl	$2\theta (\text{^\circ})$	$\lambda = 1.540598\text{\AA}$
2.50	26	2 2 1	35.96	
2.36	100	2 3 1	38.08	
2.27	30	0 6 1	39.66	
2.25	13	3 1 0	40.12	
2.21	9	1 7 0 +	40.82	
2.15	1	1 6 1	41.90	
2.13	9	2 6 0	42.48	
2.09	3	3 3 0	43.18	
2.06	49	0 0 2	44.02	
2.04	44	2 5 1 +	44.28	
1.983	32	3 4 0	45.72	
1.971	13	3 1 1	46.02	
1.946	36	1 7 1	46.64	
1.929	17	3 2 1	47.06	
1.889	10	2 6 1	48.14	
1.865	1	3 3 1	48.78	
1.836	1	0 4 2	49.60	
1.830	2	0 8 1	49.80	
1.786	2	3 4 1	51.10	
1.773	11	1 4 2	51.50	
1.759	2	2 0 2	51.94	
1.755	3	1 9 0	52.08	
1.750	2	2 1 2	52.24	
1.720	1	2 2 2	53.22	
1.700	2	4 0 0	53.88	
1.692	1	4 1 0	54.18	
1.686	2	1 5 2	54.38	
1.665	2	4 2 0	55.12	
1.635	1	0 10 0	56.22	
1.616	2	2 4 2	56.94	
1.614	2	1 9 1	57.00	
1.602	4	2 9 0	57.48	
1.595	2	1 6 2	57.74	
1.516	5	3 1 2	61.06	
1.509	3	4 5 0	61.40	
1.505	5	1 7 2	61.58	
1.478	4	2 6 2	62.82	
1.467	3	3 3 2 +	63.36	
1.449	11	0 8 2	64.22	
1.443	3	4 6 0	64.54	
1.427	16	3 4 2	65.34	
1.417	2	3 9 0	65.84	
1.370	1	0 0 3	68.40	
1.351	1	0 2 3	69.50	
1.340	6	3 9 1 +	70.18	
1.336	5	1 12 0 +	70.42	
1.320	2	5 3 0	71.40	
1.310	2	4 0 2	72.02	
1.307	4	4 8 0 +	72.22	
1.304	3	1 3 3	72.42	

Calculated Pattern (Peak heights)				
$d(\text{\AA})$	I	hkl	$2\theta (\text{^\circ})$	$\lambda = 1.540598\text{\AA}$
8.17	1	0 2 0	10.82	
6.28	6	1 1 0	14.10	
5.23	7	1 2 0	16.94	
4.25	1	1 3 0	20.88	
4.11	31	0 0 1	21.60	
3.67	25	0 2 1	24.22	
3.50	52	1 4 0	25.40	
3.44	39	1 1 1	25.88	
3.40	10	2 0 0	26.18	
3.33	5	2 1 0	26.76	
3.23	3	1 2 1	27.58	
3.14	4	2 2 0	28.40	
2.96	17	1 3 1	30.22	
2.95	16	1 5 0	30.30	
2.90	5	0 4 1	30.82	
2.73	1	0 6 0	32.84	
2.67	42	1 4 1	33.58	
2.62	17	2 0 1	34.20	
2.61	16	2 4 0	34.28	
2.53	6	1 6 0	35.46	

Gallium magnesium, Ga_2Mg - continued

d (Å)	I	hkl	2θ (°)	
$\lambda = 1.540598\text{\AA}$				
1.293	11	2 11 1 +	73.16	
1.287	6	5 1 1	73.50	
1.279	1	0 10 2	74.04	
1.276	6	5 2 1 +	74.28	
1.272	3	2 0 3	74.52	
1.264	3	2 9 2	75.12	
1.262	4	3 10 1	75.24	
1.256	4	5 3 1 +	75.64	
1.241	1	4 9 0	76.72	
1.238	7	2 3 3 +	76.98	
1.224	2	0 6 3	77.98	
1.216	2	4 5 2	78.60	
1.188	1	4 9 1	80.82	
1.185	3	2 5 3 +	81.12	
1.181	3	4 6 2	81.42	
1.176	1	5 7 0	81.88	
1.170	2	3 1 3	82.38	
1.167	3	3 12 0 +	82.60	
1.164	5	1 7 3	82.84	
1.161	3	3 2 3	83.12	
1.152	1	2 6 3	83.94	
1.134	2	2 13 1 +	85.60	
1.130	3	5 7 1	85.92	
1.124	2	5 2 2	86.56	
1.120	2	1 12 2	86.90	
1.111	1	5 3 2	87.82	
1.103	3	4 8 2	88.60	
1.083	1	6 2 1	90.66	
1.072	1	5 5 2	91.90	
1.063	1	4 9 2	92.92	
1.060	2	1 13 2	93.26	
1.053	1	5 9 1	94.08	
1.041	3	1 15 1	95.46	
1.037	2	6 5 1	96.00	
1.029	1	4 12 1	96.90	
1.028	2	0 0 4	97.10	
1.020	1	5 7 2	98.04	
1.015	2	3 12 2 +	98.70	
1.013	1	5 10 1	99.02	
.986	1	1 4 4	102.74	
.985	2	3 9 3	102.86	
.966	3	2 11 3	105.78	
.964	3	5 1 3	106.14	
.959	1	5 2 3	106.92	
.957	1	7 3 0	107.28	
.953	1	3 10 3	107.86	
.952	1	2 16 1	108.04	
.951	1	5 3 3	108.26	
.937	1	5 12 1	110.54	
.935	1	3 1 4	111.02	

Calculated Pattern (Integrated)				
d (Å)	I	hkl	2θ (°)	
$\lambda = 1.540598\text{\AA}$				
8.17	1	0 2 0	10.82	
6.28	5	1 1 0	14.09	
5.23	5	1 2 0	16.94	
4.25	1	1 3 0	20.87	
4.11	25	0 0 1	21.60	
4.09	5	0 4 0	21.73	
3.67	22	0 2 1	24.21	
3.50	47	1 4 0	25.41	
3.44	34	1 1 1	25.88	
3.40	8	2 0 0	26.18	
3.33	5	2 1 0	26.75	
3.23	3	1 2 1	27.58	
3.14	4	2 2 0	28.40	
2.96	15	1 3 1	30.21	
2.95	7	1 5 0	30.31	
2.90	5	0 4 1	30.83	
2.72	1	0 6 0	32.85	
2.67	40	1 4 1	33.58	
2.62	16	2 0 1	34.19	
2.61	6	2 4 0	34.27	
2.53	5	1 6 0	35.46	
2.50	25	2 2 1	35.96	
2.36	100	2 3 1	38.07	
2.27	30	0 6 1	39.65	
2.25	13	3 1 0	40.12	
2.21	8	1 7 0	40.82	
2.21	2	2 4 1	40.88	
2.15	1	1 6 1	41.90	
2.13	10	2 6 0	42.48	
2.09	3	3 3 0	43.18	
2.06	49	0 0 2	44.02	
2.04	26	2 5 1	44.26	
2.04	24	0 8 0	44.29	
1.983	34	3 4 0	45.73	
1.971	12	3 1 1	46.01	
1.946	39	1 7 1	46.64	
1.929	17	3 2 1	47.06	
1.889	10	2 6 1	48.14	
1.865	1	3 3 1	48.78	
1.836	1	0 4 2	49.60	
1.830	2	0 8 1	49.79	
1.786	2	3 4 1	51.11	
1.773	12	1 4 2	51.51	
1.759	2	2 0 2	51.94	
1.755	2	1 9 0	52.07	
1.749	1	2 1 2	52.26	
1.720	1	2 2 2	53.22	
1.700	3	4 0 0	53.87	
1.691	1	4 1 0	54.18	
1.686	2	1 5 2	54.38	

Gallium magnesium, Ga_2Mg - continued

$d(\text{\AA})$	I	hkl			$2\theta (\text{\\circ})$	$\lambda = 1.540598 \text{\AA}$
1.665	3	4	2	0	55.12	
1.635	1	0	10	0	56.23	
1.616	2	2	4	2	56.94	
1.614	1	1	9	1	57.02	
1.605	2	3	6	1	57.38	
1.602	4	2	9	0	57.47	
1.595	2	1	6	2	57.75	
1.516	6	3	1	2	61.06	
1.509	3	4	5	0	61.41	
1.505	4	1	7	2	61.58	
1.478	5	2	6	2	62.83	
1.467	2	4	4	1	63.36	
1.467	2	3	3	2	63.36	
1.449	14	0	8	2	64.22	
1.443	3	4	6	0	64.55	
1.427	20	3	4	2	65.34	
1.418	2	3	9	0	65.83	
1.370	1	0	0	3	68.41	
1.351	1	0	2	3	69.50	
1.342	2	5	2	0	70.06	
1.340	7	3	9	1	70.17	
1.339	2	1	1	3	70.25	
1.336	3	1	12	0	70.44	
1.335	1	1	9	2	70.50	
1.320	2	5	3	0	71.41	
1.310	2	4	0	2	72.02	
1.307	4	4	8	0	72.22	
1.306	1	4	1	2	72.28	
1.304	1	1	3	3	72.40	
1.294	2	4	2	2	73.08	
1.293	14	2	11	1	73.15	
1.288	6	5	1	1	73.49	
1.279	1	0	10	2	74.04	
1.276	3	1	4	3	74.26	
1.276	5	5	2	1	74.29	
1.271	1	2	0	3	74.61	
1.264	3	2	9	2	75.12	
1.262	4	3	10	1	75.24	
1.257	2	5	3	1	75.61	
1.256	1	5	5	0	75.66	
1.256	2	2	.2	3	75.66	
1.241	1	4	9	0	76.71	
1.238	9	2	3	3	76.97	
1.237	2	1	13	0	77.07	
1.224	3	0	6	3	77.99	
1.216	2	4	5	2	78.60	
1.188	1	4	9	1	80.81	
1.185	3	2	5	3	81.12	
1.184	2	1	13	1	81.16	
1.181	3	4	6	2	81.44	

$d(\text{\AA})$	I	hkl			$2\theta (\text{\\circ})$	$\lambda = 1.540598 \text{\AA}$
1.175	1	5	7	0	81.88	
1.170	2	3	1	3	82.37	
1.168	2	3	12	0	82.55	
1.168	1	0	14	0	82.55	
1.167	2	3	9	2	82.61	
1.164	5	1	7	3	82.83	
1.161	2	3	2	3	83.14	
1.152	2	2	6	3	83.94	
1.134	2	2	13	1	85.60	
1.133	1	4	10	1	85.68	
1.130	3	5	7	1	85.93	
1.124	2	5	2	2	86.55	
1.120	3	1	12	2	86.91	
1.111	2	5	3	2	87.83	
1.103	5	4	8	2	88.60	
1.083	2	6	2	1	90.65	
1.072	2	5	5	2	91.90	
1.063	1	4	9	2	92.92	
1.060	3	1	13	2	93.27	
1.053	2	5	9	1	94.08	
1.041	4	1	15	1	95.46	
1.036	3	6	5	1	96.01	
1.029	1	4	12	1	96.90	
1.028	4	0	0	4	97.09	
1.020	1	5	7	2	98.03	
1.015	2	3	12	2	98.70	
1.015	1	0	14	2	98.70	
1.013	1	5	10	1	98.95	
.991	1	6	1	2	102.05	
.986	1	1	4	4	102.72	
.985	3	3	9	3	102.86	
.970	1	3	13	2	105.20	
.966	5	2	11	3	105.78	
.964	2	5	1	3	106.12	
.959	2	5	2	3	106.92	
.957	1	7	3	0	107.26	
.953	2	3	10	3	107.87	
.952	1	2	16	1	108.04	
.951	1	5	3	3	108.25	
.937	1	5	12	1	110.55	
.935	1	3	1	4	111.03	
.932	1	1	7	4	111.52	

Gallium magnesium, Ga_5Mg_2

Structure

Tetragonal, I4/mmm (139), $Z = 4$. The structure was determined by Smith, Johnson and Wood [1969].

Lattice constants: [ibid.]

$$a = 8.627(26)\text{\AA}$$

$$c = 7.111(21)$$

Density

(calculated) 4.98 g/cm^3 [ibid.]

Thermal parameters

Isotropic [Smith et. al., 1969].

Scattering factors

Ga^0, Mg^0 [International Tables, 1962], corrected for dispersion [Cromer, 1965].

Scale factor

(integrated intensities) 11.81×10^4

References

- Cromer, D. T. (1965). Acta Cryst. 18, 17.
 International Tables for X-ray Crystallography III (1962), 202.
 Smith, G. S., Johnson, Q. and Wood, D.H. (1969). Acta Cryst. B25, 554.

Calculated Pattern (Peak heights)					
$d(\text{\AA})$	I	hkl	$2\theta (\text{^\circ})$		
				$\lambda = 1.540598\text{\AA}$	
6.10	1	1 1 0	14.52		
5.40	2	1 0 1	16.14		
4.31	18	2 0 0	20.58		
3.56	66	0 0 2	25.02		
3.39	62	2 1 1	26.26		
3.05	37	2 2 0	29.26		
2.74	47	2 0 2	32.62		
2.73	55	3 1 0	32.80		
2.67	47	3 0 1	33.60		
2.31	26	2 2 2	38.88		
2.29	7	1 0 3	39.40		
2.27	9	3 2 1	39.72		
2.16	44	3 1 2	41.70		
2.16	63	4 0 0	41.84		
2.03	61	3 3 0	44.52		
2.02	100	2 1 3	44.84		
1.84	22	4 0 2	49.38		
1.83	18	3 0 3	49.82		
1.77	19	3 3 2	51.74		
1.71	2	1 1 4	53.66		

$d(\text{\AA})$	I	hkl	$2\theta (\text{^\circ})$	
			$\lambda = 1.540598\text{\AA}$	
1.69	6	5 1 0	54.16	
1.68	6	4 3 1	54.70	
1.57	1	4 1 3	58.82	
1.56	6	5 2 1	59.06	
1.54	4	2 2 4	60.20	
1.53	4	5 1 2	60.56	
1.52	6	4 4 0	60.68	
1.44	8	6 0 0	64.78	
1.402	3	4 4 2	66.68	
1.395	4	4 3 3	67.04	
1.366	3	5 3 2	68.66	
1.334	14	2 1 5	70.52	
1.327	37	5 2 3	70.96	
1.324	22	5 4 1	71.16	
1.275	4	3 0 5	74.34	
1.266	1	6 3 1	74.98	
1.226	2	5 1 4	77.88	
1.222	3	3 2 5	78.12	
1.220	4	7 1 0	78.30	
1.217	3	6 1 3	78.54	
1.214	2	7 0 1	78.74	
1.196	3	6 4 0	80.16	
1.185	2	0 0 6	81.08	
1.176	1	4 1 5	81.82	
1.171	3	5 4 3	82.24	
1.154	5	7 1 2	83.76	
1.133	9	7 3 0	85.68	
1.130	5	6 3 3	85.94	
1.105	2	2 2 6	88.42	
1.097	2	4 3 5	89.16	
1.093	2	7 0 3	89.58	
1.091	1	6 5 1	89.84	
1.079	4	7 3 2	91.08	
1.064	7	5 2 5	92.82	
1.058	1	8 1 1	93.44	
1.046	1	8 2 0	94.84	
1.039	1	4 0 6	95.74	
1.032	1	8 0 2	96.56	
1.024	2	3 3 6	97.58	
1.006	1	5 5 4	99.94	
1.004	2	8 2 2	100.26	
1.001	2	6 5 3	100.60	
.982	1	2 1 7	103.28	
.978	2	5 4 5	103.92	
.975	5	8 1 3	104.34	
.971	2	5 1 6	105.04	
.931	1	7 0 5	111.60	
.928	1	9 2 1	112.26	
.915	1	6 0 6	114.76	
.881	1	9 3 2	121.94	

Gallium magnesium, Ga_5Mg_2 - continued

Calculated Pattern (Integrated)					d (Å)	I	hkl	20 (°)	λ = 1.540598 Å	20 (°)	
									λ = 1.540598 Å	°	
6.10	1	1	1	0	14.51		1.163	1	1	6	82.92
5.49	1	1	0	1	16.14		1.154	4	7	1	83.75
4.31	14	2	0	0	20.57		1.154	3	5	5	83.75
3.56	56	0	0	2	25.02		1.134	3	6	4	85.59
3.39	53	2	1	1	26.26		1.133	13	7	3	85.69
3.05	33	2	2	0	29.26		1.130	2	6	3	85.91
2.74	42	2	0	2	32.61		1.105	3	2	2	88.42
2.73	47	3	1	0	32.80		1.097	1	5	0	89.16
2.67	45	3	0	1	33.59		1.097	1	4	3	89.16
2.31	26	2	2	2	38.87		1.093	3	7	0	89.57
2.29	7	1	0	3	39.39		1.091	1	6	5	89.78
2.27	9	3	2	1	39.71		1.079	6	7	3	91.07
2.16	40	3	1	2	41.70		1.064	11	5	2	92.82
2.16	54	4	0	0	41.85		1.058	1	8	1	93.43
2.03	61	3	3	0	44.52		1.058	1	7	4	93.43
2.02	100	2	1	3	44.84		1.046	1	8	2	94.83
2.01	1	4	1	1	45.13		1.039	2	4	0	95.74
1.84	24	4	0	2	49.38		1.032	1	8	0	96.57
1.83	20	3	0	3	49.81		1.024	4	3	3	97.58
1.77	21	3	3	2	51.75		1.017	1	6	6	98.51
1.71	2	1	1	4	53.66		1.010	1	4	2	99.43
1.70	1	4	2	2	54.04		1.006	1	5	5	99.95
1.69	6	5	1	0	54.17		1.004	1	6	1	100.18
1.68	2	5	0	1	54.70		1.004	2	8	2	100.26
1.68	5	4	3	1	54.70		1.001	3	6	5	100.60
1.57	1	4	1	3	58.82		.982	1	2	1	103.28
1.56	6	5	2	1	59.06		.978	3	5	4	103.91
1.54	5	2	2	4	60.20		.978	1	6	6	104.00
1.53	4	5	1	2	60.56		.975	2	7	4	104.34
1.53	6	4	4	0	60.68		.975	6	8	1	104.34
1.44	10	6	0	0	64.79		.971	3	5	1	105.04
1.402	4	4	4	2	66.68		.965	1	7	5	105.89
1.395	5	4	3	3	67.04		.931	2	7	0	111.59
1.366	3	5	3	2	68.65		.928	1	9	2	112.26
1.334	15	2	1	5	70.52		.915	2	6	0	114.76
1.333	6	6	0	2	70.60		.910	1	7	2	115.58
1.327	49	5	2	3	70.95		.909	1	9	3	115.79
1.324	2	5	4	1	71.17		.907	1	8	5	116.27
1.275	6	3	0	5	74.35		.902	1	8	2	117.37
1.266	1	6	3	1	74.99		.895	1	6	2	118.86
1.226	2	5	1	4	77.88		.889	1	0	0	120.13
1.223	3	3	2	5	78.11		.881	1	9	3	121.93
1.220	3	7	1	0	78.30		.872	3	6	5	124.01
1.220	2	5	5	0	78.30		.871	4	7	7	124.24
1.217	1	6	1	3	78.53		.870	6	9	2	124.51
1.214	3	7	0	1	78.74		.870	1	7	6	124.51
1.196	4	6	4	0	80.16		.863	5	10	0	126.48
1.185	3	0	0	6	81.08		.858	2	5	2	127.76
1.176	1	4	1	5	81.82		.855	1	7	4	128.55
1.171	4	5	4	3	82.24		.855	4	8	1	128.55

Lead strontium nitrate, $\text{Pb}(\text{NO}_3)_2\text{-Sr}(\text{NO}_3)_2$, calculated solid solution series

Structure

Cubic, $P2_13$ (198), $Z=4$. The structures of $\text{Pb}(\text{NO}_3)_2$ and $\text{Sr}(\text{NO}_3)_2$ were determined by Vegard [1922]. He found them to be isostructural with each other and with $\text{Ba}(\text{NO}_3)_2$ and $\text{Ca}(\text{NO}_3)_2$. Hamilton [1957] refined the structure of $\text{Pb}(\text{NO}_3)_2$. These earlier studies all assumed the space group to be $\text{Pa}3$ (205). However, Birnstock [1967] used neutron diffraction methods to refine the structure of $\text{Ba}(\text{NO}_3)_2$ and found weak reflections not permitted by $\text{Pa}3$. He assigned the space group $P2_13$ which we used here. The atom positions for $\text{Sr}(\text{NO}_3)_2$ used in these calculations were those given by Vegard and Bilberg [1931]; the $\text{Pb}(\text{NO}_3)_2$ positions were from Hamilton [1957]. The system $\text{Pb}(\text{NO}_3)_2\text{-Sr}(\text{NO}_3)_2$ forms a complete solid solution series [Laybourn et al., 1934].

Lattice constants

The constants were derived by interpolation on a molar ratio using the following: for $\text{Pb}(\text{NO}_3)_2$, $a = 7.8573$ [Swanson et al., 1955], modified to conform to new wavelength measurements; for $\text{Sr}(\text{NO}_3)_2$, $a = 7.7813$ [McMurdie et al., 1974].

Thermal parameters

Isotropic: barium $B = .93$; strontium $B = 1.0$; nitrogen $B = 1.2$; oxygen $B = 1.16$.

Scattering factors

N^0 , O^- [International Tables, 1962].
 Pb^{2+} , Sr^{2+} [Cromer and Waber, 1965].

The factors used were proportional to the molar ratio, assuming random distribution of the cations.

References

- Birnstock, R. (1967). *Z. Krist.* 124, 310.
- Cromer, D. T. and Waber, J. T. (1965). *Acta Cryst.* 18, 104.
- Hamilton, W. C. (1957). *Acta Cryst.* 10, 103.
- International Tables for X-ray Crystallography III (1962), 202.
- Laybourn K., Madgin, M. W., and Freeman, D. (1934). *J. Chem. Soc.* 1934, 139.
- McMurdie, et al. (1974). This publication, pg. 31.
- Swanson, H. E., Gilfrich, N. T., and Ugrinic, G. (1955). *Nat'l. Bur. Std. U.S. Circ.* 539, V, 36.
- Vegard, L. (1922). *Z. Phys.* 9, 395.
- Vegard, L. and Bilberg, L. (1931). *Avhandl. Norske Videnskaps-Akad. Oslo. I. Mat.-Naturv. Kl.* 1931, No. 12.

$\text{Pb}_{.67}\text{Sr}_{.33}(\text{NO}_3)_2$				$\text{Pb}_{.33}\text{Sr}_{.67}(\text{NO}_3)_2$			
$h\bar{k}\bar{l}$	$d(\text{\AA})$	I	$2\theta (\text{\\textdegree})$	$d(\text{\AA})$	I	$2\theta (\text{\\textdegree})$	
		$\lambda=1.540598$			$\lambda=1.540598$		
111	4.521	100	19.62	4.507	100	19.68	
200	3.914	31	22.70	3.904	24	22.76	
210	3.501	7	25.42	3.490	12	25.50	
211	3.198	5	27.88	3.186	8	27.98	
220	2.769	29	32.30	2.759	27	32.42	
221	2.611	--	34.32	2.602	1	34.44	
311	2.361	62	38.08	2.354	62	38.20	
222	2.261	32	39.84	2.253	38	39.98	
123 +	2.093	<1	43.18	2.086	<1	43.34	
400	1.958	11	46.34	1.951	12	46.50	
410	1.900	<1	47.84	1.893	<1	48.02	
411	1.846	1	49.32	1.840	1	49.50	
331	1.796	15	50.78	1.791	14	50.96	
024 +	1.752	14	52.18	1.745	14	52.38	
124	1.709	<1	53.58	1.704	<1	53.76	
332	1.670	<1	54.94	1.664	<1	55.14	
422	1.599	10	57.60	1.593	9	57.82	
430	1.567	--	58.90	1.561	<1	59.12	
134 +	1.536	<1	60.20	1.531	<1	60.42	
511 +	1.508	11	61.46	1.502	11	61.70	

Lead strontium nitrate, $\text{Pb}(\text{NO}_3)_2\text{-Sr}(\text{NO}_3)_2$, calculated solid solution series - continued

Pb _{0.67} Sr _{0.33} (NO ₃) ₂				Pb _{0.33} Sr _{0.67} (NO ₃) ₂			
hkl	d (Å)	I $\lambda=1.540598$	2θ (°)	d (Å)	I $\lambda=1.540598$	2θ (°)	
432	1.4544	<1	63.96	1.4496	<1	64.20	
440	1.3847	5	67.60	1.3800	6	67.86	
433	1.3433	<1	69.98	1.3386	<1	70.26	
531 +	1.3239	12	71.16	1.3194	11	71.44	
442 +	1.3055	5	72.32	1.3012	5	72.60	
610	1.2877	--	73.48	1.2832	<1	73.78	
611 +	1.2706	<1	74.64	1.2662	<1	74.94	
620 +	1.2385	3	76.92	1.2344	3	77.22	
533	1.1944	4	80.32	1.1905	4	80.64	
622	1.1808	4	81.44	1.1770	4	81.76	
542	1.1676	--	82.56	1.1637	<1	82.90	
136	1.1548	--	83.68	1.1510	<1	84.02	
444	1.1305	1	85.90	1.1267	1	86.26	
711 +	1.0967	4	89.24	1.0932	4	89.60	
640 +	1.0861	2	90.34	1.0826	2	90.72	
146	1.0757	<1	91.46	1.0723	<1	91.84	
246 +	1.0466	4	94.78	1.0431	4	95.20	
553 +	1.0197	5	98.12	1.0164	5	98.56	
800	0.9790	<1	103.78	0.9758	<1	104.26	
733	.9569	1	107.22	.9537	1	107.74	
644 +	.9497	3	108.40	.9467	3	108.92	
128	.9429	--	109.56	.9398	<1	110.10	
822 +	.9230	2	113.14	.9200	2	113.70	
831	.9105	--	115.56	.9074	<1	116.18	
751 +	.9044	3	116.80	.9014	3	117.42	
662	.8984	1	118.06	.8955	1	118.68	
832	.8925	--	119.32	.8896	<1	119.96	
048 +	.8757	1	123.20	.8727	1	123.92	
753 +	.8597	4	127.28	.8569	4	128.04	
842 +	.8546	2	128.68	.8517	2	129.48	
664	.8349	1	134.62	.8322	1	135.54	
931 +	.8210	2	139.50	.8183	2	140.54	
844	.7994	1	149.00	.7967	1	150.40	
933 +	.7872	4	156.24	.7846	4	158.10	
068 +	.7832	2	159.16				
Lattice constant	7.8322 \AA			7.8064 \AA			
Density (calc.)	4.033 g/cm^3			3.506 g/cm^3			

Lithium silver bromide, LiBr-AgBr, calculated solid solution series

Structure

Cubic, Fm3m (225), Z = 4, isostructural with NaCl. The system LiBr-AgBr forms a complete solid solution series [Sandonnini and Scarpa, 1913].

Lattice constants

The constants were derived by interpolation on a molar ratio, using the cell dimensions of LiBr ($a = 5.5016\text{\AA}$) and AgBr ($a = 5.7749\text{\AA}$). Those dimensions were determined by Swanson et al. [1955] and are modified to conform to new wavelength measurements.

Thermal parameters

Isotropic. Overall B = 1.6

Scattering factors

Li^+ , Ag^+ , Br^- [International Tables, 1962].

Random distribution of the cations was assumed, and the factors used were proportional to the molar ratio.

References

International Tables for X-ray Crystallography III (1962), 202, 206, 211.

Sandonnini, C. and Scarpa, G. (1913). Atti reale accad. Lincei Sez. II, 22, 519.

Swanson, H. E., Fuyat, R. K. and Ugrinic, G. M. (1955). Natl. Bur. Std. U.S. Circ. 539, 4.

	Li _{.8} Ag _{.2} Br			Li _{.6} Ag _{.4} Br			Li _{.4} Ag _{.6} Br			Li _{.2} Ag _{.8} Br		
hkl	d(Å)	I	2θ(°) λ=1.540598									
111	3.209	53	27.78	3.238	16	27.52	3.271	2	27.24	3.302	--	26.98
200	2.778	100	32.20	2.805	100	31.88	2.833	100	31.56	2.861	100	31.24
220	1.9642	55	46.18	1.9837	58	45.70	2.003	55	45.24	2.022	60	44.78
311	1.6755	15	54.74	1.6915	4	54.18	1.7084	--	53.60	1.7246	--	53.06
222	1.6040	16	57.40	1.6196	16	56.80	1.6354	16	56.20	1.6511	17	55.62
400	1.3890	6	67.36	1.4027	6	66.62	1.4162	6	65.90	1.4301	6	65.18
331	1.2747	4	74.36	1.2871	1	73.52	1.2999	--	72.68	1.3124	--	71.88
420	1.2423	13	76.64	1.2545	14	75.76	1.2668	14	74.90	1.2791	15	74.06
422	1.1342	9	85.56	1.1454	9	84.52	1.1566	9	83.52	1.1676	9	82.56
511 +	1.0692	2	92.18	1.0798	1	91.02	1.0903	--	89.90	1.1010	--	88.80
440	0.9822	2	103.30	0.9919	2	101.90	1.0016	2	100.54	1.0112	2	99.24
531	.9392	2	110.20	.9484	1	108.62	0.9576	--	107.10	0.9669	--	105.62
600 +	.9260	5	112.58	.9351	5	110.92	.9443	5	109.32	.9534	5	107.80
620	.8785	3	122.52	.8871	3	120.52	.8959	3	118.60	.9045	3	116.78
533	.8473	1	130.76	.8557	--	128.38	.8640	--	126.14	.8723	--	124.02
622	.8376	3	133.74	.8459	3	131.18	.8541	3	128.80	.8624	3	126.56
444	.8020	1	147.68	.8099	1	144.02	.8178	1	140.76	.8257	1	137.80
711 +				.7857	--	157.28	.7933	--	152.32	.8010	--	148.18
640							.7857	3	157.30	.7933	3	152.36
Lattice constant	5.5563 ^o A			5.6110 ^o A			5.6656 ^o A			5.7203 ^o A		
Density (calc.)	4.144 g/cm ³			4.783 g/cm ³			5.384 g/cm ³			5.947 g/cm ³		

Phosphoric acid hydrate, $H_3PO_4 \cdot \frac{1}{2}H_2O$

Structure

Monoclinic, $P2_1/a$ (14), $Z=8$. The structure was determined by Mighell, Smith and Brown [1969].

Lattice constants: [ibid.]

$$\begin{aligned} a &= 7.922(10)^\circ \text{\AA} \\ b &= 12.987(20) \\ c &= 7.470(10) \\ \beta &= 109.9(1)^\circ \end{aligned}$$

Density

(calculated) 1.967 g/cm^3

Thermal parameters

Isotropic [ibid.]

Scattering factors

F^0, O^- [International Tables, 1962]

Scale factor

(integrated intensities) 2.663×10^4

Additional patterns

1. Lehr et al. [1967].
2. Norbert [1972].

References

- International Tables for X-ray Crystallography III (1962), 202.
 Lehr, J. R., Brown, E. H., Frazier, A. W., Smith, J. P. and Thrasher, R. D. (1967). TVA Chem. Engineering Bulletin # 6, 53.
 Mighell, A.D., Smith, J.P. and Brown, W.E. (1969). Acta Cryst. B25, 776.
 Norbert, A. (1972). Bull. Soc. franc. Min. Crist. 95, 154.

d (Å)	I	hkl	2θ (°)			$\lambda = 1.540598\text{\AA}$
			h	k	l	
3.21	44	-1 2 2				27.74
3.14	2	-2 0 2				28.36
3.09	6	0 2 2	+ +			28.88
3.06	9	-2 1 2				29.20
2.98	3	1 4 0				30.00
2.95	11	0 4 1				30.30
2.91	26	2 0 1				30.74
2.84	14	2 1 1				31.52
2.83	15	-2 2 2	+ +			31.58
2.81	4	-1 3 2				31.78
2.62	2	1 4 1				34.26
2.592	6	1 2 2	+ +			34.58
2.545	5	-2 3 2				35.24
2.490	4	-2 4 1				36.04
2.445	14	-3 2 1	+ +			36.72
2.438	12	0 5 1	+ +			36.84
2.418	4	-3 1 2				37.16
2.384	2	0 4 2				37.70
2.367	2	1 3 2				37.98
2.341	2	0 0 3	+ +			38.42
2.301	4	-3 2 2				39.12
2.254	8	-3 3 1	+ +			39.96
2.235	1	-2 2 3				40.32
2.207	2	2 0 2				40.86
2.203	4	0 2 3				40.94
2.176	1	2 1 2				41.46
2.158	7	-2 5 1	+ +			41.82
2.139	2	-3 3 2				42.22
2.130	2	2 5 0				42.40
2.125	4	-1 5 2				42.50
2.088	2	0 5 2	+ +			43.30
2.070	3	-3 1 3	+ +			43.70
2.060	3	0 3 3				43.92
2.047	2	-1 6 1				44.22
2.019	7	1 1 3				44.86
2.003	1	-2 5 2				45.24
1.975	8	-4 0 1	+ +			45.92
1.961	1	-3 4 2				46.26
1.951	3	-4 1 1				46.50
1.949	3	1 2 3				46.56
1.943	6	1 6 1	+ +			46.70
1.938	3	2 5 1				46.84
1.899	2	0 4 3				47.86
1.887	2	-3 3 3				48.18
1.868	6	-1 6 2				48.70
1.860	2	-4 2 2				48.92
1.848	3	1 3 3				49.28
1.843	5	0 6 2				49.42
1.831	1	-2 1 4				49.76
1.797	3	-1 5 3				50.76

Calculated Pattern (Peak heights)

d (Å)	I	hkl	2θ (°)			$\lambda = 1.540598\text{\AA}$
			h	k	l	
7.02	40	0 0 1				12.60
6.47	6	1 1 0	+ +			13.68
5.66	9	-1 1 1				15.64
4.89	46	1 2 0				18.12
4.52	74	-1 2 1				19.64
4.18	4	1 1 1				21.24
3.88	46	-2 0 1				22.88
3.72	52	2 0 0	+ +			23.88
3.68	15	0 3 1				24.14
3.65	100	1 2 1				24.36
3.56	44	-1 1 2	+ +			25.02
3.51	12	0 0 2				25.34
3.39	11	0 1 2				26.26
3.33	2	-2 2 1				26.74
3.25	68	0 4 0				27.46

Phosphoric acid hydrate, $H_3PO_4 \cdot \frac{1}{2}H_2O$ - continued

$d(\text{\AA})$	I	hkl			$2\theta(^{\circ})$
					$\lambda = 1.540598\text{\AA}$
1.792	2	4	2	0	+ 50.92
1.783	1	-2	6	2	51.20
1.779	3	-2	2	4	+ 51.32
1.766	3	-4	1	3	51.72
1.762	3	-3	4	3	51.86
1.729	2	1	4	3	52.90
1.719	2	2	1	3	53.26
1.702	4	3	2	2	+ 53.82
1.687	1	-4	4	1	54.34
1.675	1	2	2	3	54.76
1.665	4	4	0	1	55.12
1.659	1	-1	7	2	55.34
1.633	2	3	3	2	56.28
1.631	2	-3	5	3	56.36
1.623	4	0	8	0	+ 56.66
1.606	1	1	5	3	57.32
1.602	1	-2	6	3	57.48
1.581	2	1	1	4	+ 58.32
1.572	1	-4	5	1	58.70
1.567	1	-5	1	2	58.90
1.561	2	-4	1	4	59.14
1.546	1	2	6	2	59.78
1.528	1	-4	2	4	60.54
1.518	1	-3	7	1	60.98
1.501	2	-5	1	3	61.74
1.498	3	-2	8	1	61.90
1.481	3	-3	7	2	62.66
1.478	3	-4	3	4	62.82
1.470	1	-4	5	3	63.22
1.452	4	5	2	0	64.08

Calculated Pattern (Integrated)					
$d(\text{\AA})$	I	hkl			$2\theta(^{\circ})$
					$\lambda = 1.540598\text{\AA}$
7.02	33	0	0	1	12.59
6.49	4	0	2	0	13.63
6.46	4	1	1	0	13.69
5.66	9	-1	1	1	15.64
4.89	44	1	2	0	18.11
4.52	70	-1	2	1	19.63
4.18	4	1	1	1	21.24
3.88	47	-2	0	1	22.89
3.74	5	1	3	0	23.75
3.72	41	2	0	0	23.87
3.72	15	-2	1	1	23.90
3.69	11	0	3	1	24.13
3.65	100	1	2	1	24.36
3.58	1	2	1	0	24.85
3.57	7	-1	3	1	24.95
3.56	43	-1	1	2	25.01
3.51	11	0	0	2	25.34
3.39	12	0	1	2	26.27
3.33	1	-2	2	1	26.73
3.25	74	0	4	0	27.45
3.21	45	-1	2	2	27.73
3.14	2	-2	0	2	28.36
3.09	1	1	3	1	28.86
3.09	5	0	2	2	28.88
3.06	9	-2	1	2	29.20
2.98	3	1	4	0	30.00
2.95	12	0	4	1	30.30
2.91	28	2	0	1	30.74
2.89	3	-2	3	1	30.91
2.84	13	2	1	1	31.52
2.83	9	-2	2	2	31.59
2.82	2	2	3	0	31.67
2.81	3	-1	3	2	31.79
2.62	2	1	4	1	34.25
2.592	6	1	2	2	34.58
2.587	2	-3	1	1	34.64
2.544	6	-2	3	2	35.25
2.491	4	-2	4	1	36.03
2.453	2	1	5	0	36.61
2.446	11	-3	2	1	36.71
2.445	3	-1	1	3	36.73
2.439	2	3	1	0	36.82
2.436	7	0	5	1	36.87
2.417	4	-3	1	2	37.16
2.384	2	0	4	2	37.70
2.367	3	1	3	2	37.98
2.342	1	-2	1	3	38.41
2.341	2	0	0	3	38.42
2.301	4	-3	2	2	39.12
2.259	3	-2	4	2	39.88

Phosphoric acid hydrate, $H_3PO_4 \cdot \frac{1}{2}H_2O$ - continued

$d(\text{\AA})$	I	hkl			$2\theta(^{\circ})$						
						$\lambda = 1.540598\text{\AA}$					
2.254	8	-3	3	1	39.96	1.658	1	-1	7	2	55.35
2.235	1	-2	2	3	40.32	1.634	3	3	3	2	56.27
2.207	2	2	0	2	40.85	1.631	2	-3	5	3	56.35
2.203	4	0	2	3	40.94	1.625	1	-3	6	2	56.59
2.176	1	2	1	2	41.46	1.623	5	0	8	0	56.65
2.159	8	-2	5	1	41.81	1.606	1	1	5	3	57.32
2.158	1	-1	3	3	41.83	1.602	1	-2	6	3	57.50
2.139	2	-3	3	2	42.22	1.582	2	0	8	1	58.29
2.130	1	2	5	0	42.39	1.581	2	1	1	4	58.34
2.126	4	-1	5	2	42.49	1.572	1	-4	5	1	58.69
2.088	2	0	5	2	43.29	1.567	1	-5	1	2	58.90
2.086	1	-2	3	3	43.34	1.561	3	-4	1	4	59.14
2.079	1	1	6	0	43.51	1.546	1	2	6	2	59.79
2.070	2	-3	1	3	43.70	1.528	1	-4	2	4	60.54
2.069	1	0	6	1	43.73	1.518	2	-3	7	1	60.99
2.059	4	0	3	3	43.93	1.501	3	-5	1	3	61.74
2.047	2	-1	6	1	44.22	1.498	2	-2	8	1	61.90
2.019	9	1	1	3	44.87	1.481	3	-3	7	2	62.67
2.003	1	-2	5	2	45.24	1.478	3	-4	3	4	62.83
1.975	3	-1	4	3	45.90	1.470	1	-4	5	3	63.21
1.974	8	-4	0	1	45.93	1.454	1	0	7	3	63.98
1.961	1	-3	4	2	46.26	1.452	5	5	2	0	64.08
1.952	2	-4	1	1	46.49						
1.949	2	1	2	3	46.55						
1.943	5	1	6	1	46.70						
1.941	1	-4	0	2	46.76						
1.937	1	2	5	1	46.87						
1.899	3	0	4	3	47.86						
1.887	2	-3	3	3	48.19						
1.868	8	-1	6	2	49.70						
1.860	2	-4	2	2	48.93						
1.848	3	1	3	3	49.27						
1.843	4	0	6	2	49.42						
1.831	1	-2	1	4	49.75						
1.797	4	-1	5	3	50.76						
1.794	1	0	7	1	50.86						
1.790	1	4	2	0	50.98						
1.783	1	-2	6	2	51.19						
1.779	1	-1	7	1	51.30						
1.779	3	-2	2	4	51.32						
1.766	4	-4	1	3	51.72						
1.761	2	-3	4	3	51.87						
1.748	1	3	1	2	52.29						
1.729	2	1	4	3	52.90						
1.719	2	2	1	3	53.25						
1.702	5	3	2	2	53.81						
1.701	2	-2	3	4	53.86						
1.687	1	-4	4	1	54.34						
1.675	1	2	2	3	54.75						
1.665	5	4	0	1	55.11						

Potassium cerium fluoride, β - $KCeF_4$

Structure

Orthorhombic, Pnam (62), Z=4. The structure was determined by Brunton [1969].

Lattice constants: (published values: 6.2895, 15.596, 3.8040 [ibid.])

$$\begin{aligned} a &= 6.2899(3)\text{\AA} \\ b &= 15.597(2) \\ c &= 3.8042(3) \end{aligned}$$

Density

(calculated) 4.542 g/cm³

Thermal parameters

Isotropic: potassium B = 1.02; cerium B = 0.55; fluorine (1) B = 1.17; fluorine (2) B = 0.96; fluorine (3) B = 1.03; fluorine (4) B = 1.28.

Polymorphism

Two other forms have been described. At the stoichiometric composition, β - $KCeF_4$ becomes the cubic, fluorite-type α - $KCeF_4$ above 755 °C. A hexagonal phase, β_1 - $KCeF_4$ does not occur as an equilibrium compound [Brunton, 1969].

Scattering factors

K^+ , Ce^{3+} , F^- [Cromer and Waber, 1965]; the cerium factors were corrected for dispersion [Dauben and Templeton, 1955].

Scale factor

(integrated intensities) 6.570×10^4

References

- Brunton, G. (1969). Acta Cryst. B25, 600.
- Cromer, D. T. and Waber, J. T. (1965) Acta Cryst. 18, 104.
- Dauben, C. H. and Templeton, D. H. (1955). Acta Cryst. 8, 241.

Calculated Pattern (Peak heights)				
d (\text{\AA})	I	hkl	2θ (°)	$\lambda = 1.540598\text{\AA}$
7.797	100	0 2 0	11.34	
4.897	74	1 2 0	18.10	
3.314	81	1 4 0	26.88	
3.186	93	1 1 1	27.98	
3.144	33	2 0 0	28.36	
3.0703	45	0 3 1	29.06	
2.9173	9	2 2 0	30.62	
2.7946	1	1 5 0	32.00	
2.5991	5	0 6 0	34.48	
2.4994	7	1 4 1	35.90	
2.4238	9	2 0 1	37.06	
2.4125	27	0 5 1	37.24	
2.4051	17	1 6 0	37.36	
2.3952	3	2 1 1	37.52	
2.2140	2	2 5 0	40.72	

d (\text{\AA})	I	hkl	2θ (°)	$\lambda = 1.540598\text{\AA}$
2.1965	63	2 3 1	41.06	
2.0990	2	1 7 0	43.04	
2.0779	1	3 1 0	43.52	
2.0309	2	1 6 1	44.58	
2.0248	3	3 2 0	44.72	
2.0036	5	2 6 0	45.22	
1.9498	12	0 8 0	46.54	
1.9451	8	3 3 0	46.66	
1.9225	3	0 7 1	47.24	
1.9141	25	2 5 1	47.46	
1.9021	20	0 0 2	47.78	
1.8469	24	3 4 0	+ 49.30	
1.8385	35	1 7 1	49.54	
1.8234	23	3 1 1	49.98	
1.7731	7	1 2 2	51.50	
1.7312	1	3 3 1	52.84	
1.6571	8	2 8 0	55.40	
1.6495	15	1 4 2	55.68	
1.6402	2	2 7 1	56.02	
1.6317	2	3 6 0	56.34	
1.6274	8	2 0 2	56.50	
1.5934	2	2 2 2	57.82	
1.5824	1	3 5 1	58.26	
1.5726	3	4 0 0	58.66	
1.5600	1	0 10 0	59.18	
1.5415	2	4 2 0	59.96	
1.5350	2	0 6 2	60.24	
1.5295	6	1 9 1	60.48	
1.5137	3	1 10 0	61.18	
1.4913	1	1 6 2	62.20	
1.4170	6	3 7 1	65.86	
1.4098	1	1 7 2	66.24	
1.3997	6	4 3 1	66.78	
1.3960	3	2 10 0	66.98	
1.3861	1	3 2 2	67.52	
1.3797	2	2 6 2	67.88	
1.3614	5	0 8 2	68.92	
1.3453	2	4 6 0	69.86	
1.3284	3	0 11 1	70.88	
1.3249	11	3 4 2	71.10	
1.3172	2	4 5 1	71.58	
1.2729	3	1 12 0	74.48	
1.2602	3	3 9 1	75.36	
1.2512	2	3 10 0	76.00	
1.2495	5	2 8 2	76.12	
1.2418	1	5 2 0	76.68	
1.2390	4	1 1 3	+ 76.88	
1.2320	2	0 3 3	77.40	
1.2240	8	2 11 1	+ 78.00	
1.2120	2	4 0 2	78.92	

Potassium cerium fluoride, β -KCeF₄ - continued

d (Å)	I	hkl	2θ (°)	λ = 1.540598 Å
1.2062	1	0 10 2	79.38	
1.1974	3	5 4 0 +	80.08	
1.1910	4	5 1 1	80.60	
1.1844	2	1 10 2	81.14	
1.1746	2	0 5 3	81.96	
1.1470	4	2 3 3	84.38	
1.1443	3	0 13 1	84.62	
1.1224	1	3 11 1	86.68	
1.1047	2	3 12 0	88.42	
1.1004	3	2 5 3	88.86	
1.0984	2	4 6 2	89.06	
1.0856	3	1 7 3	90.40	
1.0826	4	3 1 3	90.72	
1.0752	2	2 13 1	91.52	
1.0579	3	1 12 2	93.46	
1.0527	2	5 7 1	94.06	
1.0500	2	2 14 0	94.38	
1.0483	1	6 0 0	94.58	
1.0455	1	3 10 2	94.92	
1.0400	1	5 2 2	95.58	
1.0293	3	4 8 2	96.90	
1.0148	2	4 11 1	98.76	
1.0132	3	5 4 2	98.98	
1.0105	2	1 9 3	99.34	
.9920	2	6 3 1	101.88	
.9905	3	1 15 1	102.10	
.9835	1	5 9 1	103.12	
.9755	2	3 7 3 +	104.30	
.9730	2	5 6 2	104.68	
.9698	2	4 3 3	105.18	
.9614	2	6 5 1 +	106.50	
.9553	2	3 12 2 +	107.48	
.9511	1	0 0 4 +	108.18	
.9452	1	0 11 3	109.16	
.9412	1	4 5 3	109.86	
.9311	1	2 16 0	111.64	
.9253	1	4 13 1	112.72	
.9232	1	6 8 0	113.10	
.9195	2	3 9 3 +	113.80	
.9181	1	6 0 2	114.08	
.9141	2	1 4 4	114.84	
.9118	1	6 2 2	115.30	
.9103	1	2 0 4	115.60	
.9091	1	4 14 0	115.84	
.9051	3	2 11 3 +	116.66	
.8916	2	5 1 3	119.52	

Calculated Pattern (Integrated)				
d (Å)	I	hkl	2θ (°)	λ = 1.540598 Å
7.799	84	0 2 0	11.34	
4.896	73	1 2 0	18.10	
3.314	86	1 4 0	26.88	
3.186	100	1 1 1	27.98	
3.145	35	2 0 0	28.36	
3.0701	49	0 3 1	29.06	
2.9167	10	2 2 0	30.63	
2.7946	1	1 5 0	32.00	
2.5995	6	0 6 0	34.47	
2.4988	9	1 4 1	35.91	
2.4239	9	2 0 1	37.06	
2.4121	32	0 5 1	37.25	
2.4024	3	1 6 0	37.40	
2.3952	1	2 1 1	37.52	
2.2147	1	2 5 0	40.71	
2.1969	79	2 3 1	41.05	
2.1003	3	1 7 0	43.03	
2.0779	1	3 1 0	43.52	
2.0313	2	1 6 1	44.57	
2.0247	3	3 2 0	44.72	
2.0037	6	2 6 0	45.22	
1.9496	16	0 8 0	46.54	
1.9445	1	3 3 0	46.68	
1.9226	3	0 7 1	47.24	
1.9140	32	2 5 1	47.46	
1.9021	25	0 0 2	47.78	
1.8479	4	0 2 2	49.27	
1.8466	29	3 4 0	49.31	
1.8387	44	1 7 1	49.54	
1.8236	31	3 1 1	49.97	
1.7730	9	1 2 2	51.50	
1.7314	1	3 3 1	52.83	
1.6570	10	2 8 0	55.40	
1.6497	21	1 4 2	55.67	
1.6404	1	2 7 1	56.01	
1.6320	3	3 6 0	56.33	
1.6276	10	2 0 2	56.49	
1.5932	4	2 2 2	57.83	
1.5824	1	3 5 1	58.26	
1.5725	4	4 0 0	58.66	
1.5597	1	0 10 0	59.19	
1.5414	2	4 2 0	59.96	
1.5350	2	0 6 2	60.24	
1.5297	9	1 9 1	60.47	
1.5139	4	1 10 0	61.17	
1.4913	2	1 6 2	62.20	
1.4170	9	3 7 1	65.86	
1.4099	1	1 7 2	66.24	
1.3996	9	4 3 1	66.79	
1.3973	1	2 10 0	66.91	

Potassium cerium fluoride, β -KCeF₄ - continued

$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$	$\lambda = 1.540598\text{\AA}$	$d(\text{\AA})$	I	hkl	$2\theta(^{\circ})$	$\lambda = 1.540598\text{\AA}$
1.3863	2	3 2 2	67.51		.9792	1	5 10 0	103.75	
1.3795	3	2 6 2	67.89		.9755	3	3 7 3	104.30	
1.3615	8	0 8 2	68.91		.9748	1	0 16 0	104.41	
1.3455	3	4 6 0	69.85		.9730	2	5 6 2	104.69	
1.3286	4	0 11 1	70.87		.9698	3	4 3 3	105.18	
1.3249	16	3 4 2	71.10		.9614	4	6 5 1	106.49	
1.3173	3	4 5 1	71.57		.9613	1	0 14 2	106.51	
1.2729	5	1 12 0	74.48		.9570	1	4 10 2	107.20	
1.2603	5	3 9 1	75.35		.9556	1	2 15 1	107.43	
1.2514	2	3 10 0	75.98		.9553	4	3 12 2	107.48	
1.2494	7	2 8 2	76.13		.9510	2	0 0 4	108.18	
1.2419	1	5 2 0	76.67		.9503	1	1 14 2	108.31	
1.2391	5	1 1 3	76.87		.9452	2	0 11 3	109.16	
1.2386	2	3 6 2	76.91		.9411	2	4 5 3	109.87	
1.2319	3	0 3 3	77.40		.9336	1	1 2 4	111.19	
1.2240	5	4 8 0	78.00		.9311	1	2 16 0	111.64	
1.2239	10	2 11 1	78.01		.9252	2	4 13 1	112.73	
1.2120	3	4 0 2	78.93		.9233	2	6 8 0	113.08	
1.2061	1	0 10 2	79.39		.9197	3	3 9 3	113.77	
1.1976	2	4 ? 2	80.06		.9193	2	2 14 2	113.84	
1.1972	4	5 4 0	80.09		.9181	2	6 0 2	114.07	
1.1909	7	5 1 1	80.61		.9141	4	1 4 4	114.84	
1.1845	3	1 10 2	81.13		.9118	1	6 2 2	115.30	
1.1747	3	0 5 3	81.95		.9103	2	2 0 4	115.60	
1.1471	7	2 3 3	84.37		.9091	1	4 14 0	115.85	
1.1442	1	0 13 1	84.63		.9052	5	2 11 3	116.63	
1.1324	1	5 6 0	85.73		.9048	4	3 15 1	116.72	
1.1261	1	2 10 2	86.32		.9042	1	2 2 4	116.84	
1.1223	1	3 11 1	86.69		.9039	2	5 12 0	116.90	
1.1141	1	0 14 0	87.49		.8927	1	7 2 0	119.30	
1.1047	3	3 12 0	88.42		.8916	4	5 1 3	119.52	
1.1004	5	2 5 3	88.85						
1.0984	3	4 6 2	89.06						
1.0970	1	1 14 0	89.21						
1.0855	6	1 7 3	90.40						
1.0824	5	3 1 3	90.74						
1.0753	3	2 13 1	91.51						
1.0579	5	1 12 2	93.47						
1.0527	5	5 7 1	94.07						
1.0501	1	2 14 0	94.37						
1.0483	1	6 0 0	94.58						
1.0454	2	3 10 2	94.92						
1.0399	2	5 2 2	95.59						
1.0293	6	4 8 2	96.90						
1.0149	5	4 11 1	98.75						
1.0132	5	5 4 2	98.97						
1.0101	2	1 9 3	99.39						
.9921	3	6 3 1	101.87						
.9905	5	1 15 1	102.10						
.9834	3	5 9 1	103.12						

Potassium sodium bromide, KBr-NaBr, calculated solid solution series

Structure

Cubic, Fm₃m (225), Z = 4, isostructural with NaCl. The system KBr-NaBr forms a complete solid solution series [Bellanca, 1939].

Lattice constants

The constants were derived by interpolation on a molar ratio, using the cell dimensions of KBr [Swanson and Tatge, 1953] and NaBr [Swanson et al., 1954]. For KBr, a=6.6004 Å and for NaBr, a=5.9776 Å; the original values have been modified to conform to new wavelength measurements.

Thermal parameters

Isotropic: overall B = 1.6.

Scattering factors

K⁺, Na⁺, Br⁻ [International Tables, 1962].

Random distribution of the cations was assumed, and the factors used were proportional to the molar ratio.

References

Bellanca, A. (1939). Periodico Mineral. 10, 18.

International Tables for X-ray Crystallography III (1962), 202, 204, 206.

Swanson, H. E., Fuyat, R. K., and Ugrinic, G. M. (1954). Natl. Bur. Std. U.S. Circ. 539, 3, 47.

Swanson, H. E. and Tatge, E. (1953). Natl. Bur. Std. U.S. Circ. 539, 1, 66.

	K _{0.8} Na _{0.2} Br			K _{0.6} Na _{0.4} Br			K _{0.4} Na _{0.6} Br			K _{0.2} Na _{0.8} Br		
hkl	d (Å)	I	2θ (°) λ=1.540598									
111	3.74	29	23.78	3.67	34	24.26	3.60	43	24.74	3.52	54	25.26
200	3.238	100	27.52	3.175	100	28.08	3.112	100	28.66	3.052	100	29.24
220	2.290	63	39.32	2.246	60	40.12	2.202	63	40.96	2.157	62	41.84
311	1.952	10	46.48	1.915	12	47.44	1.878	14	48.44	1.840	17	49.50
222	1.870	18	48.66	1.834	17	49.68	1.797	17	50.76	1.762	18	51.86
400	1.619	7	56.82	1.588	7	58.04	1.557	7	59.32	1.525	7	60.66
331	1.486	3	62.46	1.457	4	63.82	1.429	4	65.26	1.400	5	66.76
420	1.448	17	64.28	1.420	16	65.70	1.392	16	67.18	1.364	16	68.74
422	1.322	10	71.28	1.296	10	72.90	1.271	10	74.60	1.246	10	76.40
511 +	1.246	2	76.36	1.222	2	78.14	1.198	3	80.00	1.174	3	81.98
440	1.1448	3	84.58	1.1228	2	86.64	1.1008	2	88.82	1.0787	2	91.14
531	1.0945	2	89.46	1.0736	2	91.70	1.0526	2	94.08	1.0315	2	96.62
442 +	1.0792	5	91.08	1.0586	5	93.38	1.0378	5	95.84	1.0170	5	98.48
620	1.0239	3	97.58	1.0042	3	100.18	0.9845	3	102.96	0.9649	3	105.94
533	0.9876	--	102.52	0.9686	--	105.36	.9496	1	108.42	.9306	1	111.74
622	.9763	2	104.18	.9575	2	107.12	.9388	3	110.28	.9199	3	113.72
444	.9347	1	111.00	.9167	1	114.34	.8988	1	117.98	.8808	1	121.98
711 +	.9068	1	116.30	.8894	1	120.02	.8719	1	124.12	.8545	1	128.70
640	.8980	2	118.14	.8807	2	122.00	.8635	2	126.28	.8462	2	131.08
642	.8654	4	125.78	.8488	4	130.34	.8321	4	135.56	.8154	4	141.70
731 +	.8431	1	132.04	.8269	1	137.36	.8106	2	143.70	.7944	2	151.68
820 +	.7853	3	157.56									
Lattice constant	6.4758 Å			6.3513 Å			6.2267 Å			6.1022 Å		
Density (calc.)	2.832 g/cm ³			2.918 g/cm ³			3.008 g/cm ³			3.102 g/cm ³		

Potassium sodium chloride, KCl-NaCl, calculated solid solution series

Structure

Cubic, Fm3m (225), Z = 4. The system KCl-NaCl forms a solid solution series, complete only between 480° and 650 °C [Scheil and Stadelmaier, 1952].

Lattice constants

The constants were derived by interpolation on a molar ratio, using the cell dimensions of KCl [Swanson and Tatge, 1953] and NaCl [Swanson and Fuyat, 1953]. The original values were modified to a = 6.2935 Å (KCl) and a = 5.6406 Å (NaCl), to conform to new wavelength measurements.

Thermal parameters

Isotropic: potassium B = 1.6; sodium B = 1.9; chlorine B = 1.6.

Scattering factors

K^+ , Na^+ , Cl^- [International Tables, 1962]. The factors used were proportional to the molar ratio, assuming random distribution of the cations.

References

International Tables for X-ray Crystallography III (1962), 202, 204.

Scheil, E. and Stadelmaier, Z. (1952). Z. Metallk. 43, 227.

Swanson, H. E. and Fuyat, R. K. (1953). Natl. Bur. Std. U. S. Circ. 539, II, 41.

Swanson, H. E. and Tatge, E. (1953). Natl. Bur. Std. U. S. Circ. 539, I, 65.

	K _{.8} Na _{.2} Cl			K _{.6} Na _{.4} Cl			K _{.4} Na _{.6} Cl			K _{.2} Na _{.8} Cl		
hkl	d (Å)	I	2θ (°) λ=1.540598									
111	3.56	--	25.00	3.48	--	25.56	3.41	2	26.14	3.33	6	26.74
200	3.081	100	28.96	3.016	100	29.60	2.951	100	30.26	2.886	100	30.96
220	2.179	53	41.40	2.133	53	42.34	2.087	50	43.32	2.040	52	44.36
222	1.779	14	51.32	1.742	14	52.50	1.704	14	53.76	1.666	14	55.08
400	1.541	5	60.00	1.508	5	61.44	1.476	5	62.94	1.443	5	64.54
420	1.378	12	67.96	1.349	11	69.66	1.320	11	71.42	1.290	11	73.30
422	1.258	7	75.52	1.232	7	77.44	1.205	7	79.50	1.178	6	81.68
440	1.0894	2	90.00	1.0664	2	92.50	1.0433	2	95.18	1.0202	2	98.06
442 +	1.0271	4	97.18	1.0054	3	100.02	0.9836	3	103.10	0.9619	3	106.42
620	0.9745	2	104.46	0.9538	2	107.72	.9331	2	111.28	.9125	2	115.16
622	.9290	2	112.02	.9094	2	115.78	.8897	2	119.94	.8700	2	124.60
640	.8546	2	128.66	.8365	2	134.10	.8184	2	140.50	.8003	2	148.52
642	.8236	3	138.56	.8061	3	145.72	.7887	4	155.22			
Lattice constant	6.1629 Å			6.0323 Å			5.9018 Å			5.7712 Å		
Density (calc.)	2.024 g/cm³			2.061 g/cm³			2.097 g/cm³			2.131 g/cm³		

Thorium cobalt, $\text{Th}_2\text{Co}_{17}$

Structure

Hexagonal, $\bar{R}\bar{3}m$ (166), $Z = 3$ isostructural with $\text{Th}_2\text{Zn}_{17}$. The structure was determined by Johnson, Smith and Wood [1969].

Lattice constants: [ibid.]

$$\begin{aligned} a &= 8.438(5)\text{\AA} \\ c &= 12.254(8) \end{aligned}$$

Density

(calculated) 9.664 g/cm^3

Thermal parameters

Isotropic [Johnson et al., 1969].

Scattering factors

Th^0 , Co^0 [International Tables, 1962], corrected for anomalous dispersion [Dauben and Templeton, 1955].

Scale factor

(integrated intensities) 56.46×10^4

References

- Dauben, C. H. and Templeton, D. H. (1955). Acta Cryst. 8, 241.
 International Tables for X-ray Crystallography III (1962), 202, 212.
 Johnson, Q., Smith, G. S., and Wood, D.H. (1969). Acta Cryst. B25, 464.

d (Å)	I	hkl			$2\theta (\circ)$	$\lambda = 1.540598\text{\AA}$
		1	0	2		
1.751	1	0	4	2	52.20	
1.703	6	1	0	7	53.80	
1.690	5	1	3	4	54.22	
1.661	5	3	2	1	55.26	
1.617	6	2	3	2	56.90	
1.594	6	4	1	0	57.78	
1.579	4	0	2	7	58.40	
1.569	2	4	0	4	58.80	
1.565	9	0	3	6 +	58.98	
1.485	22	1	4	3 +	62.48	
1.478	12	2	1	7	62.80	
1.470	12	3	2	4	63.18	
1.467	21	2	2	6	63.34	
1.451	2	0	5	1	64.12	
1.422	1	5	0	2	65.62	
1.406	4	3	3	0	66.42	
1.384	2	2	3	5	67.66	
1.372	1	2	4	1	68.30	
1.362	1	0	0	9	68.90	
1.330	12	3	3	3	70.80	
1.325	5	1	3	7	71.10	
1.319	3	0	5	4	71.46	
1.305	2	5	1	1	72.36	
1.296	4	1	1	9	72.96	
1.283	2	1	5	2	73.78	
1.259	6	2	4	4	75.44	
1.256	4	5	0	5 +	75.68	
1.218	10	6	0	0	78.46	
1.211	6	3	2	7	79.02	
1.208	4	1	0	10	79.26	
1.206	5	5	1	4	79.36	
1.203	5	4	2	5	79.62	
1.189	10	3	0	9 +	80.80	
1.174	2	0	4	8	82.04	
1.170	2	5	2	0	82.34	
1.162	2	0	2	10	83.06	
1.158	2	3	3	6	83.36	
1.157	2	1	5	5	83.48	
1.131	1	2	3	8	85.88	
1.125	6	5	2	3 +	86.44	
1.122	5	0	5	7	86.72	
1.120	2	2	1	10	86.90	
1.084	1	2	4	7	90.54	
1.055	6	4	4	0	93.82	
1.050	4	5	1	7	94.36	
1.047	4	1	6	4	94.70	
1.046	7	6	0	6 +	94.84	
1.040	1	3	5	1	95.56	
1.035	6	1	4	9 +	96.14	
1.033	3	1	2	11	96.44	

Calculated Pattern (Peak heights)						
d (Å)	I	hkl	20 (°)	λ = 1.540598Å		
6.28	9	1 0 1	14.10			
4.697	6	0 1 2	18.88			
4.219	30	1 1 0	21.04			
4.085	11	0 0 3	21.74			
3.501	18	0 2 1	25.42			
3.138	8	2 0 2	28.42			
2.934	80	1 1 3	30.44			
2.826	18	1 0 4	31.64			
2.695	18	2 1 1	33.22			
2.518	10	1 2 2	35.62			
2.435	50	3 0 0	36.88			
2.347	36	0 2 4	38.32			
2.324	1	0 1 5	38.72			
2.109	68	2 2 0	42.84			
2.093	100	3 0 3 +	43.20			
2.051	25	2 1 4	44.12			
2.042	32	0 0 6	44.32			
2.036	24	2 0 5	44.46			
1.874	4	2 2 3	48.54			
1.833	5	1 2 5	49.70			

Thorium cobalt, $\text{Th}_2\text{Co}_{17}$ - continued

d (Å)	I	hkl			20 (°)
					$\lambda = 1.540598\text{\AA}$
1.021	2	0	0	12	97.94
1.010	1	6	2	1	99.42
.990	1	4	3	7	102.12
.989	2	3	2	10	102.28
.988	2	3	5	4	102.44
.978	4	3	3	9	103.90
.976	3	3	1	11	104.24
.968	2	7	1	0	105.46
.962	3	6	2	4	106.38
.960	2	5	3	5	106.76
.942	8	1	7	3 +	109.74
.939	5	1	6	7 +	110.16
.937	6	4	4	6 +	110.56
.935	4	1	0	13	110.98
.933	1	5	4	1	111.32
.925	1	4	5	2	112.78
.921	1	6	3	0	113.58
.919	3	2	2	12	113.88
.917	3	2	4	10	114.36
.898	4	3	6	3 +	118.12
.897	3	3	5	7	118.44
.896	4	5	1	10	118.62
.895	3	5	4	4	118.82
.892	3	2	1	13	119.42
.890	2	2	7	1	119.90
.887	4	5	2	9 +	120.46
.877	2	6	2	7	122.88
.875	2	7	1	6 +	123.44
.860	1	4	1	12 +	127.20
.855	2	1	3	13	128.64
.857	1	2	7	4	127.98
.853	1	8	1	1	129.06
.851	1	2	0	14	129.64
.839	1	7	2	5	133.34
.826	3	5	5	3 +	137.56
.825	3	5	4	7	137.98
.824	3	1	6	10	138.30
.824	3	8	1	4	138.48
.822	4	3	2	13	139.26
.817	2	3	4	11	141.12
.808	1	4	6	4	144.64
.808	1	1	8	5	145.06

Calculated Pattern (Integrated)					
d (Å)	I	hkl	20 (°)		
$\lambda = 1.540598\text{\AA}$					
6.28	9	1	0	1	14.10
4.695	7	0	1	2	18.89
4.219	33	1	1	0	21.04
4.085	12	0	0	3	21.74
3.501	21	0	2	1	25.42
3.138	9	2	0	2	28.42
2.935	100	1	1	3	30.44
2.825	23	1	0	4	31.64
2.694	23	2	1	1	33.22
2.518	14	1	2	2	35.63
2.436	69	3	0	0	36.87
2.348	50	0	2	4	38.31
2.324	1	0	1	5	38.72
2.109	95	2	2	0	42.83
2.092	74	3	0	3	43.21
2.002	72	0	3	3	43.21
2.051	34	2	1	4	44.11
2.042	40	0	0	6	44.32
2.035	19	2	0	5	44.48
1.874	6	2	2	3	48.53
1.833	7	1	2	5	49.69
1.807	1	4	0	1	50.47
1.751	2	0	4	2	52.21
1.702	9	1	0	7	53.81
1.690	7	1	3	4	54.22
1.661	7	3	2	1	55.26
1.617	9	2	3	2	56.90
1.595	11	4	1	0	57.77
1.579	6	0	2	7	58.41
1.569	2	4	0	4	58.80
1.565	7	3	0	6	58.97
1.565	8	0	3	6	58.97
1.485	19	4	1	3	62.47
1.485	19	1	4	3	62.47
1.479	19	2	1	7	62.79
1.471	17	3	2	4	63.17
1.467	27	2	2	6	63.33
1.451	3	0	5	1	64.12
1.422	1	5	0	2	65.62
1.406	7	3	3	0	66.42
1.384	3	2	3	5	67.66
1.372	2	2	4	1	68.29
1.362	1	0	0	9	68.91
1.347	1	4	2	2	69.75
1.330	21	3	3	3	70.80
1.325	6	1	3	7	71.10
1.319	4	0	5	4	71.46
1.305	5	5	1	1	72.35
1.296	8	1	1	9	72.95
1.283	3	1	5	2	73.77

Thorium cobalt, $\text{Th}_2\text{Co}_{17}$ - continued

d (Å)	I	hkl			2θ (°)	λ = 1.540598 Å
		h	k	l	°	
1.259	11	2	4	4	75.45	
1.257	1	4	1	6	75.59	
1.257	1	1	4	6	75.59	
1.255	1	5	0	5	75.71	
1.218	20	6	0	0	78.47	
1.211	11	3	2	7	79.02	
1.209	1	1	0	10	79.19	
1.206	9	5	1	4	79.36	
1.203	5	4	2	5	79.62	
1.188	11	3	0	9	80.80	
1.188	10	0	3	9	80.80	
1.174	3	0	4	8	82.03	
1.170	3	5	2	0	82.34	
1.162	4	0	2	10	83.06	
1.158	3	3	3	6	83.37	
1.157	3	1	5	5	83.48	
1.131	1	2	3	8	85.87	
1.125	7	5	2	3	86.44	
1.125	7	2	5	3	86.44	
1.122	4	0	5	7	86.72	
1.120	3	2	1	10	86.90	
1.101	1	0	1	11	88.77	
1.084	3	2	4	7	90.54	
1.055	15	4	4	0	93.83	
1.050	9	5	1	7	94.37	
1.049	1	1	3	10	94.54	
1.047	3	1	6	4	94.71	
1.046	7	6	0	5	94.85	
1.046	7	0	6	6	94.85	
1.040	1	3	5	1	95.56	
1.035	6	4	1	9	96.13	
1.035	7	1	4	9	96.13	
1.033	1	1	2	11	96.42	
1.029	1	5	3	2	96.92	
1.021	4	0	0	12	97.93	
1.010	2	6	2	1	99.41	
1.000	1	2	6	2	100.79	
.997	1	1	5	8	101.23	
.991	1	4	3	7	102.09	
.989	3	3	2	10	102.27	
.988	4	3	5	4	102.44	
.978	10	3	3	9	103.90	
.976	3	3	1	11	104.19	
.968	5	7	1	0	105.47	
.962	8	6	2	4	106.38	
.960	1	5	3	5	106.65	
.942	8	7	1	3	109.75	
.942	9	1	7	3	109.75	
.942	3	0	3	12	109.76	
.942	3	3	0	12	109.76	

d (Å)	I	hkl			2θ (°)	λ = 1.540598 Å
		h	k	l	°	
.940	3	1	6	7	110.05	
.939	1	0	5	10	110.24	
.937	15	4	4	6	110.56	
.936	4	2	6	5	110.68	
.935	2	1	0	13	110.97	
.933	1	5	4	1	111.32	
.925	2	4	5	2	112.78	
.921	3	6	3	0	113.58	
.919	7	2	2	12	113.87	
.917	6	2	4	10	114.37	
.913	2	0	2	13	115.12	
.898	6	6	3	3	118.11	
.898	6	3	6	3	118.11	
.897	6	3	5	7	118.44	
.896	4	5	1	10	118.63	
.895	6	5	4	4	118.82	
.892	6	2	1	13	119.42	
.890	2	2	7	1	119.79	
.887	5	2	5	9	120.45	
.887	6	5	2	9	120.45	
.883	1	7	2	2	121.37	
.877	5	6	2	7	122.88	
.875	2	0	8	4	123.28	
.875	2	1	7	6	123.45	
.875	2	7	1	6	123.45	
.874	1	4	5	5	123.59	
.860	2	4	1	12	127.21	
.860	2	1	4	12	127.21	
.857	4	2	7	4	127.98	
.856	1	8	0	5	128.31	
.855	4	1	3	13	128.65	
.853	3	8	1	1	129.07	
.851	2	2	0	14	129.63	
.847	2	1	8	2	130.84	
.844	1	5	5	0	131.82	
.829	1	6	3	6	133.20	
.839	2	7	2	5	133.36	
.834	1	4	4	9	134.98	
.826	6	5	5	3	137.55	
.826	5	3	3	12	137.57	
.825	9	5	4	7	137.98	
.824	2	1	6	10	138.24	
.824	7	8	1	4	138.48	
.822	11	3	2	13	139.28	
.817	6	3	4	11	141.13	
.812	2	9	0	0	143.14	
.810	1	0	8	7	144.05	
.809	5	4	6	4	144.63	
.808	3	1	8	5	145.07	
.802	1	1	1	15	147.66	

Thorium iron, $\text{Th}_2\text{Fe}_{17}$

Structure

Hexagonal, $\bar{R}\bar{3}m$ (166), $Z = 3$, isostructural with $\text{Th}_2\text{Zn}_{17}$. The structure was determined by Johnson, Smith and Wood [1969].

Lattice constants: [ibid.]

$$a = 8.565(2) \text{\AA}$$

$$c = 12.469(3)$$

Density
(calculated) 8.888 g/cm^3

Thermal parameters

Isotropic [Johnson et. al., 1969]

Scattering factors

Th^0 , Fe^0 [International Tables, 1962], corrected for anomalous dispersion [Dauben and Templeton, 1955].

Scale factor

(integrated intensities) 58.61×10^4

References

Dauben, C. H. and Templeton, D. H. (1955). Acta Cryst. 8, 241.

International Tables for X-ray Crystallography III (1962), 202, 212.

Johnson, Q., Smith, G. S., and Wood, D.H. (1969). Acta Cryst. B25, 464.

$d(\text{\AA})$	I	hkl			$2\theta (\text{^\circ})$	$\lambda = 1.540598\text{\AA}$
		0	4	2		
1.778	1	0	4	2	51.36	
1.732	5	1	0	7	52.80	
1.717	4	1	3	4	53.30	
1.686	4	3	2	1	54.38	
1.6419	5	2	3	2	55.96	
1.6185	6	4	1	0	56.84	
1.6056	4	0	2	7	57.34	
1.5909	9	0	3	6 +	57.92	
1.5083	22	1	4	3 +	61.42	
1.5039	17	2	1	7	61.62	
1.4935	13	3	2	4	62.10	
1.4913	19	2	2	6	62.20	
1.4730	1	0	5	1	63.06	
1.4431	1	5	0	2	64.52	
1.4274	4	3	3	0	65.32	
1.4057	2	2	3	5	66.46	
1.3931	1	2	4	1	67.14	
1.3501	12	3	3	3	69.58	
1.3467	9	1	3	7	69.78	
1.3396	2	0	5	4	70.20	
1.3246	2	5	1	1	71.12	
1.3181	4	1	1	9	71.52	
1.3027	2	1	5	2	72.50	
1.2785	5	2	4	4	74.10	
1.2752	3	5	0	5	74.32	
1.2363	10	6	0	0	77.08	
1.2304	6	3	2	7 +	77.52	
1.2251	5	5	1	4	77.92	
1.2219	4	4	2	5	78.16	
1.2087	11	3	0	9 +	79.18	
1.1932	1	0	4	8	80.42	
1.1878	2	5	2	0	80.86	
1.1820	2	0	2	10	81.34	
1.1767	2	3	3	6	81.78	
1.1751	2	1	5	5	81.92	
1.1419	6	5	2	3 +	84.84	
1.1393	5	0	5	7 +	85.08	
1.1015	1	2	4	7	88.74	
1.0707	6	4	4	0	92.02	
1.0669	4	5	1	7	92.44	
1.0625	7	6	0	6 +	92.94	
1.0558	1	3	5	1	93.70	
1.0526	5	1	4	9 +	94.08	
1.0392	2	0	0	12	95.68	
1.0252	1	6	2	1	97.42	
1.0059	2	3	2	10 +	99.96	
1.0034	2	3	5	4	100.30	
0.9943	4	3	3	9	101.56	
0.9929	1	3	1	11	101.76	
0.9825	2	7	1	0	103.26	

Calculated Pattern (Peak heights)					
$d(\text{\AA})$	I	hkl			$2\theta (\text{^\circ})$
		0	4	2	
6.375	8	1	0	1	13.88
4.772	5	0	1	2	18.58
4.283	27	1	1	0	20.72
4.157	10	0	0	3	21.36
3.553	17	0	2	1	25.04
3.186	9	2	0	2	27.98
2.982	76	1	1	3	29.94
2.873	18	1	0	4	31.10
2.735	16	2	1	1	32.72
2.557	10	1	2	2	35.06
2.473	50	3	0	0	36.30
2.387	33	0	2	4	37.66
2.364	2	0	1	5	38.04
2.142	63	2	2	0	42.16
2.125	100	3	0	3 +	42.50
2.084	26	2	1	4	43.38
2.079	40	0	0	6	43.50
2.070	15	2	0	5	43.70
1.904	4	2	2	3	47.74
1.863	5	1	2	5	48.84

Thorium iron, $\text{Th}_2\text{Fe}_{17}$ - continued

d (Å)	I	hkl			$2\theta (\circ)$ λ = 1.540598 Å	Calculated Pattern (Integrated)					
		h	k	l		d (Å)	I	hkl			$2\theta (\circ)$ λ = 1.540598 Å
.9769	3	6	2	4	104.10	6.375	9	1	0	1	13.88
.9745	1	5	3	5	104.46	4.773	6	0	1	2	18.58
.9580	2	0	3	12	+ 107.04	4.283	32	1	1	0	20.72
.9562	6	1	7	3	+ 107.34	4.157	11	0	0	3	21.36
.9549	3	1	6	7	+ 107.54	3.555	22	0	2	1	25.03
.9518	6	4	4	6	+ 108.06	3.187	12	2	0	2	27.97
.9470	1	5	4	1	108.86	2.983	100	1	1	3	29.93
.9389	1	4	5	2	110.26	2.874	24	1	0	4	31.09
.9348	3	2	2	12	+ 110.98	2.735	22	2	1	1	32.71
.9318	2	2	4	10	111.52	2.557	14	1	2	2	35.07
.9293	1	0	2	13	111.98	2.473	70	3	0	0	36.30
.9117	4	3	6	3	+ 115.32	2.386	46	0	2	4	37.66
.9106	3	3	5	7	+ 115.54	2.364	2	0	1	5	38.03
.9084	3	5	4	4	115.98	2.141	94	2	2	0	42.17
.9076	3	2	1	13	116.14	2.125	75	3	0	3	42.51
.9038	1	2	7	1	116.92	2.125	74	0	3	3	42.51
.9018	3	5	2	9	+ *****	2.085	35	2	1	4	43.37
.8908	1	6	2	7	119.70	2.078	43	0	0	6	43.51
.8885	2	0	8	4	+ 120.22	2.070	16	2	0	5	43.70
.8744	1	4	1	12	+ 123.50	1.904	7	2	2	3	47.74
.8702	1	2	7	4	124.56	1.863	8	1	2	5	48.84
.8694	1	1	3	13	124.76	1.834	1	4	0	1	49.66
.8661	1	8	1	1	125.60	1.777	1	0	4	2	51.36
.8402	1	3	3	12	132.94	1.732	8	1	0	7	52.81
.8388	2	5	5	3	133.36	1.717	7	1	3	4	53.31
.8381	3	5	4	7	+ 133.60	1.686	8	3	2	1	54.37
.8363	3	8	1	4	134.18	1.6416	8	2	3	2	55.97
.8356	3	3	2	13	134.38	1.6186	10	4	1	0	56.84
.8303	1	3	4	11	136.18	1.6058	7	0	2	7	57.33
.8208	1	4	6	4	139.58	1.5937	2	4	0	4	57.81
.8199	1	1	8	5	139.94	1.5909	7	3	0	6	57.92
.8093	6	8	2	0	144.28	1.5909	7	0	3	6	57.92
.8084	3	9	0	3	+ 144.66	1.5083	18	4	1	3	61.42
.8074	4	2	7	7	+ 145.14	1.5083	19	1	4	3	61.42
						1.5036	17	2	1	7	61.64
						1.4937	17	3	2	4	62.09
						1.4914	28	2	2	6	62.20
						1.4731	2	0	5	1	63.05
						1.4432	1	5	0	2	64.52
						1.4275	7	3	3	0	65.31
						1.4057	4	2	3	5	66.46
						1.3930	2	2	4	1	67.14
						1.3856	1	0	0	9	67.55
						1.3676	1	4	2	2	68.56
						1.3501	22	3	3	3	69.58
						1.3467	5	1	3	7	69.78
						1.3396	4	0	5	4	70.20
						1.3247	4	5	1	1	71.11
						1.3183	9	1	1	9	71.51
						1.3028	3	1	5	2	72.49

Thorium iron, Th₂Fe₁₇ - continued

d (Å)	I	hkl	20 (°) λ = 1.540598 Å		d (Å)	I	hkl	20 (°) λ = 1.540598 Å
1.2785	10	2 4 4	74.10		.9513	2	1 0 13	108.14
1.2750	2	5 0 5	74.34		.9509	3	2 6 5	108.20
1.2363	20	6 0 0	77.08		.9470	1	5 4 1	108.87
1.2305	11	3 2 7	77.51		.9389	2	4 5 2	110.26
1.2297	1	1 0 10	77.57		.9349	8	2 2 12	110.96
1.2251	8	5 1 4	77.92		.9345	3	6 3 0	111.03
1.2220	4	4 2 5	78.15		.9317	5	2 4 10	111.54
1.2087	11	3 0 9	79.18		.9287	1	0 2 13	112.09
1.2087	11	0 3 9	79.18		.9118	5	6 3 3	115.31
1.1932	2	0 4 8	80.42		.9118	5	3 6 3	115.31
1.1878	3	5 2 0	80.86		.9107	5	3 5 7	115.52
1.1820	4	0 2 10	81.34		.9104	3	5 1 10	115.58
1.1767	3	3 3 6	81.78		.9085	5	5 4 4	115.97
1.1751	3	1 5 5	81.92		.9076	6	2 1 13	116.15
1.1494	1	2 3 8	84.16		.9038	2	2 7 1	116.92
1.1420	7	5 2 3	84.83		.9018	5	5 2 9	117.35
1.1420	6	2 5 3	84.83		.9018	5	2 5 9	117.35
1.1400	4	0 5 7	85.02		.8968	1	7 2 2	118.40
1.1394	3	2 1 10	85.07		.8908	4	6 2 7	119.71
1.1206	1	0 1 11	86.85		.8887	2	0 8 4	120.17
1.1016	3	2 4 7	88.73		.8882	1	1 7 6	120.28
1.0706	14	4 4 0	92.02		.8882	1	7 1 6	120.28
1.0669	8	5 1 7	92.44		.8875	1	4 5 5	120.43
1.0633	2	1 6 4	92.84		.8745	1	4 1 12	123.50
1.0625	8	6 0 6	92.94		.8745	1	1 4 12	123.50
1.0625	8	0 6 6	92.94		.8702	4	2 7 4	124.56
1.0558	1	3 5 1	93.70		.8694	5	1 3 13	124.76
1.0526	6	1 4 9	94.08		.8661	2	8 1 1	125.60
1.0526	6	4 1 9	94.08		.8599	2	1 8 2	127.23
1.0447	1	5 3 2	95.01		.8565	1	5 5 0	128.15
1.0392	4	0 0 12	95.68		.8517	2	7 2 5	129.49
1.0251	2	6 2 1	97.42		.8472	1	4 4 9	130.80
1.0149	1	2 6 2	98.75		.8401	4	3 3 12	132.95
1.0127	1	1 5 8	99.04		.8389	5	5 5 3	133.34
1.0063	1	4 3 7	99.90		.8381	7	5 4 7	133.60
1.0058	3	3 2 10	99.96		.8378	1	1 6 10	133.68
1.0033	4	3 5 4	100.31		.8363	6	8 1 4	134.16
.9942	9	3 3 9	101.57		.8356	9	3 2 13	134.39
.9929	2	3 1 11	101.76		.8303	4	3 4 11	136.18
.9825	4	7 1 0	103.26		.8242	1	9 0 0	138.34
.9768	7	6 2 4	104.11		.8225	1	0 8 7	138.97
.9753	1	5 3 5	104.34		.8208	3	4 6 4	139.58
.9604	1	3 4 8	106.65		.8199	3	1 8 5	139.94
.9580	3	0 3 12	107.04		.8161	1	1 1 15	141.43
.9580	2	3 0 12	107.04		.8110	1	4 5 8	143.53
.9561	7	7 1 3	107.35		.8093	25	8 2 0	144.27
.9561	8	1 7 3	107.35		.8084	4	9 0 3	144.66
.9549	3	1 6 7	107.54		.8084	4	0 9 3	144.66
.9546	1	0 5 10	107.60		.8077	9	2 7 7	144.99
.9518	14	4 4 6	108.06		.8075	4	3 5 10	145.09

CUMULATIVE INORGANIC INDEX

	Vol. or Sec.	Page		Vol. or Sec.	Page
Aluminum, Al	1	11	Ammonium copper bromide hydrate, $(\text{NH}_4)_2\text{CuBr}_4 \cdot 2\text{H}_2\text{O}$	10m	6
Aluminum antimony, AlSb	4	72	Ammonium copper chloride, NH_4CuCl_3 ..	7m	7
Aluminum bismuth oxide, $\text{Al}_4\text{Bi}_2\text{O}_9$..	11m	5	Ammonium copper chloride hydrate, $(\text{NH}_4)_2\text{CuCl}_4 \cdot 2\text{H}_2\text{O}$	12m	6
Aluminum chloride, AlCl_3	9m	61	Ammonium copper fluoride, NH_4CuF_3 ..	11m	8
Aluminum chloride hydrate (chloraluminite), $\text{AlCl}_3 \cdot 6\text{H}_2\text{O}$	7	3	Ammonium gallium sulfate hydrate, $\text{NH}_4\text{Ga}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	6	9
Aluminum fluorine hydroxide silicate, topaz, $\text{Al}_2(\text{F},\text{OH})_2\text{SiO}_4$	1m	4	Ammonium germanium fluoride, $(\text{NH}_4)_2\text{GeF}_6$	6	8
Aluminum nitride, AlN	12m	5	Ammonium hydrogen carbonate (teschemacherite), $(\text{NH}_4)\text{HCO}_3$	9	5
Aluminum nitrate hydrate, $\text{Al}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$	1m	6	Ammonium hydrogen phosphate, $\text{NH}_4\text{H}_2\text{PO}_4$	4	64
Aluminum oxide (corundum), $\alpha\text{-Al}_2\text{O}_3$..	9	3	Ammonium iodate, NH_4IO_3	10m	7
Aluminum oxide hydrate (böhmite), $\alpha\text{-Al}_2\text{O}_3 \cdot \text{H}_2\text{O}$	3	38	Ammonium iodide, NH_4I	4	56
Aluminum oxide hydrate, diaspore, $\beta\text{-Al}_2\text{O}_3 \cdot \text{H}_2\text{O}$	3	41	Ammonium iridium chloride, $(\text{NH}_4)_2\text{IrCl}_6$	8	6
Aluminum phosphate, $\text{Al}(\text{PO}_3)_3$	2m	3	Ammonium iron fluoride, $(\text{NH}_4)_3\text{FeF}_6$	9m	9
Aluminum phosphate (berlinite), AlPO_4 (trigonal)	10	3	Ammonium iron sulfate, $\text{NH}_4\text{Fe}(\text{SO}_4)_2$	10m	8
Aluminum phosphate, AlPO_4 (orthorhombic)	10	4	Ammonium iron sulfate hydrate, $\text{NH}_4\text{Fe}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	6	10
Aluminum silicate (mullite), $\text{Al}_6\text{Si}_2\text{O}_1_3$	3m	3	Ammonium lead chloride, $(\text{NH}_4)_2\text{PbCl}_6$	11m	10
Aluminum tungsten oxide, $\text{Al}_2(\text{WO}_4)_3$..	11m	7	Ammonium magnesium aluminum fluoride, $\text{NH}_4\text{MgAlF}_6$	10m	9
Ammonium aluminum fluoride, $(\text{NH}_4)_3\text{AlF}_6$	9m	5	Ammonium magnesium chromium oxide hydrate, $(\text{NH}_4)_2\text{Mg}(\text{CrO}_4)_2 \cdot 6\text{H}_2\text{O}$	8m	10
Ammonium aluminum selenate hydrate, $\text{NH}_4\text{Al}(\text{SeO}_4)_2 \cdot 12\text{H}_2\text{O}$	9m	6	Ammonium manganese chloride hydrate, $(\text{NH}_4)_2\text{MnCl}_4 \cdot 2\text{H}_2\text{O}$	11m	11
Ammonium aluminum sulfate, $\text{NH}_4\text{Al}(\text{SO}_4)_2$	10m	5	Ammonium manganese(II) fluoride, NH_4MnF_3	5m	8
Ammonium aluminum sulfate hydrate (tschermigite), $\text{NH}_4\text{Al}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$..	6	3	Ammonium manganese sulfate, $(\text{NH}_4)_2\text{Mn}_2(\text{SO}_4)_3$	7m	8
Ammonium azide, NH_4N_3	9	4	Ammonium manganese sulfate hydrate, $(\text{NH}_4)_2\text{Mn}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	8m	12
Ammonium beryllium fluoride, $(\text{NH}_4)_2\text{BeF}_4$	3m	5	Ammonium mercury chloride, NH_4HgCl_3	8m	14
Ammonium boron fluoride, NH_4BF_4 ...	3m	6	Ammonium molybdenum oxide phosphate hydrate, $(\text{NH}_4)_3(\text{MoO}_3)_12\text{PO}_4 \cdot 4\text{H}_2\text{O}$...	8	10
Ammonium bromide, NH_4Br	2	49	Ammonium nickel(II) chloride, NH_4NiCl_3	6m	6
Ammonium cadmium chloride, NH_4CdCl_3 ..	5m	6	Ammonium nickel chromium oxide hydrate, $(\text{NH}_4)_2\text{Ni}(\text{CrO}_4)_2 \cdot 6\text{H}_2\text{O}$	8m	16
Ammonium cadmium sulfate, $(\text{NH}_4)_2\text{Cd}_2(\text{SO}_4)_3$	7m	5	Ammonium nitrate (ammonia-niter), NH_4NO_3	7	4
Ammonium cadmium sulfate hydrate, $(\text{NH}_4)_2\text{Cd}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	8m	5	Ammonium osmium bromide, $(\text{NH}_4)_2\text{OsBr}_6$	3	71
Ammonium calcium sulfate, $(\text{NH}_4)_2\text{Ca}_2(\text{SO}_4)_3$	8m	7	Ammonium osmium chloride, $(\text{NH}_4)_2\text{OsCl}_6$	1m	6
Ammonium chlorate, NH_4ClO_4 (orthorhombic)	7	6	Ammonium palladium chloride, $(\text{NH}_4)_2\text{PdCl}_4$	6	6
Ammonium chloride (sal-ammoniac), NH_4Cl	1	59	Ammonium palladium chloride, $(\text{NH}_4)_2\text{PdCl}_6$	8	7
Ammonium chromium sulfate hydrate, $\text{NH}_4\text{Cr}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	6	7	Ammonium platinum bromide, $(\text{NH}_4)_2\text{PtBr}_6$	9	6
Ammonium cobalt (II) chloride, NH_4CoCl_3	6m	5	Ammonium platinum chloride, $(\text{NH}_4)_2\text{PtCl}_6$	5	3
Ammonium cobalt fluoride, NH_4CoF_3 ..	8m	9	Ammonium rhenium oxide, NH_4ReO_4	9	7

Further work on this program is in progress, and it is anticipated that additional sections will be issued. Therefore, the accumulative index here is not necessarily the concluding index for the project.

m - Monograph 25.

A mineral name in () indicates a synthetic sample.

CUMULATIVE INORGANIC INDEX - Continued

	Vol. or Sec.	Page	Vol. or Sec.	Page	
Ammonium tellurium chloride,			Barium lead nitrate,		
$(\text{NH}_4)_2\text{TeCl}_6$	8	8	$\text{Ba}_{.33}\text{Pb}_{.67}(\text{NO}_3)_2$	12m	40
Ammonium tin chloride, $(\text{NH}_4)_2\text{SnCl}_6$	5	4	Barium lead nitrate,		
Ammonium vanadium oxide, NH_4VO_3	8	9	$\text{Ba}_{.67}\text{Pb}_{.33}(\text{NO}_3)_2$	12m	40
Ammonium zinc fluoride, NH_4ZnF_3	8m	18	Barium molybdenum oxide, BaMoO_4	7	7
Ammonium zirconium fluoride,			Barium molybdenum oxide, Ba_2MoO_5	12m	10
$(\text{NH}_4)_3\text{ZrF}_7$	6	14	Barium nitrate (nitrobarite),		
Antimony, Sb	3	14	$\text{Ba}(\text{NO}_3)_2$	11m	14
Antimony(III) fluoride, SbF_3	2m	4	Barium oxide, BaO	9m	63
Antimony(III) iodide, SbI_3	6	16	Barium oxide, BaO_2	6	18
Antimony(III) oxide (senarmontite),			Barium phosphate, $\text{Ba}_3(\text{PO}_4)_2$	12m	12
Sb_2O_3 (cubic)	3	31	Barium selenide, BaSe	5m	61
Antimony(III) oxide, valentinite,			Barium silicon fluoride, BaSiF_6	4m	7
Sb_2O_3 (orthorhombic)	10	6	Barium strontium nitrate,		
Antimony(IV) oxide (cervantite),			$\text{Ba}_{.25}\text{Sr}_{.75}(\text{NO}_3)_2$	12m	42
Sb_2O_4	10	8	Barium strontium nitrate,		
Antimony(V) oxide, Sb_2O_5	10	10	$\text{Ba}_{.50}\text{Sr}_{.50}(\text{NO}_3)_2$	12m	42
Antimony selenide, Sb_2Se_3	3m	7	Barium strontium nitrate,		
Antimony(III) sulfide (stibnite),			$\text{Ba}_{.75}\text{Sr}_{.25}(\text{NO}_3)_2$	12m	42
Sb_2S_3	5	6	Barium sulfate (barite), BaSO_4	10m	12
Antimony telluride, Sb_2Te_3	3m	8	Barium sulfide, BaS	7	8
Arsenic, As	3	6	Barium tin oxide, BaSnO_3	3m	11
Arsenic(III) iodide, AsI_3	6	17	Barium titanium oxide, BaTiO_3	3	45
Arsenic oxide (arsenolite),			Barium titanium silicate (fresnoite),		
As_2O_3 (cubic)	1	51	$\text{Ba}_2\text{TiSi}_2\text{O}_8$	9m	14
Arsenic oxide, claudetite, As_2O_3 (monoclinic)	3m	9	Barium tungsten oxide, BaWO_4	7	9
Barium, Ba	4	7	Barium tungsten oxide, Ba_2WO_5	12m	14
Barium aluminum oxide, BaAl_2O_4	5m	11	Barium zirconium oxide, BaZrO_3	5	8
Barium aluminum oxide, $\text{Ba}_3\text{Al}_2\text{O}_6$	12m	7	Beryllium, alpha, Be	9m	64
Barium arsenate, $\text{Ba}_3(\text{AsO}_4)_2$	2m	6	Beryllium aluminum oxide (chrysoberyl), BeAl_2O_4	9	10
Barium borate, BaB_4O_7	4m	6	Beryllium aluminum silicate, beryl, $\text{Be}_3\text{Al}_2(\text{SiO}_3)_6$	9	13
Barium borate, high form, BaB_2O_4	4m	4	Beryllium calcium oxide, $\text{Be}_{17}\text{Ca}_{12}\text{O}_{29}$	7m	89
Barium borate, $\text{BaB}_8\text{O}_{13}$	7m	10	Beryllium chromium oxide, BeCr_2O_4	10	12
Barium bromate hydrate, $\text{Ba}(\text{BrO}_3)_2 \cdot \text{H}_2\text{O}$	8m	19	Beryllium cobalt, BeCo	5m	62
Barium bromide, BaBr_2	10m	63	Beryllium germanium oxide, Be_2GeO_4	10	13
Barium bromide fluoride, BaBrF	10m	10	Beryllium lanthanum oxide, $\text{Be}_2\text{La}_2\text{O}_5$	9m	65
Barium bromide hydrate, $\text{BaBr}_2 \cdot \text{H}_2\text{O}$	3m	10	Beryllium niobium, Be_2Nb	7m	92
Barium calcium nitrate, $\text{Ba}_{.25}\text{Ca}_{.75}(\text{NO}_3)_2$	12m	38	Beryllium oxide (bromellite), BeO	1	36
Barium calcium nitrate, $\text{Ba}_{.50}\text{Ca}_{.50}(\text{NO}_3)_2$	12m	38	Beryllium palladium, BePd	5m	62
Barium calcium nitrate, $\text{Ba}_{.75}\text{Ca}_{.25}(\text{NO}_3)_2$	12m	38	Beryllium silicate, phenacite, BeSi_2O_4	8	11
Barium calcium tungsten oxide, Ba_2CaW_6	9m	10	Bismuth, Bi	3	20
Barium carbonate (witherite), BaCO_3 (orthorhombic)	2	54	Bismuth fluoride, BiF_3	1m	7
Barium carbonate, BaCO_3 (cubic) at 1075 °C	10	11	Bismuth(III) iodide, BiI_3	6	20
Barium chlorate hydrate, $\text{Ba}(\text{ClO}_4)_2 \cdot 3\text{H}_2\text{O}$	2m	7	Bismuth oxide (bismite), $\alpha\text{-Bi}_2\text{O}_3$	3m	16
Barium chlorate hydrate, $\text{Ba}(\text{ClO}_4)_2 \cdot \text{H}_2\text{O}$	8m	21	Bismuth oxide bromide, BiOBr	8	14
Barium chloride, BaCl_2 , (cubic)	9m	13	Bismuth oxide chloride (bismoclite), BiOCl	4	54
Barium chloride, BaCl_2 , (orthorhombic)	9m	11	Bismuth oxide iodide, BiOI	9	16
Barium chloride fluoride, BaClF	10m	11	Bismuth phosphate, BiPO_4 (monoclinic)	3m	11
Barium chloride hydrate, $\text{BaCl}_2 \cdot 2\text{H}_2\text{O}$	12m	9	Bismuth phosphate, BiPO_4 (trigonal)	3m	13
Barium fluoride, BaF_2	1	70	Bismuth sulfide (bismuthinite), Bi_2S_3	5m	13
Barium hydroxide phosphate, $\text{Ba}_5(\text{OH})(\text{PO}_4)_3$	11m	12	Bismuth telluride, BiTe	4m	50
Barium iodide, BaI_2	10m	66	Bismuth telluride (tellurobis-muthite), Bi_2Te_3	3m	16
Barium lead chloride, BaPbCl_4	11m	13	Bismuth vanadium oxide, low form, BiVO_4 (tetragonal)	3m	14
			Bismuth vanadium oxide, high form, BiVO_4 (monoclinic)	3m	14
			Boron oxide, B_2O_3 , phase 1	10m	70
			Cadmium, Cd	3	10

CUMULATIVE INORGANIC INDEX - Continued

	Vol. or Sec.	Page		Vol. or Sec.	Page
Cadmium ammine chloride, $\text{Cd}(\text{NH}_3)_2\text{Cl}_2$	10m	14	Calcium iron silicate (andradite), $\text{Ca}_3\text{Fe}_2\text{Si}_3\text{O}_{12}$	9	22
Cadmium bromide, CdBr_2	9	17	Calcium iron silicate hydroxide, jul- goldite, $\text{Ca}_2\text{Fe}_3\text{Si}_3\text{O}_{10}(\text{OH},\text{O})_2(\text{OH})_2$	10m	72
Cadmium bromide chloride, CdBrCl ...	11m	15	Calcium lead nitrate, $\text{Ca}_{.33}\text{Pb}_{.67}(\text{NO}_3)_2$	12m	44
Cadmium carbonate (otavite), CdCO_3	7	11	Calcium lead nitrate, $\text{Ca}_{.67}\text{Pb}_{.33}(\text{NO}_3)_2$	12m	44
Cadmium chlorate hydrate, $\text{Cd}(\text{ClO}_4)_2 \cdot 6\text{H}_2\text{O}$	3m	19	Calcium magnesium silicate (diopside), $\text{CaMg}(\text{SiO}_3)_2$	5m	17
Cadmium chloride, CdCl_2	9	18	Calcium molybdenum oxide (powellite), CaMoO_4	6	22
Cadmium chromium oxide, CdCr_2O_4	5m	16	Calcium nitrate, $\text{Ca}(\text{NO}_3)_2$	7	14
Cadmium cyanide, $\text{Cd}(\text{CN})_2$	2m	8	Calcium oxide, CaO	1	43
Cadmium fluoride, CdF_2	10m	15	Calcium oxide phosphate, $\text{Ca}_4\text{O}(\text{PO}_4)_2$	12m	17
Cadmium iron oxide, CdFe_2O_4	9m	16	Calcium phosphate, $\beta\text{-Ca}_2\text{P}_2\text{O}_7$	7m	95
Cadmium manganese oxide, CdMn_2O_4 ...	10m	16	Calcium platinum oxide, Ca_4PtO_6	10m	18
Cadmium molybdenum oxide, CdMoO_4 ...	6	21	Calcium selenide, CaSe	5m	64
Cadmium nitrate hydrate, $\text{Cd}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$	7m	93	Calcium strontium nitrate, $\text{Ca}_{.33}\text{Sr}_{.67}(\text{NO}_3)_2$	12m	46
Cadmium oxide, CdO	2	27	Calcium strontium nitrate, $\text{Ca}_{.67}\text{Sr}_{.33}(\text{NO}_3)_2$	12m	46
Cadmium oxide, CdO (ref. standard)	8m	2	Calcium sulfate (anhydrite), CaSO_4	4	65
Cadmium selenide, CdSe (hexagonal)	7	12	Calcium sulfide (oldhamite), CaS	7	15
Cadmium sulfate, CdSO_4	3m	20	Calcium telluride, CaTe	4m	50
Cadmium sulfate hydrate, $3\text{CdSO}_4 \cdot 8\text{H}_2\text{O}$	6m	8	Calcium titanium oxide (perovskite), CaTiO_3	9m	17
Cadmium sulfate hydrate, $\text{CdSO}_4 \cdot \text{H}_2\text{O}$	6m	10	Calcium tungsten oxide, Ca_3WO_6	9m	19
Cadmium sulfide (greenockite), CdS	4	15	Calcium tungsten oxide, scheelite, CaWO_4	6	23
Cadmium telluride, CdTe	3m	21	Carbon, diamond, C	2	5
Cadmium tungsten oxide, CdWO_4	2m	8	Cerium antimony, CeSb	4m	40
Calcium, Ca	9m	68	Cerium arsenate, CeAsO_4	4m	8
Calcium aluminum germanium oxide, $\text{Ca}_3\text{Al}_2(\text{GeO}_4)_3$	10	15	Cerium arsenide, CeAs	4m	51
Calcium aluminum hydroxide, $\text{Ca}_3\text{Al}_2(\text{OH})_{12}$	11m	16	Cerium bismuth, CeBi	4m	46
Calcium aluminum oxide, $\text{Ca}_3\text{Al}_2\text{O}_6$...	5	10	Cerium cadmium, CeCd	5m	63
Calcium aluminum oxide, $\text{Ca}_{12}\text{Al}_14\text{O}_{33}$	9	20	Cerium(III) chloride, CeCl_3	1m	8
Calcium aluminum sulfate hydrate (ettringite), $\text{Ca}_6\text{Al}_2\text{S}_3\text{O}_{18} \cdot 3\text{H}_2\text{O}$...	8	3	Cerium copper, CeCu_6	7m	99
Calcium bromide, CaBr_2	11m	70	Cerium(III) fluoride, CeF_3	8	17
Calcium bromide hydrate, $\text{CaBr}_2 \cdot 6\text{H}_2\text{O}$	8	15	Cerium niobium titanium oxide (eschynite), CeNbTiO_6	3m	24
Calcium carbonate (aragonite), CaCO_3 (orthorhombic)	3	53	Cerium nitride, CeN	4m	51
Calcium carbonate (calcite), CaCO_3 (hexagonal)	2	51	Cerium(IV) oxide (cerianite), CeO_2	1	56
Calcium chloride (hydrophilite), CaCl_2	11m	18	Cerium phosphide, CeP	4m	52
Calcium chloride fluoride, CaClF ...	10m	17	Cerium(III) vanadium oxide, CeVO_4	1m	9
Calcium chloride hydrate, $\text{CaCl}_2 \cdot 4\text{H}_2\text{O}$	11m	73	Cerium zinc, CeZn	5m	65
Calcium chloride hydrate (antarcticite), $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$	12m	16	Cesium aluminum sulfate hydrate, $\text{CsAl}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	6	25
Calcium chromium germanium oxide, $\text{Ca}_3\text{Cr}_2(\text{GeO}_4)_3$	10	16	Cesium antimony fluoride, CsSbF_6	4m	9
Calcium chromium oxide, CaCrO_4	7	13	Cesium beryllium fluoride, CsBeF_3	9m	69
Calcium chromium silicate (uvarovite), $\text{Ca}_3\text{Cr}_2(\text{SiO}_4)_3$	10	17	Cesium boron fluoride, CsBF_4	8	22
Calcium fluoride (fluorite), CaF_2 ..	1	69	Cesium bromate, CsBrO_3	8	18
Calcium fluoride phosphate (fluorapatite), $\text{Ca}_5\text{F}(\text{PO}_4)_3$	3m	22	Cesium bromide, CsBr	3	49
Calcium gallium germanium oxide, $\text{Ca}_3\text{Ga}_2(\text{GeO}_4)_3$	10	18	Cesium cadmium bromide, CsCdBr_3 (hexagonal)	10m	20
Calcium hydroxide (portlandite), $\text{Ca}(\text{OH})_2$	1	58	Cesium calcium chloride, CsCaCl_3 (hexagonal)	5m	19
Calcium iron germanium oxide, $\text{Ca}_3\text{Fe}_2(\text{GeO}_4)_3$	10	19	Cesium calcium fluoride, CsCaF_3	5m	21
			Cesium calcium sulfate, $\text{Cs}_2\text{Ca}_2(\text{SO}_4)_3$	8m	25
			Cesium cerium chloride, Cs_2CeCl_6	7m	12
			Cesium chlorate, CsClO_4 , (orthorhombic)	7m	101
				8	20
				1m	10

CUMULATIVE INORGANIC INDEX - Continued

	Vol. or Sec.	Page		Vol. or Sec.	Page
Cesium chloride, CsCl	2	44	Chromium phosphate, β -CrPO ₄	9	26
Cesium chromium oxide, Cs ₂ CrO ₄	3m	25	Chromium rhodium 3:1, Cr ₃ Rh	6m	15
Cesium chromium sulfate hydrate, CsCr(SO ₄) ₂ ·12H ₂ O	8	21	Chromium silicide, Cr ₃ Si	6	29
Cesium cobalt(II) chloride, CsCoCl ₃	6m	11	Cobalt, Co (cubic)	4m	10
Cesium cobalt chloride, Cs ₂ CoCl ₄	11m	19	Cobalt aluminum oxide, CoAl ₂ O ₄	9	27
Cesium copper(II) chloride, CsCuCl ₃	5m	22	Cobalt ammine iodide, Co(NH ₃) ₆ I ₃	10m	83
Cesium copper chloride, Cs ₂ CuCl ₄	11m	20	Cobalt antimony oxide, CoSb ₂ O ₆	5m	26
Cesium copper sulfate hydrate, Cs ₂ Cu(SO ₄) ₂ ·6H ₂ O	7m	14	Cobalt arsenide, CoAs ₂	4m	10
Cesium fluoride, CsF	3m	26	Cobalt arsenide (skutterudite), CoAs ₃	10	21
Cesium gallium sulfate hydrate, CsGa(SO ₄) ₂ ·12H ₂ O	8	23	Cobalt borate, Co ₃ (BO ₃) ₂	12m	20
Cesium germanium fluoride, Cs ₂ GeF ₆	5	17	Cobalt bromide hydrate, CoBr ₂ ·6H ₂ O	12m	21
Cesium iodide, CsI	4	47	Cobalt(II) carbonate (sphero- cobaltite), CoCO ₃	10	24
Cesium iodine bromide, CsI ₂ Br	7m	103	Cobalt chlorate hydrate, Co(ClO ₄) ₂ ·6H ₂ O	3m	28
Cesium iodine chloride, CsICl ₂	3	50	Cobalt chloride hydrate, CoCl ₂ ·2H ₂ O	11m	22
Cesium iron sulfate hydrate, Cs ₂ Fe(SO ₄) ₂ ·6H ₂ O	7m	16	Cobalt chloride hydrate, CoCl ₂ ·6H ₂ O	11m	23
Cesium iron sulfate hydrate, CsFe(SO ₄) ₂ ·12H ₂ O	6	28	Cobalt chromium oxide, CoCr ₂ O ₄	9m	21
Cesium lead(II) chloride, CsPbCl ₃ (tetragonal)	5m	24	Cobalt fluoride, CoF ₂	10m	85
Cesium lead fluoride, CsPbF ₃	8m	26	Cobalt fluoride hydrate, CoF ₂ ·4H ₂ O	11m	24
Cesium lithium cobalt cyanide, CsLiCo(CN) ₆	10m	79	Cobalt gallium oxide, CoGa ₂ O ₄	10	27
Cesium lithium fluoride, CsLiF ₂	7m	105	Cobalt germanium oxide, Co ₂ GeO ₄	10	27
Cesium magnesium chromium oxide hydrate, Cs ₂ Mg(CrO ₄) ₂ ·6H ₂ O	8m	27	Cobalt iodide, CoI ₂	4m	52
Cesium magnesium sulfate hydrate, Cs ₂ Mg(SO ₄) ₂ ·6H ₂ O	8m	29	Cobalt iron arsenide (safflorite), CoFeAs ₄	10	28
Cesium manganese fluoride, CsMnF ₃	7m	18	Cobalt iron oxide, CoFe ₂ O ₄	9m	22
Cesium manganese sulfate hydrate, Cs ₂ Mn(SO ₄) ₂ ·6H ₂ O	10m	21	Cobalt mercury thiocyanate, Co[Hg(CNS) ₄]	2m	13
Cesium mercury chloride, CsHgCl ₃	7m	22	Cobalt nitrate hydrate, α -Co(NO ₃) ₂ ·6H ₂ O	12m	22
Cesium nickel(II) chloride, CsNiCl ₃	6m	12	Cobalt(II) oxide, CoO	9	28
Cesium nickel sulfate hydrate, Cs ₂ Ni(SO ₄) ₂ ·6H ₂ O	7m	23	Cobalt(II,III) oxide, Co ₃ O ₄	9	29
Cesium nitrate, CsNO ₃	9	25	Cobalt silicate, Co ₂ SiO ₄ (orthorhombic)	4m	11
Cesium osmium(IV) bromide, Cs ₂ OsBr ₆	2m	10	Cobalt silicon fluoride hydrate, CoSiF ₆ ·6H ₂ O	3m	27
Cesium osmium chloride, Cs ₂ OscI ₆	2m	11	Cobalt sulfate, β -CoSO ₄	2m	14
Cesium platinum bromide, Cs ₂ PtBr ₆	8	19	Cobalt titanium oxide, CoTiO ₃	4m	13
Cesium platinum chloride, Cs ₂ PtCl ₆	5	14	Cobalt tungsten oxide, CoWO ₄	4m	13
Cesium platinum fluoride, Cs ₂ PtF ₆	6	27	Copper, Cu	1	15
Cesium selenium bromide, Cs ₂ SeBr ₆	8	20	Copper aluminum, Cu ₉ Al ₄	11m	79
Cesium silicon fluoride, Cs ₂ SiF ₆	5	19	Copper ammine selenate, Cu(NH ₃) ₄ SeO ₄	10m	87
Cesium strontium chloride, CsSrCl ₃	6m	13	Copper ammine sulfate hydrate, Cu(NH ₃) ₄ SO ₄ ·H ₂ O	10m	90
Cesium sulfate, Cs ₂ SO ₄	7	17	Copper antimony oxide, CuSb ₂ O ₆	5m	27
Cesium tellurium bromide, Cs ₂ TeBr ₆	9	24	Copper(I) bromide, CuBr	4	36
Cesium tin chloride, Cs ₂ SnCl ₆	5	16	Copper cadmium, Cu ₅ Cd ₈	11m	81
Cesium vanadium sulfate hydrate, CsV(SO ₄) ₂ ·12H ₂ O	1m	11	Copper(I) chloride (nantokite), CuCl	4	35
Cesium zinc sulfate hydrate, Cs ₂ Zn(SO ₄) ₂ ·6H ₂ O	7m	25	Copper fluoride hydrate, CuF ₂ ·2H ₂ O	11m	25
Chromium, Cr	5	20	Copper hydrogen phosphite hydrate, CuHPO ₃ ·2H ₂ O	11m	83
Chromium chloride, CrCl ₂	11m	77	Copper hydroxide carbonate, azurite, Cu ₃ (OH) ₂ (CO ₃) ₂	10	30
Chromium fluoride, Cr ₂ F ₅	7m	108	Copper hydroxide carbonate (malachite), Cu ₂ (OH) ₂ CO ₃	10	31
Chromium fluoride, CrF ₂	10m	81	Copper(I) iodide (marchite), CuI	4	38
Chromium(III) fluoride hydrate, CrF ₃ ·3H ₂ O	5m	25	Copper(I) oxide (cuprite), Cu ₂ O	2	23
Chromium iridium 3:1, Cr ₃ Ir	6m	14	Copper(II) oxide (tenorite), CuO	1	49
Chromium(III) oxide, Cr ₂ O ₃	5	22	Copper phosphate, α -Cu ₂ P ₂ O ₇	7m	113
Chromium phosphate, α -CrPO ₄	2m	12	Copper sulfate (chalcocyanite), CuSO ₄	3m	29
			Copper(II) sulfide (covellite), CuS	4	13

CUMULATIVE INORGANIC INDEX - Continued

	Vol. or Sec.	Page		Vol. or Sec.	Page
Copper uranium oxide, CuUO ₄	10m	93	Germanium oxide, GeO ₂ (tetragonal) (high form)	8	28
Dysprosium antimony, DySb	4m	41	Gold, Au	1	33
Dysprosium arsenate, DyAsO ₄	3m	30	Gold antimony 1:2 (aurostibite), AuSb ₂	7	18
Dysprosium arsenide, DyAs	4m	53	Gold(I) cyanide, AuCN	10	33
Dysprosium bismuth, DyBi	4m	47	Gold potassium cyanide, AuK(CN) ₂	8m	36
Dysprosium gallium oxide, Dy ₃ Ga ₅ O ₁₂	2m	15	Gold tin 1:1, AuSn	7	19
Dysprosium gold, DyAu	5m	66	Gold titanium 1:3, AuTi ₃	6m	17
Dysprosium nitride, DyN	4m	53	Hafnium, Hf	3	18
Dysprosium oxide, Dy ₂ O ₃	9	30	Holmium arsenate, HoAsO ₄	3m	34
Dysprosium silver, DyAg	5m	66	Holmium bismuth, HoBi	4m	48
Dysprosium telluride, DyTe	4m	54	Holmium fluoride, HoF ₃	10m	23
Dysprosium vanadium oxide, DyVO ₄ ...	4m	15	Holmium gold, HoAu	5m	68
Erbium antimony, ErSb	4m	41	Holmium nitride, HoN	4m	58
Erbium arsenate, ErAsO ₄	3m	31	Holmium oxide, Ho ₂ O ₃	9	32
Erbium arsenide, ErAs	4m	54	Holmium selenide, HoSe	4m	59
Erbium bismuth, ErBi	4m	47	Holmium silver, HoAg	5m	68
Erbium gallium oxide, Er ₃ Ga ₅ O ₁₂ ...	1m	12	Holmium vanadium oxide, HoVO ₄	4m	18
Erbium manganese oxide, ErMnO ₃	2m	16	Hydrogen amidosulfate, H ₂ NSO ₃ H	7	54
Erbium nitride, ErN	4m	55	Hydrogen arsenate, H ₅ As ₃ O ₁₀	7m	84
Erbium oxide, Er ₂ O ₃	8	25	Hydrogen borate, β-HBO ₂	9m	71
Erbium phosphate, ErPO ₄	9	31	Hydrogen borate (metaborite), HBO ₂ (cubic)	4m	27
Erbium silver, ErAg	5m	67	Hydrogen iodate, HIO ₃	5	28
Erbium telluride, ErTe	4m	55	Hydrogen iodate, HI ₃ O ₈	8m	104
Erbium vanadium oxide, ErVO ₄	5m	29	Hydrogen phosphate hydrate, H ₃ PO ₄ · ½H ₂ O	12m	56
Europium arsenate, EuAsO ₄	3m	32	Hydrogen tellurate, H ₆ TeO ₆	12m	34
Europium(III) chloride, EuCl ₃	1m	13	Indium, In	3	12
Europium gallium oxide, Eu ₃ Ga ₅ O ₁₂	2m	17	Indium antimony, InSb	4	73
Europium nitride, EuN	4m	56	Indium arsenide, InAs	3m	35
Europium oxide, EuO	4m	56	Indium oxide, In ₂ O ₃	5	26
Europium oxychloride, EuOCl	1m	13	Indium phosphate, InPO ₄	8	29
Europium phosphate, EuPO ₄	11m	26	Indium sulfide, In ₂ S ₃	11m	30
Europium(III) vanadium oxide, EuVO ₄ ...	4m	16	Iodine, I ₂	3	16
Gadolinium antimony, GdSb	4m	42	Iridium, Ir	4	9
Gadolinium arsenate, GdAsO ₄	4m	17	Iridium oxide, IrO ₂	4m	19
Gadolinium arsenide, GdAs	4m	57	Iridium titanium 1:3, IrTi ₃	6m	20
Gadolinium chloride hydrate, GdCl ₃ · 6H ₂ O	7m	118	Iron, α-Fe	4	3
Gadolinium fluoride, GdF ₃	1m	14	Iron arsenide, FeAs	1m	19
Gadolinium gallium oxide, Gd ₃ Ga ₅ O ₁₂	2m	18	Iron arsenide (loellingite), FeAs ₂	10	34
Gadolinium indium, GdIn	5m	67	Iron bromide, FeBr ₂	4m	59
Gadolinium nitride, GdN	4m	57	Iron chloride hydrate, FeCl ₂ · 2H ₂ O ..	11m	32
Gadolinium oxide, Gd ₂ O ₃	1m	16	Iron fluoride hydrate, FeF ₂ · 4H ₂ O ..	11m	90
Gadolinium oxychloride, GdOCl	1m	17	Iron hydroxide sulfate hydrate, butlerite, Fe(OH)SO ₄ · 2H ₂ O	10m	95
Gadolinium silver, GdAg	6m	87	Iron iodide, FeI ₂	4m	60
Gadolinium titanium oxide, Gd ₂ TiO ₅ ...	8m	32	Iron(II,III) oxide (magnetite), Fe ₃ O ₄	5m	31
Gadolinium vanadium oxide, GdVO ₄ ...	5m	30	Iron sulfate hydrate (melanterite), FeSO ₄ · 7H ₂ O	8m	38
Gallium, Ga	2	9	Iron sulfide (pyrite), FeS ₂	5	29
Gallium antimony, GaSb	6	30	Lanthanum antimony, LaSb	4m	42
Gallium arsenide, GaAs	3m	33	Lanthanum arsenate, LaAsO ₄	3m	36
Gallium magnesium, Ga ₂ Mg	12m	48	Lanthanum arsenide, LaAs	4m	60
Gallium magnesium, Ga ₅ Mg ₂	12m	51	Lanthanum bismuth, LaBi	4m	48
Gallium oxide, α-Ga ₂ O ₃	4	25	Lanthanum borate, LaBO ₃	1m	20
Gallium phosphate hydrate, GaPO ₄ · 2H ₂ O	8m	34	Lanthanum cadmium, LaCd	5m	63
Gallium phosphate (α-quartz type), GaPO ₄	8	27	Lanthanum chloride, LaCl ₃	1m	20
Germanium, Ge	1	18	Lanthanum fluoride, LaF ₃	7	21
Germanium iodide, GeI ₂	4m	58	Lanthanum niobium titanium oxide, LaNbTiO ₆	3m	37
Germanium(IV) iodide, GeI ₄	5	25	Lanthanum nitrate hydrate, La(NO ₃) ₃ · 6H ₂ O	8m	40
Germanium oxide, GeO ₂ (hexagonal) (low form)	1	51			

CUMULATIVE INORGANIC INDEX - Continued

	Vol. or Sec.	Page		Vol. or Sec.	Page
Lanthanum nitride, LaN	4m	61	Lithium niobium oxide, LiNbO ₃	6m	22
Lanthanum oxide, La ₂ O ₃	3	33	Lithium nitrate, LiNO ₃	7	27
Lanthanum oxychloride, LaOCl	7	22	Lithium oxide, Li ₂ O	1m	25
Lanthanum phosphide, LaP	5m	69	Lithium phosphate hydrate, Li ₃ P ₃ O ₉ ·3H ₂ O	2m	20
Lanthanum selenide, LaSe	4m	61	Lithium phosphate, low form (lithio- phosphate), Li ₃ PO ₄	4m	21
Lanthanum zinc, LaZn	5m	70	Lithium phosphate, high form, Li ₃ PO ₄	3m	39
Lead, Pb	1	34	Lithium rubidium fluoride, LiRbF ₂ ..	7m	128
Lead borate, PbB ₄ O ₇	4m	19	Lithium selenide, Li ₂ Se	10m	100
Lead bromide, PbBr ₂	2	47	Lithium silver bromide, Li ₂ Ag ₈ Br	12m	55
Lead bromide chloride, PbBrCl	11m	33	Lithium silver bromide, Li ₄ Ag ₆ Br	12m	55
Lead bromide fluoride, PbBrF	10m	25	Lithium silver bromide, Li ₆ Ag ₄ Br	12m	55
Lead chloride (cotunnite), PbCl ₂	12m	23	Lithium sodium aluminum fluoride, cryolithionite, Li ₃ Na ₃ Al ₂ F ₁₂	9m	23
Lead carbonate (cerrussite), PbCO ₃	2	56	Lithium sodium sulfate, LiNaSO ₄	6m	24
Lead chloride fluoride (matlockite), PbClF	1	76	Lithium sulfate, Li ₂ SO ₄	6m	26
Lead fluoride, α-PbF ₂ (orthorhombic)	5	31	Lithium sulfate hydrate, Li ₂ SO ₄ ·H ₂ O	4m	22
Lead fluoride, β-PbF ₂ (cubic)	5	33	Lithium sulfide, Li ₂ S	10m	101
Lead fluoride iodide, PbFI	10m	26	Lithium telluride, Li ₂ Te	10m	102
Lead hydroxide phosphate, Pb ₅ (PO ₄) ₃ OH	8	33	Lithium tungsten oxide, Li ₂ WO ₄ (trigonal)	1m	25
Lead(II) iodide, PbI ₂	5	34	Lithium tungsten oxide hydrate, Li ₂ WO ₄ ·½H ₂ O	2m	20
Lead molybdenum oxide (wulfenite), PbMoO ₄	7	23	Lithium uranium fluoride, LiUF ₅	7m	131
Lead nitrate, Pb(NO ₃) ₂	5	36	Lutetium arsenate, LuAsO ₄	5m	36
Lead oxide (litharge), PbO (red, tetragonal)	2	30	Lutetium gallium oxide, Lu ₃ Ga ₅ O ₁₂	2m	22
Lead oxide (massicot), PbO (yellow, orthorhombic)	2	32	Lutetium manganese oxide, LuMnO ₃	2m	23
Lead(II,III) oxide (minium), Pb ₃ O ₄	8	32	Lutetium nitride, LuN	4m	62
Lead oxide sulfate, Pb ₅ O ₄ SO ₄	10m	27	Lutetium oxide, Lu ₂ O ₃	1m	27
Lead oxybromide, Pb ₃ O ₂ Br ₂	5m	32	Lutetium vanadium oxide, LuVO ₄	5m	37
Lead selenide (clausthalite), PbSe	5	38	Magnesium, Mg	1	10
Lead strontium nitrate, Pb _{0.33} Sr _{0.67} (NO ₃) ₂	12m	53	Magnesium aluminum oxide (spinel), MgAl ₂ O ₄	9m	25
Lead strontium nitrate, Pb _{0.67} Sr _{0.33} (NO ₃) ₂	12m	53	Magnesium aluminum silicate (pyrope), Mg ₃ Al ₂ (SiO ₄) ₃	4m	24
Lead sulfate (anglesite), PbSO ₄	3	67	Magnesium aluminum silicate (low cordierite), Mg ₂ Al ₄ Si ₅ O ₁₈ (orthorhombic)	1m	28
Lead sulfide (galena), PbS	2	18	Magnesium aluminum silicate (high cordierite), Mg ₂ Al ₄ Si ₅ O ₁₈ (hexagonal)	1m	29
Lead tin oxide, Pb ₂ SnO ₄	10m	29	Magnesium ammonium phosphate hydrate, (struvite), MgNH ₄ PO ₄ ·6H ₂ O	3m	41
Lead titanium oxide, PbTiO ₃	5	39	Magnesium borate, Mg ₂ B ₂ O ₅ (triclinic)	4m	25
Lead tungsten oxide (stolzite), PbWO ₄ (tetragonal)	5m	34	Magnesium bromide, MgBr ₂	4m	62
Lead uranium oxide, Pb ₃ UO ₆	8m	109	Magnesium bromide hydrate, MgBr ₂ ·6H ₂ O	11m	35
Lithium aluminum, Li ₉ Al ₄	10m	98	Magnesium carbonate (magnesite), MgCO ₃	7	28
Lithium aluminum fluoride, α-Li ₃ AlF ₆	8m	111	Magnesium cerium MgCe	5m	65
Lithium arsenate, Li ₃ AsO ₄	2m	19	Magnesium cerium nitrate hydrate, Mg ₃ Ce ₂ (NO ₃) ₁₂ ·24H ₂ O	10	20
Lithium azide, LiN ₃	8m	113	Magnesium chlorate hydrate, Mg(ClO ₄) ₂ ·6H ₂ O	7m	30
Lithium barium fluoride, LiBaF ₃	5m	35			
Lithium beryllium fluoride, Li ₂ BeF ₄	7m	126			
Lithium borate, Li ₂ B ₄ O ₇	8m	114			
Lithium bromide, LiBr	4	30			
Lithium carbonate, Li ₂ CO ₃	8m	42			
Lithium chlorate hydrate, LiClO ₄ ·3H ₂ O	8	34			
Lithium chloride, LiCl	1	62			
Lithium fluoride, LiF	1	61			
Lithium gallium oxide, LiGaO ₂	10m	31			
Lithium hydroxide hydrate, LiOH·H ₂ O	11m	92			
Lithium iodate, LiIO ₃ (hexagonal) ..	7	26			
Lithium iodate, LiIO ₃ (tetragonal)	10m	33			
Lithium molybdenum oxide, Li ₂ MoO ₄ (trigonal)	1m	23			

CUMULATIVE INORGANIC INDEX - Continued

	Vol. or Sec.	Page		Vol. or Sec.	Page
Magnesium chloride (chloro-magnesite), $MgCl_2$	11m	94	Manganese chloride hydrate, $MnCl_2 \cdot 2H_2O$	11m	38
Magnesium chloride hydrate, $MgCl_2 \cdot 12H_2O$	7m	135	Manganese chloride hydrate, $MnCl_2 \cdot 4H_2O$	9m	28
Magnesium chloride hydrate (bischofite), $MgCl_2 \cdot 6H_2O$	11m	37	Manganese cobalt oxide, $MnCo_2O_4$	9m	30
Magnesium chromium oxide (picrochromite), $MgCr_2O_4$	9	34	Manganese fluoride, MnF_2	10m	105
Magnesium fluoride (sellaite), MgF_2	4	33	Manganese iodide, MnI_2	4m	63
Magnesium fluoride silicate (humite), $Mg_7F_2(SiO_4)_3$	1m	30	Manganese iron oxide (jacobsite), $MnFe_2O_4$	9	36
Magnesium fluoride silicate (norbergite), $Mg_3F_2SiO_4$	10	39	Manganese oxide (hausmannite), Mn_3O_4	10m	38
Magnesium gallium oxide, $MgGa_2O_4$	10	36	Manganese oxide (partridgeite), $\alpha\text{-Mn}_2O_3$	11m	95
Magnesium germanium oxide, Mg_2GeO_4 (cubic)	10	37	Manganese oxide (pyrolusite), $\beta\text{-MnO}_2$	10m	39
Magnesium germanium oxide, Mg_2GeO_4 (orthorhombic)	10	38	Manganese oxide hydroxide, groutite, $\alpha\text{-MnOOH}$	11m	97
Magnesium gold, $MgAu$	6m	83	Manganese(II) oxide (manganosite), MnO	5	45
Magnesium hydrogen phosphate hydrate, newberryite, $MgHPO_4 \cdot 3H_2O$..	7m	139	Manganese selenide, $MnSe$	10	41
Magnesium hydroxide (brucite), $Mg(OH)_2$	6	30	Manganese sulfide (alabandite), $\alpha\text{-MnS}$	4	11
Magnesium iron hydroxide carbonate hydrate, pyroaurite, $Mg_6Fe_2(OH)_{16}CO_3 \cdot 4H_2O$, phase II ..	10m	104	Manganese(II) tungsten oxide (huebnerite), $MnWO_4$	2m	24
Magnesium iron hydroxide carbonate hydrate, sjögrenite, $Mg_6Fe_2(OH)_{16}CO_3 \cdot 4H_2O$, phase I ..	10m	103	Manganese vanadium oxide, $Mn_2V_2O_7$..	9m	75
Magnesium lanthanum, $MgLa$	5m	69	Mercury amide chloride, $HgNH_2Cl$	10m	40
Magnesium lanthanum nitrate hydrate, $Mg_3La_2(NO_3)_{12} \cdot 24H_2O$	1m	22	Mercury ammine chloride, $Hg(NH_3)_2Cl_2$	11m	39
Magnesium manganese oxide, $MgMn_2O_4$	10m	35	Mercury bromate, $Hg(BrO_3)_2$	10m	107
Magnesium mercury, $MgHg$	6m	84	Mercury bromide, $HgBr_2$	10m	110
Magnesium molybdenum oxide, $MgMoO_4$	7m	28	Mercury(I) bromide, Hg_2Br_2	7	33
Magnesium nickel oxide, $MgNiO_2$	10m	36	Mercury(I) chloride (calomel), Hg_2Cl_2	1	72
Magnesium oxide (periclase), MgO	1	37	Mercury(II) chloride, $HgCl_2$	1	73
Magnesium phosphate, $\alpha\text{-Mg}_2P_2O_7$	9m	73	Mercury chloride sulfide, $\alpha\text{-Hg}_3Cl_2S_2$	8m	118
Magnesium selenide, $MgSe$	5m	70	Mercury(II) cyanide, $Hg(CN)_2$	6	35
Magnesium selenite hydrate, $MgSeO_3 \cdot 6H_2O$	8m	116	Mercury(II) fluoride, HgF_2	2m	25
Magnesium silicate, enstatite, $MgSiO_3$	6	32	Mercury(II) iodide, HgI	4	49
Magnesium silicate (forsterite), Mg_2SiO_4	1	83	Mercury iodide, HgI_2 (tetragonal) ..	7m	32
Magnesium sulfate hydrate (epsomite), $MgSO_4 \cdot 7H_2O$	7	30	Mercury(II) oxide (montroydite), HgO	9	39
Magnesium sulfide, MgS	7	31	Mercury(II) selenide (tiemannite), $HgSe$	7	35
Magnesium sulfite hydrate, $MgSO_3 \cdot 6H_2O$	9m	26	Mercury(II) sulfide (cinnabar), HgS (hexagonal)	4	17
Magnesium tin, Mg_2Sn	5	41	Mercury(II) sulfide (metacinnabar), HgS (cubic)	4	21
Magnesium tin oxide, Mg_2SnO_4	10m	37	Molybdenum, Mo	1	20
Magnesium titanium oxide (geikielite), $MgTiO_3$	5	43	Molybdenum arsenide, Mo_2As_3	10m	115
Magnesium titanium oxide, $MgTiO_4$	12m	25	Molybdenum osmium 3:1, Mo_3Os	6m	28
Magnesium tungsten oxide, $MgWO_4$	1	84	Molybdenum oxide (molybdite), MoO_3	3	30
Manganese, $\alpha\text{-Mn}$	7m	142	Molybdenum sulfide (molybdenite), MoS_2	5	47
Manganese aluminum oxide (galaxite), $MnAl_2O_4$	9	35	Neodymium antimony, $NdSb$	4m	43
Manganese bromide, $MnBr_2$	4m	63	Neodymium arsenate, $NdAsO_4$	4m	28
Manganese(II) carbonate (rhodochrosite), $MnCO_3$	7	32	Neodymium arsenide, $NdAs$	4m	64
Manganese chloride (scacchite), $MnCl_2$	8m	43	Neodymium bismuth, $NdBi$	4m	49
			Neodymium borate, NdB_3O_3	1m	32
			Neodymium chloride, $NdCl_3$	1m	33
			Neodymium fluoride, NdF_3	8	36
			Neodymium gallium oxide, $Nd_3Ga_5O_12$	1m	34
			Neodymium oxide, Nd_2O_3	4	26
			Neodymium oxychloride, $NdOCl$	8	37
			Neodymium phosphate, $NdPO_4$	11m	40
			Neodymium selenide, $NdSe$	5m	71
			Neodymium silver, $NdAg$	5m	71

CUMULATIVE INORGANIC INDEX - Continued

	Vol. or Sec.	Page		Vol. or Sec.	Page
Neodymium vanadium oxide, NdVO_4	4m	30	Potassium bromide chloride,		
Neptunium nitride, NpN	4m	64	$\text{KBr}_{0.5}\text{Cl}_{0.5}$	8m	46
Nickel, Ni	1	13	Potassium bromide iodide,		
Nickel aluminum, NiAl	6m	82	$\text{KBr}_{.33}\text{I}_{.67}$	11m	44
Nickel aluminum oxide, NiAl_2O_4	9	42	Potassium bromide iodide,		
Nickel arsenide 1:2 (rammelsbergite), NiAs_2	10	42	$\text{KBr}_{.67}\text{I}_{.33}$	11m	45
Nickel arsenic sulfide (gersdorffite), NiAsS	1m	35	Potassium cadmium fluoride, KCdF_3 ..	8m	47
Nickel bromide, NiBr_2	10m	119	Potassium cadmium sulfate,		
Nickel(II) carbonate, NiCO_3 (trigonal)	1m	36	$\text{K}_2\text{Cd}_2(\text{SO}_4)_3$	7m	34
Nickel chloride, NiCl_2	9m	81	Potassium calcium carbonate (fairchildite), $\text{K}_2\text{Ca}(\text{CO}_3)_2$	8m	48
Nickel chloride hydrate, $\text{NiCl}_2 \cdot 6\text{H}_2\text{O}$	11m	42	Potassium calcium chloride		
Nickel fluoride, NiF_2	10m	121	(chlorocalcrite), KCaCl_3	7m	36
Nickel fluoride hydrate, $\text{NiF}_2 \cdot 4\text{H}_2\text{O}$	11m	43	Potassium calcium fluoride, KCaF_3 ..	8m	49
Nickel gallium oxide, NiGa_2O_4	10	45	Potassium calcium magnesium sulfate,		
Nickel germanium oxide, Ni_2GeO_4	9	43	$\text{K}_2\text{CaMg}(\text{SO}_4)_3$	7m	37
Nickel iron oxide (trevorite), NiFe_2O_4	10	44	Potassium calcium nickel nitrite,		
Nickel nitrate hydrate, $\text{Ni}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$	12m	26	$\text{K}_2\text{CaNi}(\text{NO}_2)_6$	9m	33
Nickel(II) oxide (bunsenite), NiO ..	1	47	Potassium calcium sulfate,		
Nickel phosphide, Ni_{12}P_5	9m	83	$\text{K}_2\text{Ca}_2(\text{SO}_4)_3$	7m	39
Nickel silicon fluoride hydrate, $\text{NiSiF}_6 \cdot 6\text{H}_2\text{O}$	8	38	Potassium cerium fluoride, $\beta\text{-KCeF}_4$	12m	59
Nickel sulfate, NiSO_4	2m	26	Potassium chlorate, KClO_3	3m	42
Nickel sulfate hydrate (retgersite), $\text{NiSO}_4 \cdot 6\text{H}_2\text{O}$	7	36	Potassium chlorate, KClO_4	6	43
Nickel sulfide, millerite, NiS	1m	37	Potassium chloride (sylvite), KCl ..	1	65
Nickel tungsten oxide, NiWO_4	2m	27	Potassium chromium oxide, K_3CrO_8 ...	3m	44
Niobium gold 3:1, Nb_3Au	6m	16	Potassium chromium oxide sulfate,		
Niobium iridium 3:1, Nb_3Ir	6m	19	$\text{K}_2(\text{CrO}_4)_{.33}(\text{SO}_4)_{.67}$	12m	28
Niobium osmium 3:1, Nb_3Os	6m	30	Potassium chromium oxide sulfate,		
Niobium oxychloride, NbOCl_3	7m	148	$\text{K}_2(\text{CrO}_4)_{.67}(\text{SO}_4)_{.33}$	12m	27
Niobium platinum 3:1, Nb_3Pt	6m	31	Potassium chromium sulfate hydrate,		
Niobium silicide, NbSi_2	8	39	$\text{KCr}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	6	39
Osmium, Os	4	8	Potassium cobalt(II) fluoride,		
Osmium titanium, OsTi	6m	85	KCoF_3	6m	37
Palladium, Pd	1	21	Potassium cobalt fluoride, K_2CoF_4 ..	11m	46
Palladium hydride, $\text{PdH}_0.706$	5m	72	Potassium cobalt nitrite,		
Palladium oxide, PdO	4	27	$\text{K}_3\text{Co}(\text{NO}_2)_6$	9	45
Phosphorus bromide, PBr_7	7m	150	Potassium cobalt(II) sulfate,		
Phosphorus oxide (stable form I), P_2O_5 (orthorhombic)	9m	86	$\text{K}_2\text{Co}_2(\text{SO}_4)_3$	6m	35
Phosphorus oxide (stable form II), P_2O_5 (orthorhombic)	9m	88	Potassium copper chloride, KCuCl_3 ..	7m	41
Phosphorus oxide (metastable form), P_4O_{10} (rhombohedral)	9m	91	Potassium copper(II) hydrate		
Platinum, Pt	1	31	(mitscherlichite), $\text{K}_2\text{CuCl}_4 \cdot 2\text{H}_2\text{O}$...	9m	34
Platinum titanium 1:3, PtTi_3	6m	33	Potassium copper(II) fluoride,		
Plutonium arsenide, PuAs	4m	65	KCuF_3	6m	38
Plutonium phosphide, PuP	4m	65	Potassium cyanate, KCNO	7	39
Plutonium telluride, PuTe	4m	66	Potassium cyanide, KCN	1	77
Potassium aluminum sulfate, $\text{KAl}(\text{SO}_4)_2$	9m	31	Potassium fluoride, KF	1	64
Potassium aluminum sulfate hydrate, (alum), $\text{KAl}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	6	36	Potassium germanium fluoride, K_2GeF_6	6	41
Potassium barium nickel nitrite, $\text{K}_2\text{BaNi}(\text{NO}_2)_6$	9m	32	Potassium hydrogen arsenate,		
Potassium borohydride, KBH_4	9	44	KH_2AsO_4	1m	38
Potassium bromate, KBrO_3	7	38	Potassium hydrogen phosphate,		
Potassium bromide, KBr	1	66	KH_2PO_4	3	69

CUMULATIVE INORGANIC INDEX - Continued

	Vol. or Sec.	Page		Vol. or Sec.	Page
Potassium magnesium fluoride, K_2MgF_4	10m	42	Potassium sodium sulfate, $K_{0.67}Na_{1.33}SO_4$	6m	48
Potassium magnesium selenate hydrate, $K_2Mg(SeO_4)_2 \cdot 6H_2O$	10m	43	Potassium sodium sulfate, $KNaSO_4$	6m	50
Potassium magnesium sulfate (langbeinite), $K_2Mg_2(SO_4)_3$	6m	40	Potassium sodium sulfate (aphthitalite), $K_3Na(SO_4)_2$	6m	52
Potassium magnesium sulfate hydrate (picromerite), $K_2Mg(SO_4)_2 \cdot 6H_2O$	8m	54	Potassium sulfate, $K_2S_2O_7$	9m	99
Potassium manganese(II) fluoride, $KMnF_3$	6m	45	Potassium sulfate (arcanite), K_2SO_4	3	62
Potassium manganese oxide, $KMnO_4$...	7	42	Potassium sulfide, K_2S	10m	127
Potassium manganese(II) sulfate (manganolangbeinite), $K_2Mn_2(SO_4)_3$	6m	43	Potassium telluride, K_2Te	10m	128
Potassium molybdenum oxide phosphate hydrate, $K_2(MoO_3)_{12}PO_4 \cdot 4H_2O$	8	43	Potassium thiocyanate, $KCNS$	8	44
Potassium nickel fluoride, $KNiF_3$...	7m	42	Potassium tin chloride, K_2SnCl_6	6	38
Potassium nickel fluoride, K_2NiF_4 ..	10m	45	Potassium titanium fluoride, K_2TiF_6	7	40
Potassium nickel(II) sulfate, $K_2Ni_2(SO_4)_3$	6m	46	Potassium tungsten oxide, K_2WO_4	11m	47
Potassium niobium fluoride, K_2NbF_7	8m	120	Potassium vanadium oxide, KV_3O_8	8m	56
Potassium nitrate (niter), KNO_3	3	58	Potassium zinc bromide hydrate, $KZnBr_3 \cdot 2H_2O$	11m	104
Potassium nitrite, KNO_2	9m	38	Potassium zinc fluoride, $KZnF_3$	5	51
Potassium nitroso ruthenium chloride, $K_2(NO)RuCl_5$	2m	29	Potassium zinc fluoride, K_2ZnF_4	10m	46
Potassium oxide, K_2O	10m	125	Potassium zinc iodide hydrate, $KZnI_3 \cdot 2H_2O$	11m	107
Potassium platinum bromide, K_2PtBr_6	8	40	Potassium zinc sulfate, $K_2Zn_2(SO_4)_3$	6m	54
Potassium platinum chloride, K_2PtCl_6	5	49	Potassium zinc sulfate hydrate, $K_2Zn(SO_4)_2 \cdot 6H_2O$	7m	43
Potassium platinum fluoride, K_2PtF_6	6	42	Potassium zinc vanadium oxide hydrate, $K_2Zn_2V_{10}O_{28} \cdot 16H_2O$	3m	45
Potassium rhenium chloride, K_2ReCl_6	2m	28	Potassium zirconium fluoride, K_3ZrF_7	9	46
Potassium rhenium oxide, $KReO_4$	8	41	Praseodymium antimony, $PrSb$	4m	43
Potassium rubidium chloride, $K_{0.5}Rb_{0.5}Cl$	8m	76	Praseodymium arsenate, $PrAsO_4$	4m	32
Potassium rubidium chromium oxide, $KRbCrO_4$	12m	29	Praseodymium arsenide, $PrAs$	4m	67
Potassium ruthenium chloride, K_2RuCl_6	10	46	Praseodymium bismuth, $PrBi$	4m	49
Potassium ruthenium oxide chloride hydrate, $K_4Ru_2OCl_{10} \cdot H_2O$	10	47	Praseodymium cadmium, $PrCd$	5m	64
Potassium selenate, K_2SeO_4	9m	41	Praseodymium chloride, $PrCl_3$	1m	39
Potassium selenide, K_2Se	10m	126	Praseodymium fluoride, PrF_3	5	52
Potassium selenium bromide, K_2SeBr_6	8	41	Praseodymium oxychloride, $PrOCl$	9	47
Potassium silicon fluoride (hieratite), K_2SiF_6	5	50	Praseodymium sulfide, PrS	4m	67
Potassium silver cyanide, $KAg(CN)_2$	8m	78	Praseodymium vanadium oxide, $PrVO_4$	5m	40
Potassium sodium aluminum fluoride (elpasolite), K_2NaAlF_6	9m	43	Praseodymium zinc, $PrZn$	5m	72
Potassium sodium bromide, $K_2Na_0.8Br$	12m	62	Rhenium, Re	2	13
Potassium sodium bromide, $K_4Na_0.8Br$	12m	62	Rhodium, Rh	3	9
Potassium sodium bromide, K_8Na_2Br	12m	62	Rubidium aluminum sulfate hydrate, $RbAl(SO_4)_2 \cdot 12H_2O$	6	44
Potassium sodium chloride, $K_2Na_0.8Cl$	12m	63	Rubidium amide, $RbNH_2$	5m	73
Potassium sodium chloride, $K_4Na_0.6Cl$	12m	63	Rubidium bromate, $RbBrO_3$	8	45
Potassium sodium chloride, $K_6Na_0.4Cl$	12m	63	Rubidium bromide, $RbBr$	7	43
Potassium sodium chloride, K_8Na_2Cl	12m	63	Rubidium cadmium chloride, high form, $RbCdCl_3$ (tetragonal)	5m	43
			Rubidium cadmium chloride, low form, $RbCdCl_3$ (orthorhombic)	5m	41
			Rubidium cadmium sulfate, $Rb_2Cd_2(SO_4)_3$	7m	45
			Rubidium calcium chloride, $RbCaCl_3$	7m	47
			Rubidium calcium fluoride, $RbCaF_3$	8m	57
			Rubidium calcium sulfate, $Rb_2Ca_2(SO_4)_3$	7m	48
			Rubidium chlorate, $RbClO_3$	8	47
			Rubidium chlorate, $RbClO_4$	2m	30
			Rubidium chloride, $RbCl$	4	41
			Rubidium chromium oxide, Rb_2CrO_4	3m	46
			Rubidium chromium sulfate hydrate, $RbCr(SO_4)_2 \cdot 12H_2O$	6	47

CUMULATIVE INORGANIC INDEX - Continued

	Vol. or Sec.	Page	Vol. or Sec.	Page	
Rubidium cobalt(II) chloride, RbCoCl ₃	6m	57	Scandium arsenate, ScAsO ₄	4m	35
Rubidium cobalt fluoride, RbCoF ₃	8m	58	Scandium arsenide, ScAs	4m	68
Rubidium cobalt sulfate, Rb ₂ Co ₂ (SO ₄) ₃	8m	59	Scandium oxide, Sc ₂ O ₃	3	27
Rubidium copper chloride hydrate, Rb ₂ CuCl ₄ ·2H ₂ O	10m	47	Scandium phosphate, ScPO ₄	8	50
Rubidium copper sulfate hydrate, Rb ₂ Cu(SO ₄) ₂ ·6H ₂ O	8m	61	Scandium silicate (thortveitite), Sc ₂ Si ₂ O ₇	7m	58
Rubidium fluoride, RbF	8m	63	Selenium, Se	5	54
Rubidium iodate, RbIO ₄	2m	31	Selenium oxide (selenolite), SeO ₂ ..	7m	60
Rubidium iodide, RbI	4	43	Silicon, Si	2	6
Rubidium iron sulfate hydrate, Rb ₂ Fe(SO ₄) ₂ ·6H ₂ O	8m	64	Silicon, Si (reference standard) ..:	12m	2
Rubidium magnesium chromium oxide, Rb ₂ Mg ₂ (CrO ₄) ₃	8m	66	Silicon oxide (α or low cristobalite), SiO ₂ (tetragonal)	10	48
Rubidium magnesium chromium oxide hydrate, Rb ₂ Mg(CrO ₄) ₂ ·6H ₂ O	8m	68	Silicon oxide (α or low quartz), SiO ₂ (hexagonal)	3	24
Rubidium magnesium sulfate, Rb ₂ Mg ₂ (SO ₄) ₃	7m	50	Silicon oxide (β or high cristobalite), SiO ₂ (cubic)	1	42
Rubidium magnesium sulfate hydrate, Rb ₂ Mg(SO ₄) ₂ ·6H ₂ O	8m	70	Silver, Ag	1	23
Rubidium manganese(II) fluoride, RbMnF ₃	5m	44	Silver, Ag (reference standard)	8m	2
Rubidium manganese sulfate, Rb ₂ Mn ₂ (SO ₄) ₃	7m	52	Silver antimony sulfide, AgSbS ₂ (cubic)	5m	48
Rubidium nickel(II) chloride, RbNiCl ₃	6m	58	Silver antimony sulfide (miargyrite), AgSbS ₂ (monoclinic)	5m	49
Rubidium nickel sulfate, Rb ₂ Ni ₂ (SO ₄) ₃	8m	72	Silver antimony sulfide (pyrargyrite), Ag ₃ SbS ₃ (trigonal)	5m	51
Rubidium nickel sulfate hydrate, Rb ₂ Ni(SO ₄) ₂ ·6H ₂ O	8m	74	Silver antimony telluride, AgSbTe ₂ ..	3m	47
Rubidium nitrate, RbNO ₃ (trigonal)	5m	45	Silver arsenate, Ag ₃ AsO ₄	5	56
Rubidium platinum chloride, Rb ₂ PtCl ₆	5	53	Silver arsenic sulfide, xanthoconite, Ag ₃ AsS ₃	8m	126
Rubidium platinum fluoride, Rb ₂ PtF ₆	6	48	Silver bromate, AgBrO ₃	5	57
Rubidium selenate, Rb ₂ SeO ₄	9m	44	Silver bromide (bromyrite), AgBr ..	4	46
Rubidium silicon fluoride, Rb ₂ SiF ₆	6	49	Silver carbonate, Ag ₂ CO ₃	1m	44
Rubidium strontium chloride, RbSrCl ₃	7m	54	Silver chlorate, AgClO ₃	7	44
Rubidium sulfate, Rb ₂ SO ₄	8	48	Silver chloride (cerargyrite), AgCl ..	4	44
Rubidium tellurium bromide, Rb ₂ TeBr ₆	8	46	Silver chromium oxide, Ag ₂ CrO ₄	12m	30
Rubidium tellurium chloride, Rb ₂ TeCl ₆	8	48	Silver cyanide, AgCN	9m	48
Rubidium tin chloride, Rb ₂ SnCl ₆	6	46	Silver fluoride, Ag ₂ F	5m	53
Rubidium zinc fluoride, RbZnF ₃	7m	57	Silver iodate, AgIO ₄	9	49
Rubidium zinc sulfate hydrate, Rb ₂ Zn(SO ₄) ₂ ·6H ₂ O	7m	55	Silver iodide (iodyrite), AgI (hexagonal)	8	51
Ruthenium, Ru	4	5	Silver iodide, γ -AgI (cubic)	9	48
Ruthenium titanium, RuTi	6m	86	Silver manganese oxide, AgMnO ₄	7m	155
Samarium arsenate, SmAsO ₄	4m	33	Silver molybdenum oxide, Ag ₂ MoO ₄ ..	7	45
Samarium arsenide, SmAs	4m	68	Silver nitrate, AgNO ₃	5	59
Samarium chloride, SmCl ₃	1m	40	Silver nitrite, AgNO ₂	5	60
Samarium fluoride, SmF ₃	1m	41	Silver oxide, Ag ₂ O	1m	45
Samarium gallium oxide, Sm ₃ Ga ₅ O ₁₂ ..	1m	42	Silver(II) oxide nitrate, Ag ₇ O ₈ NO ₃ ..	4	61
Samarium oxide, Sm ₂ O ₃ (cubic)	4m	34	Silver phosphate, Ag ₃ PO ₄	5	62
Samarium oxychloride, SmOCl	1m	43	Silver rhenium oxide, AgReO ₄	8	53
Samarium silver, SmAg	5m	73	Silver selenate, Ag ₂ SeO ₄	2m	32
Samarium tin oxide, Sm ₂ Sn ₂ O ₇	8m	77	Silver sodium chloride, Ag _{0.5} Na _{0.5} Cl ..	8m	79
Samarium vanadium oxide, SmVO ₄	5m	47	Silver sulfate, Ag ₂ SO ₄	7	46
Scandium antimony, ScSb	4m	44	Silver sulfide (argentite), Ag ₂ S ..	10	51
			Sodium, Na	9m	105
			Sodium aluminum chloride silicate, sodalite, Na ₈ Al ₆ Cl ₂ (SiO ₄) ₆	7m	158
			Sodium azide, α -NaN ₃ , at -90 to -100 °C	8m	129
			Sodium azide, β -NaN ₃	8m	130
			Sodium beryllium calcium fluoride silicate, leucophanite, NaBeCaFSi ₂ O ₆	8m	138
			Sodium borate, Na ₂ B ₈ O ₁₃	7m	160
			Sodium boron hydride, NaBH ₄	9	51
			Sodium bromate, NaBrO ₃	5	65

CUMULATIVE INORGANIC INDEX - Continued

	Vol. or Sec.	Page		Vol. or Sec.	Page
Sodium bromide, NaBr	3	47	Sodium manganese(II) fluoride, NaMnF_3	6m	65
Sodium bromide chloride, $\text{NaBr}_{.33}\text{Cl}_{.67}$	11m	49	Sodium mercury(II) chloride hydrate, $\text{NaHgCl}_3 \cdot 2\text{H}_2\text{O}$	6m	66
Sodium bromide chloride, $\text{NaBr}_{.67}\text{Cl}_{.33}$	11m	50	Sodium molybdenum oxide, Na_2MoO_4 ..	1m	46
Sodium calcium aluminum fluoride hydrate, thomsenolite, $\text{NaCaAlF}_6 \cdot \text{H}_2\text{O}$	8m	132	Sodium molybdenum oxide, $\text{Na}_2\text{Mo}_2\text{O}_7$..	9m	110
Sodium calcium beryllium aluminum fluorosilicate, meliphantite, ($\text{Na}_{0.63}\text{Ca}_{1.37}\text{Be}(\text{Al}_{0.13}\text{Si}_{1.87})$ ($\text{O}_{6.25}\text{F}_{0.75}$)	8m	135	Sodium neodymium fluoride silicate, $(\text{Na}_2\text{Nd}_8)\text{F}_2(\text{SiO}_4)_6$	7m	66
Sodium calcium carbonate hydrate, pirssonite, $\text{Na}_2\text{Ca}(\text{CO}_3)_2 \cdot 2\text{H}_2\text{O}$	9m	106	Sodium nickel(II) sulfate hydrate, $\text{Na}_2\text{Ni}(\text{SO}_4)_2 \cdot 4\text{H}_2\text{O}$	6m	68
Sodium calcium silicate, $\text{Na}_2\text{CaSiO}_4$	10m	48	Sodium nitrate (soda-niter), NaNO_3	6	50
Sodium calcium sulfate (glauberite), $\text{Na}_2\text{Ca}(\text{SO}_4)_2$	6m	59	Sodium nitrite, NaNO_2	4	62
Sodium carbonate hydrate (thermo- natrite), $\text{Na}_2\text{CO}_3 \cdot \text{H}_2\text{O}$	8	54	Sodium oxide, Na_2O	10m	134
Sodium carbonate sulfate, $\text{Na}_4\text{CO}_3\text{SO}_4$	11m	51	Sodium phosphate, $\text{Na}_3\text{P}_3\text{O}_9$	3m	49
Sodium carbonate sulfate (burkeite), $\text{Na}_6\text{CO}_3(\text{SO}_4)_2$	11m	52	Sodium phosphate hydrate, $\text{Na}_3\text{P}_3\text{O}_9 \cdot \text{H}_2\text{O}$	3m	50
Sodium carbonate sulfate, $\text{Na}_6\text{CO}_3(\text{SO}_4)_2$	11m	53	Sodium phosphate hydrate, $\alpha\text{-Na}_4\text{P}_4\text{O}_{12} \cdot 4\text{H}_2\text{O}$ (monoclinic)	10	52
Sodium carbonate sulfate, $\text{Na}_6(\text{CO}_3)_2\text{SO}_4$	11m	54	Sodium phosphate hydrate, $\beta\text{-Na}_4\text{P}_4\text{O}_{12} \cdot 4\text{H}_2\text{O}$ (triclinic)	2m	35
Sodium chlorate, NaClO_3	3	51	Sodium phosphate hydrate, $\text{Na}_6\text{P}_6\text{O}_{18} \cdot 6\text{H}_2\text{O}$	5m	54
Sodium chlorate, NaClO_4 (orthorhombic)	7	49	Sodium praseodymium fluoride silicate, $(\text{Na}_2\text{Pr}_8)\text{F}_2(\text{SiO}_4)_6$	7m	68
Sodium chloride (halite), NaCl	2	41	Sodium selenate, Na_2SeO_4	9m	55
Sodium chromium oxide, Na_2CrO_4	9m	48	Sodium selenide, Na_2Se	10m	135
Sodium chromium oxide hydrate, $\text{Na}_2\text{Cr}_2\text{O}_7 \cdot 2\text{H}_2\text{O}$	7m	62	Sodium silicate, $\alpha\text{(III)}, \text{Na}_2\text{Si}_2\text{O}_5$..	8m	141
Sodium chromium oxide hydrate, $\text{Na}_2\text{CrO}_4 \cdot 4\text{H}_2\text{O}$	9m	50	Sodium silicate, $\beta\text{-Na}_2\text{Si}_2\text{O}_5$	10m	136
Sodium chromium oxide sulfate, $\text{Na}_4(\text{CrO}_4)(\text{SO}_4)$	11m	55	Sodium sulfate, Na_2SO_4	11m	57
Sodium cobalt(II) sulfate hydrate, $\text{Na}_2\text{Co}(\text{SO}_4)_2 \cdot 4\text{H}_2\text{O}$	6m	61	Sodium sulfate (thenardite), Na_2SO_4	2	59
Sodium cyanate, NaCNO	2m	33	Sodium sulfide, Na_2S	10m	140
Sodium cyanide, NaCN (cubic)	1	78	Sodium sulfite, Na_2SO_3	3	60
Sodium cyanide, NaCN (orthorhombic) at 6 °C	1	79	Sodium telluride, Na_2Te	10m	141
Sodium fluoride (villiaumite), NaF	1	63	Sodium tin fluoride, NaSn_2F_5	7m	166
Sodium hydrogen fluoride, NaHF_2	5	63	Sodium tungsten oxide, Na_2WO_4	1m	47
Sodium hydrogen phosphate, $\text{Na}_3\text{H}(\text{PO}_4)_2$	10m	130	Sodium tungsten(VI) oxide hydrate, $\text{Na}_2\text{WO}_4 \cdot 2\text{H}_2\text{O}$	2m	33
Sodium hydrogen silicate hydrate, $\text{Na}_2\text{H}_2\text{SiO}_4 \cdot 4\text{H}_2\text{O}$	7m	163	Sodium zinc fluoride, NaZnF_3	6m	74
Sodium hydrogen sulfate hydrate, $\text{NaHSO}_4 \cdot \text{H}_2\text{O}$	9m	52	Sodium zinc sulfate hydrate, $\text{Na}_2\text{Zn}(\text{SO}_4)_2 \cdot 4\text{H}_2\text{O}$	6m	72
Sodium hydroxide, NaOH at 300 °C ..	4m	69	Sodium zirconium fluoride, $\text{Na}_7\text{Zr}_6\text{F}_{31}$	8m	144
Sodium iodate, NaIO_3	7	47	Strontium aluminum hydroxide, $\text{Sr}_3\text{Al}_2(\text{OH})_{12}$	10m	50
Sodium iodate, NaIO_4	7	48	Strontium aluminum oxide, $\text{Sr}_3\text{Al}_2\text{O}_6$	10m	52
Sodium iodide, NaI	4	31	Strontium arsenate, $\text{Sr}_3(\text{AsO}_4)_2$	2m	36
Sodium iron fluoride, Na_3FeF_6	9m	54	Strontium azide, $\text{Sr}(\text{N}_3)_2$	8m	146
Sodium lanthanum fluoride silicate, $(\text{Na}_2\text{La}_8)\text{F}_2(\text{SiO}_4)_6$	7m	64	Strontium borate, SrB_2O_4	3m	53
Sodium lanthanum molybdenum oxide, $\text{NaLa}(\text{MoO}_4)_2$	10m	49	Strontium borate, SrB_4O_7	4m	36
Sodium magnesium aluminum boron hydroxide silicate, dravite, $\text{NaMg}_3\text{Al}_6\text{B}_3(\text{OH})_4\text{Si}_6\text{O}_{27}$	3m	47	Strontium bromide fluoride, SrBrF ..	10m	54
Sodium magnesium carbonate (eitelite), $\text{Na}_2\text{Mg}(\text{CO}_3)_2$	11m	56	Strontium bromide hydrate, $\text{SrBr}_2 \cdot 6\text{H}_2\text{O}$	4	60
Sodium magnesium sulfate hydrate, bloedite, $\text{Na}_2\text{Mg}(\text{SO}_4)_2 \cdot 4\text{H}_2\text{O}$	6m	63	Strontium carbonate (strontianite), SrCO_3	3	56
			Strontium chloride, SrCl_2	4	40
			Strontium chloride fluoride, SrClF ..	10m	55
			Strontium chloride hydrate, $\text{SrCl}_2 \cdot 2\text{H}_2\text{O}$	11m	58
			Strontium chloride hydrate, $\text{SrCl}_2 \cdot 6\text{H}_2\text{O}$	4	58
			Strontium chloride hydroxide phosphate, $\text{Sr}_5\text{Cl}_{.65}(\text{OH})_{.35}(\text{PO}_4)_3$..	11m	60
			Strontium fluoride, SrF_2	5	67
			Strontium indium hydroxide, $\text{Sr}_3\text{In}_2(\text{OH})_{12}$	6m	76

CUMULATIVE INORGANIC INDEX - Continued

	Vol. or Sec.	Page		Vol. or Sec.	Page
Strontium iodide hydrate, $\text{SrI}_2 \cdot 6\text{H}_2\text{O}$	8	58	Thallium gallium sulfate hydrate, $\text{TlGa}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	6	57
Strontium manganese oxide, SrMnO_3 (cubic)	10m	56	Thallium(I) iodate, TlIO_3	8	62
Strontium manganese oxide, SrMnO_3 (hexagonal)	10m	58	Thallium(I) iodide, TlI (orthorhombic)	4	53
Strontium molybdenum oxide, SrMoO_4	7	50	Thallium iron sulfate hydrate, $\text{Tl}_2\text{Fe}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	8m	87
Strontium nitrate, $\text{Sr}(\text{NO}_3)_2$	12m	31	Thallium magnesium chromium oxide, $\text{Tl}_2\text{Mg}_2(\text{CrO}_4)_3$	8m	89
Strontium oxide, SrO	5	68	Thallium magnesium sulfate hydrate, $\text{Tl}_2\text{Mg}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	7m	74
Strontium oxide, SrO_2	6	52	Thallium manganese sulfate, $\text{Tl}_2\text{Mn}_2(\text{SO}_4)_3$	7m	76
Strontium oxide hydrate, $\text{SrO}_2 \cdot 8\text{H}_2\text{O}$	11m	61	Thallium nickel sulfate hydrate, $\text{Tl}_2\text{Ni}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	7m	78
Strontium phosphate, $\alpha\text{-Sr}_2\text{P}_2\text{O}_7$	11m	62	Thallium(I) nitrate, TlNO_3	6	58
Strontium phosphate, $\alpha\text{-Sr}_3(\text{PO}_4)_2$	11m	64	Thallium(III) oxide, Tl_2O_3	2	28
Strontium scandium oxide hydrate, $\text{Sr}_3\text{Sc}_2\text{O}_6 \cdot 6\text{H}_2\text{O}$	6m	78	Thallium(I) phosphate, Tl_3PO_4	7	58
Strontium sulfate (celestite), SrSO_4	2	61	Thallium(III) phosphate, TlPO_4	7	59
Strontium sulfide, SrS	7	52	Thallium platinum chloride, Tl_2PtCl_6	5	70
Strontium telluride, SrTe	4m	69	Thallium silicon fluoride, Tl_2SiF_6	6	56
Strontium tin oxide, SrSnO_3	8m	80	Thallium(I) sulfate, Tl_2SO_4	6	59
Strontium titanium oxide, SrTiO_3	3	44	Thallium(I) thiocyanate, TlCNS	8	63
Strontium tungsten oxide, SrWO_4	7	53	Thallium tin chloride, Tl_2SnCl_6	6	54
Strontium tungsten oxide, Sr_2WO_5	12m	32	Thallium(I) tungsten oxide, Tl_2WO_4	1m	48
Strontium zirconium oxide, SrZrO_3	9	51	Thallium zinc sulfate hydrate, $\text{Tl}_2\text{Zn}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	7m	80
Sulfamic acid, $\text{H}_2\text{NSO}_3\text{H}$	7	54	Thorium antimony, ThSb	4m	44
Sulfur, S (orthorhombic)	9	54	Thorium arsenide, ThAs	4m	70
Tantalum, Ta	1	29	Thorium cobalt, $\text{Th}_2\text{Co}_{17}$	12m	64
Tantalum silicide, TaSi_2	8	59	Thorium iron, $\text{Th}_2\text{Fe}_{17}$	12m	67
Tellurium, Te	1	26	Thorium oxide (thorianite), ThO_2	1	57
Tellurium(IV) oxide (paratellurite), TeO_2 (tetragonal)	7	56	Thulium antimony, TmSb	4m	45
Tellurium(IV) oxide, paratellurite, TeO_2 (tetragonal)	10	55	Thulium arsenate, TmAsO_4	3m	56
Tellurium(IV) oxide, tellurite, TeO_2 (orthorhombic)	9	57	Thulium arsenide, TmAs	4m	71
Terbium antimony, TbSb	5m	61	Thulium nitride, TmN	4m	71
Terbium arsenate, TbAsO_4	3m	54	Thulium oxide, Tm_2O_3	9	58
Terbium arsenide, TbAs	5m	75	Thulium silver, TmAg	5m	74
Terbium nitride, TbN	4m	70	Thulium telluride, TmTe	4m	72
Terbium phosphide, TbP	5m	76	Thulium vanadium oxide, TmVO_4	5m	57
Terbium selenide, TbSe	5m	76	Tin, $\alpha\text{-Sn}$ (cubic)	2	12
Terbium silver, TbAg	5m	74	Tin, $\beta\text{-Sn}$ (tetragonal)	1	24
Terbium sulfide, TbS	5m	77	Tin arsenide, SnAs	4m	37
Terbium telluride, TbTe	5m	77	Tin(II) fluoride, SnF_2	3m	51
Terbium vanadium oxide, TbVO_4	5m	56	Tin(IV) iodide, SnI_4	5	71
Thallium aluminum sulfate hydrate, $\text{TlAl}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	6	53	Tin(II) oxide, Sno	4	28
Thallium(I) arsenate, Tl_3AsO_4	2m	37	Tin(IV) oxide (cassiterite), SnO_2	1	54
Thallium azide, TlN_3	8m	82	Tin sulfide (berndtite), $\beta\text{-SnS}_2$	9m	57
Thallium(I) bromate, TlBrO_3	8	60	Tin(II) telluride, SnTe	7	61
Thallium bromide, TlBr	7	57	Titanium, Ti	3	1
Thallium cadmium sulfate, $\text{Tl}_2\text{Cd}_2(\text{SO}_4)_3$	8m	83	Titanium oxide (anatase), TiO_2	7m	82
Thallium(I) chlorate, TlClO_4	2m	38	Titanium oxide, brookite, TiO_2 (orthorhombic)	3m	57
Thallium(I) chlorate, TlClO_3	8	61	Titanium oxide (rutile), TiO_2	7m	83
Thallium(I) chloride, TlCl	4	51	Titanium(III) oxide, $\text{TiO}_{1.515}$	9	59
Thallium chromium oxide, Tl_2CrO_4	3m	54	Titanium silicide, Ti_5Si_3	8	64
Thallium chromium sulfate hydrate, $\text{TlCr}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	6	55	Titanium sulfide, TiS_2	4m	72
Thallium cobalt sulfate, $\text{Tl}_2\text{Co}_2(\text{SO}_4)_3$	8m	85	Titanium sulfide, Ti_2S	8m	149
Thallium cobalt sulfate hydrate, $\text{Tl}_2\text{Co}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	7m	70	Tungsten, W	1	28
Thallium copper sulfate hydrate, $\text{Tl}_2\text{Cu}(\text{SO}_4)_2 \cdot 6\text{H}_2\text{O}$	7m	72	Tungsten, W (reference standard)	8m	2

CUMULATIVE INORGANIC INDEX - Continued

	Vol. or Sec.	Page		Vol. or Sec.	Page
Vanadium, V	9m	58	Zinc fluoride, ZnF_2	6	60
Vanadium gold 3:1, V_3Au	6m	18	Zinc fluoride hydrate, $ZnF_2 \cdot 4H_2O$	11m	69
Vanadium iridium 3:1, V_3Ir	6m	21	Zinc germanium oxide, Zn_2GeO_4	10	56
Vanadium(V) oxide, V_2O_5	8	66	Zinc hydroxide silicate hydrate, hemimorphite, $Zn_4(OH)_2Si_2O_7 \cdot H_2O$...	2	62
Vanadium palladium 3:1, V_3Pd	6m	32	Zinc iodide, ZnI_2	9	60
Vanadium platinum 3:1, V_3Pt	6m	34	Zinc iron oxide (franklinite), $ZnFe_2O_4$	9m	60
Vanadium rhodium 3:1, V_3Rh	6m	56	Zinc manganese oxide (hetaerolite), $ZnMn_2O_4$	10m	61
Ytterbium antimony, $YbSb$	4m	45	Zinc molybdenum oxide, $Zn_2Mo_3O_8$	7m	173
Ytterbium arsenate, $YbAsO_4$	4m	38	Zinc nitrate hydrate, $\alpha-Zn(NO_3)_2 \cdot 6H_2O$	12m	36
Ytterbium arsenide, $YbAs$	4m	73	Zinc oxide (zincite), ZnO	2	25
Ytterbium gallium oxide, $Yb_3Ga_5O_{12}$	1m	49	Zinc selenide, $ZnSe$	3	23
Ytterbium nitride, YbN	4m	74	Zinc silicate (willemite), Zn_2SiO_4	7	62
Ytterbium oxide, Yb_2O_3	6m	80	Zinc silicon fluoride hydrate, $ZnSiF_6 \cdot 6H_2O$	8	70
Ytterbium selenide, $YbSe$	5m	79	Zinc sulfate (zinkosite), $ZnSO_4$	7	64
Ytterbium telluride, $YbTe$	5m	79	Zinc sulfate hydrate (goslarite), $ZnSO_4 \cdot 7H_2O$	8	71
Ytterbium(III) vanadium oxide, $YbVO_4$	5m	58	Zinc sulfide (wurtzite), $\alpha-ZnS$ (hexagonal)	2	14
Yttrium antimony, YSb	4m	46	Zinc sulfide (sphalerite), $\beta-ZnS$ (cubic)	2	16
Yttrium arsenate, $YASO_4$	2m	39	Zinc telluride, $ZnTe$	3m	58
Yttrium arsenide, YAs	4m	74	Zinc tin oxide, Zn_2SnO_4	10m	62
Yttrium gallium oxide, $Y_3Ga_5O_{12}$	1m	50	Zinc titanium oxide, Zn_2TiO_4	12m	37
Yttrium nickel, YNi_3	10m	123	Zinc tungsten oxide (sanmartinite), $ZnWO_4$	2m	40
Yttrium oxide, Y_2O_3	3	28	Zirconium, $\alpha-Zr$	2	11
Yttrium oxychloride, YOC_1	1m	51	Zirconium hydride, ZrH_2	5m	60
Yttrium phosphate (xenotime), YPO_4	8	67	Zirconium iodate, $Zr(IO_3)_4$	1m	51
Yttrium silver, YAg	5m	75	Zirconium nitride, ZrN	5m	80
Yttrium sulfide, YS	5m	80	Zirconium oxide, ZrO	5m	81
Yttrium telluride, YTe	4m	75	Zirconium phosphide, ZrP	4m	75
Yttrium titanium oxide, Y_2TiO_5	11m	113	Zirconium silicate, zircon, $ZrSiO_4$	4	68
Yttrium vanadium oxide, YVO_4	5m	59	Zirconium sulfate hydrate, $Zr(SO_4)_2 \cdot 4H_2O$	7	66
Zinc, Zn	1	16			
Zinc aluminum oxide (gahnite), $ZnAl_2O_4$	2	38			
Zinc ammine bromide, $Zn(NH_3)_2Br_2$..	11m	68			
Zinc ammine chloride, $Zn(NH_3)_2Cl_2$..	10m	59			
Zinc antimony oxide, $ZnSb_2O_4$	4m	39			
Zinc borate, ZnB_2O_4	1	83			
Zinc carbonate, smithsonite, $ZnCO_3$	8	69			
Zinc chromium oxide, $ZnCr_2O_4$	9m	59			
Zinc cobalt oxide, $ZnCo_2O_4$	10m	60			
Zinc cyanide, $Zn(CN)_2$	5	73			

CUMULATIVE ORGANIC INDEX

	Vol. or Sec.	Page		Vol. or Sec.	Page
4-Acetyl-2'-fluorodiphenyl, $C_{14}H_{11}FO$	8m	91	Nickel hexaimidazole nitrate, $Ni(C_3H_4N_2)_6(NO_3)_2$	7m	27
Alanine, L, $CH_3CHNH_2CO_2H$	8m	93	Nickel tetrapyrazole chloride, $Ni(C_3H_4N_2)_4Cl_2$	8m	44
Ammonium acetate, $NH_4 \cdot CH_3CO_2$	8m	95	Octahydro-1,3,5,7-tetranitro- 1,3,5,7-tetrazocene (α -HMX), $C_4H_8N_8O_8$	11m	100
Ammonium formate, NH_4HCO_2	11m	9	Octahydro-1,3,5,7-tetranitro- 1,3,5,7-tetrazocene (β -HMX), $C_4H_8N_8O_8$	11m	102
Ammonium oxalate hydrate (oxammitte), $(NH_4)_2C_2O_4 \cdot H_2O$	7	5	Palladium bis-(N-isopropyl-3-ethyl- salicylaldiminate), $Pd(C_{12}H_{16}NO)_2$	7m	144
Ammonium yttrium oxalate hydrate, $NH_4Y(C_2O_4)_2 \cdot H_2O$	8m	97	Pimelic acid, $(CH_2)_5(CO_2H)_2$	7m	153
Ascorbic acid, L- $C_6H_8O_6$	8m	99	Potassium formate-formic acid complex, $KO_2CH \cdot HO_2CH$	9m	93
Azobenzene, $C_6H_5NNC_6H_5$	7m	86	Potassium hydrogen o-phthalate, $C_6H_4(COOH)(COOK)$	4m	30
Cadmium hexaimidazole nitrate, $Cd(C_3H_4N_2)_6(NO_3)_2$	8m	23	Potassium oxalate hydrate, $K_2C_2O_4 \cdot H_2O$	9m	39
Calcium formate, $Ca(HCO_2)_2$	8	16	Potassium oxalate perhydrate, $K_2C_2O_4 \cdot H_2O_2$	9m	96
Calcium malate hydrate, $Ca(O_2C)_2(CH_2CHOH) \cdot 2H_2O$	10m	76	Reserpine, $C_{33}H_{40}N_2O_9$	8m	123
Cobalt acetate hydrate, $Co(C_2H_3O_2)_2 \cdot 4H_2O$	12m	19	Rubidium oxalate perhydrate, $Rb_2C_2O_4 \cdot H_2O_2$	9m	102
Copper glutamate hydrate, $Cu(O_2C)_2(H_2NCHCH_2CH_2) \cdot 2H_2O$	7m	110	Silver oxalate, $Ag_2C_2O_4$	9m	47
Copper tetrapyrazole chloride, $Cu(C_3H_4N_2)_4Cl_2$	8m	31	Sodium D-tartrate hydrate, $(CHOH-CO_2Na)_2 \cdot 2H_2O$	11m	110
Cysteine, L, $HSCH_2 \cdot CH(NH_2) \cdot COOH$	11m	86	Sodium oxalate, $Na_2C_2O_4$	6m	70
Dibenzoylmethane, $(C_6H_5CO)_2CH_2$	7m	115	Strontium formate, $Sr(CHO_2)_2$	8	55
bis-(o-Dodecacarborane), $C_4B_{20}H_{22}$..	6m	7	Strontium formate hydrate, $Sr(CHO_2)_2 \cdot 2H_2O$ (orthorhombic)	8	56
Glucose, D, α ,(dextrose), $C_6H_{12}O_6$..	11m	28	Sucrose, $C_{12}H_{22}O_{11}$	11m	66
Glyoxime, $H_2C_2(NOH)_2$	8m	102	Tartaric acid, D, $(CHOHCO_2H)_2$	7m	168
Hexamethylenediammonium adipate, $(CH_2)_4(CO_2H_3N)_2(CH_2)_6$	7m	121	Trimethylammonium chloride, $(CH_3)_3NHCl$	9m	113
Holmium ethylsulfate hydrate, $Ho[(C_2H_5)SO_4]_3 \cdot 9H_2O$	1m	18	2,4,6-Trinitrophenetole, $C_2H_5OC_6H_2(NO_2)_3$	8m	152
Hydroquinone, γ - HOC_6H_4OH	8m	107	Urea, $CO(NH_2)_2$	7	61
Iron oxalate hydrate (humboldtine), $FeC_2O_4 \cdot 2H_2O$	10m	24	Uric acid, $C_5H_4N_4O_3$	8m	154
Lead formate, $Pb(HCO_2)_2$	8	30	Zinc diimidazole chloride, $Zn(C_3H_4N_2)_2Cl_2$	7m	123
Lithium oxalate, $Li_2C_2O_4$	10m	34	Zinc glutamate hydrate, $Zn(O_2CCHNH_2CH_2CH_2CO_2) \cdot 2H_2O$	7m	170
Mercury o-phthalate, $C_6H_4(CO_2Hg)_2$..	10m	113			
Methyl sulfonanilide, $C_6H_5NSO_2CH_3$..	9m	78			
N-Methylphenazinium-7,7,8,8-tetra- cyanoquinodimethanide, $C_{25}H_{15}N_6$...	7m	146			
2-Naphthylamine, N-phenyl-, $C_{10}H_7NHC_6H_5$	6m	29			
Neodymium ethylsulfate hydrate, $Nd[(C_2H_5)SO_4]_3 \cdot 9H_2O$	9	41			

CUMULATIVE MINERAL INDEX

	Vol. or Sec.	Page		Vol. or Sec.	Page
Alabandite, MnS	4	11	Cryptohalite, $(\text{NH}_4)_2\text{SiF}_6$	5	5
Alum, $\text{KAl}(\text{SO}_4)_2 \cdot 12\text{H}_2\text{O}$	6	36	Cuprite, Cu_2O	2	23
Ammonia-niter, NH_4NO_3	7	4	*Diamond, C	2	5
Anatase, TiO_2	7m	82	*Diaspore, $\text{Al}_2\text{O}_3 \cdot \text{H}_2\text{O}$	3	41
Andradite, $\text{Ca}_3\text{Fe}_2\text{Si}_3\text{O}_{12}$	9	22	Diopside, $\text{CaMg}(\text{SiO}_3)_2$	5m	17
Anglesite, PbSO_4	3	67	*Dravite, $\text{NaMg}_3\text{Al}_6\text{B}_3\text{Si}_6\text{O}_{27}(\text{OH})_4$	3m	47
Anhydrite, CaSO_4	4	65	Eitelite, $\text{Na}_2\text{Mg}(\text{CO}_3)_2$	11m	56
Antimony, Sb	3	14	Elpasolite, K_2NaAlF_6	9m	43
Antarcticcite, $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$	12m	16	*Enstatite, MgSiO_3	6	32
Aphthitalite, $\text{K}_3\text{Na}(\text{SO}_4)_2$	6m	52	Epsomite, $\text{MgSO}_4 \cdot 7\text{H}_2\text{O}$	7	30
Aragonite, CaCO_3	3	53	Eschynite, CeNbTiO_6	3m	24
Arcanite, K_2SO_4	3	62	Eskolaite, Cr_2O_3	5	22
Argentite, Ag_2S	10	51	Ettringite, $\text{Ca}_6\text{Al}_2\text{S}_3\text{O}_{18} \cdot 31\text{H}_2\text{O}$	8	3
Arsenic, As	3	6	Fairchildite, $\text{K}_2\text{Ca}(\text{CO}_3)_2$	8m	48
Arsenolite, As_2O_3	1	51	Fluorapatite, $\text{Ca}_5\text{F}(\text{PO}_4)_3$	3m	22
Aurostibite, AuSb_2	7	18	Fluorite, CaF_2	1	69
*Azurite, $\text{Cu}_3(\text{OH})_2(\text{CO}_3)_2$	10	30	Forsterite, Mg_2SiO_4	1	83
Barite, BaSO_4	10m	12	Franklinite, ZnFe_2O_4	9m	60
Berlinite, AlPO_4	10	3	Fresnoite, $\text{Ba}_2\text{TiSi}_2\text{O}_8$	9m	14
Berndtite, SnS_2	9m	57	Gahnite, ZnAl_2O_4	2	38
*Beryl, $\text{Be}_3\text{Al}_2(\text{SiO}_3)_6$	9	13	Galaxite, MnAl_2O_4	9	35
Bischofite, $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$	11m	37	Galena, PbS	2	18
Bismite, $\alpha\text{-Bi}_2\text{O}_3$	3m	17	Geikielite, MgTiO_3	5	43
Bismoclite, BiOCl	4	54	Gersdorffite, NiAsS	1m	35
Bismuth, Bi	3	20	Glaserite, $\text{K}_3\text{Na}(\text{SO}_4)_2$	6m	52
Bismuthinite, Bi_2S_3	5m	13	Glauberite, $\text{Na}_2\text{Ca}(\text{SO}_4)_2$	6m	59
*Bloedite, $\text{Na}_2\text{Mg}(\text{SO}_4)_2 \cdot 4\text{H}_2\text{O}$	6m	63	Gold, Au	1	33
Böhmite, $\text{Al}_2\text{O}_3 \cdot \text{H}_2\text{O}$	3	38	Goslarite, $\text{ZnSO}_4 \cdot 7\text{H}_2\text{O}$	8	71
Bromellite, BeO	1	36	Greenockite, CdS	4	15
Bromyrite, AgBr	4	46	*Groutite, MnO(OH)	11m	97
*Brookite, TiO_2	3m	57	Halite, NaCl	2	41
Brucite, Mg(OH)_2	6	30	Hausmannite, Mn_3O_4	10m	38
Bunsenite, NiO	1	47	*Hemimorphite, $\text{Zn}_{n_4}(\text{OH})_2\text{Si}_2\text{O}_7 \cdot \text{H}_2\text{O}$	2	62
Burkeite, $\text{Na}_6\text{CO}_3(\text{SO}_4)_2$	11m	52	Hetaerolite, ZnMn_2O_4	10m	61
*Butlerite, $\text{FeSO}_4(\text{OH}) \cdot 2\text{H}_2\text{O}$	10m	95	Hieratite, K_2SiF_6	5	50
Calcite, CaCO_3	2	51	Huebnerite, MnWO_4	2m	24
Calomel, Hg_2Cl_2	1	72	Humboldtine, $\text{FeC}_2\text{O}_4 \cdot 2\text{H}_2\text{O}$	10m	24
Carnallite, $\text{KMgCl}_3 \cdot 6\text{H}_2\text{O}$	8m	50	Humite, $3\text{Mg}_2\text{SiO}_4 \cdot \text{MgF}_2$	1m	30
Cassiterite, SnO_2	1	54	Hydrophilite, CaCl_2	11m	18
Celestite, SrSO_4	2	61	Iodrite, AgI	8	51
Cerargyrite, AgCl	4	44	Iron, $\alpha\text{-Fe}$	4	3
Cerianite, CeO_2	1	56	Jacobsite, MnFe_2O_4	9	36
Cerussite, PbCO_3	2	56	*Julgoldite, $\text{Ca}_2\text{Fe}_3\text{Si}_3\text{O}_{10}(\text{OH},\text{O})_2(\text{OH})_2$	10m	72
Cervantite, Sb_2O_4	10	8	Langbeinite, $\text{K}_2\text{Mg}_2(\text{SO}_4)_3$	6m	40
Chalcocyanite, CuSO_4	3m	29	Lead, Pb	1	34
Chloraluminite, $\text{AlCl}_2 \cdot 6\text{H}_2\text{O}$	7	3	*Leucophanite, $\text{NaCaBeSi}_2\text{O}_6$	8m	138
Chlorocalcite, KCaCl_3	7m	36	Litharge, PbO (red)	2	30
Chloromagnesite, MgCl_2	11m	94	Lithiphosphate, Li_3PO_4	4m	21
Chrysoberyl, BeAl_2O_4	9	10	Loellingite, FeAs_2	10	34
Cinnabar, HgS	4	17	Magnesite, MgCO_3	7	28
*Claudetite, As_2O_3	3m	9	Magnetite, Fe_3O_4	5m	31
Clausthalite, PbSe	5	38	Malachite, $\text{Cu}_2(\text{OH})_2\text{CO}_3$	10	31
Copper, Cu	1	15	Manganolangbeinite, $\text{K}_2\text{Mn}_2(\text{SO}_4)_3$	6m	43
Cordierite, $\text{Mg}_2\text{Al}_4\text{Si}_5\text{O}_{18}$ (hexagonal)	1m	29	Manganosite, MnO	5	45
Cordierite, $\text{Mg}_2\text{Al}_4\text{Si}_5\text{O}_{18}$ (orthorhombic)	1m	28	Marshite, CuI	4	38
Corundum, Al_2O_3	9	3	Mascagnite, $(\text{NH}_4)_2\text{SO}_4$	9	8
Cotunnite, PbCl_2	12m	23	Massicot, PbO (yellow)	2	32
Covellite, CuS	4	13	Matlockite, PbFCl	1	76
Cristobalite (α or low) SiO_2	10	48	Melanterite, $\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$	8m	38
Cristobalite (β or high) SiO_2	1	42	*Meliphanite, $\text{Na}_{.63}\text{Ca}_{1.37}\text{BeAl}_{.13}\text{Si}_{1.87}\text{O}_{6.25}\text{F}_{.75}$	8m	135
*Cryolithionite, $\text{Li}_3\text{Na}_3\text{Al}_2\text{F}_{12}$	9m	23	Metaborite, HBO_2 (cubic)	4m	27
			Metacinnabar, HgS	4	21
			Miargyrite, AgSbS_2	5m	49
			*Millerite, NiS	1m	37

*Natural mineral.

CUMULATIVE MINERAL INDEX - Continued

	Vol. or Sec.	Page		Vol. or Sec.	Page
Minium, Pb_3O_4	8	32	Silver, Ag (reference standard)	8m	2
Mitscherlichite, $K_2CuCl_4 \cdot 2H_2O$	9m	34	*Sjögrenite, $Mg_6Fe_2CO_3(OH)_{16} \cdot 4H_2O$, phase I	10m	103
Molybdenite, MoS_2	5	47	Skutterudite, $CoAs_3$	10	21
Molybdite, MoO_3	3	30	*Smithsonite, $ZnCO_3$	8	69
Montroydite, HgO	9	39	*Sodalite, $Na_8Si_6Al_6O_{24}Cl_2$	7m	158
Mullite, $Al_6Si_2O_{13}$	3m	3	Soda-niter, $NaNO_3$	6	50
Nantokite, $CuCl$	4	35	Sphalerite, ZnS	2	16
*Newberryite, $MgHPO_4 \cdot 3H_2O$	7m	139	Spherocobaltite, $CoCO_3$	10	24
Niter, KNO_3	3	58	Spinel, $MgAl_2O_4$	9m	25
Nitrobarite, $Ba(NO_3)_2$	11m	14	Stibnite, Sb_2S_3	5	6
Norbergite, $Mg_2SiO_4 \cdot MgF_2$	10	39	Stolzite, $PbWO_4$	5m	34
Oldhamite, CaS	7	15	Strontianite, $SrCO_3$	3	56
Otavite, $CdCO_3$	7	11	Struvite, $MgNH_4PO_4 \cdot 6H_2O$	3m	41
Oxammite, $(NH_4)_2C_2O_4 \cdot H_2O$	7	5	Sulfur, S (orthorhombic)	9	54
Palladium, Pd	1	21	Sylvite, KCl	1	65
*Paratellurite, TeO_2	10	55	Tantalum, Ta	1	29
Paratellurite, TeO_2	7	56	Tellurium, Te	1	26
Partridgeite, $\alpha\text{-Mn}_2O_3$	11m	95	*Tellurite, TeO_2	9	57
Periclase, MgO	1	37	Tellurobismuthite, Bi_2Te_3	3m	16
Perovskite, $CaTiO_3$	9m	17	Tenorite, CuO	1	49
*Phenacite, Be_2SiO_4	8	11	Teschemacherite, NH_4HCO_3	9	5
Picrochromite, $MgCr_2O_4$	9	34	Thenardite, Na_2SO_4	2	59
Picromerite, $K_2Mg(SO_4)_2 \cdot 6H_2O$	8m	54	Thermonatrite, $Na_2CO_3 \cdot H_2O$	8	54
*Pirssonite, $Na_2Ca(CO_3)_2 \cdot 2H_2O$	9m	106	*Thomsenolite, $NaCaAlF_6 \cdot H_2O$	8m	132
Platinum, Pt	1	31	Thorianite, ThO_2	1	57
Portlandite, $Ca(OH)_2$	1	58	Thortveitite, $Sc_2Si_2O_7$	7m	58
Powellite, $CaMoO_4$	6	22	Tiemannite, $HgSe$	7	35
Pyrargyrite, Ag_3SbS_3	5m	51	Tin, $\alpha\text{-Sn}$ (cubic)	2	12
Pyrite, FeS_2	5	29	Tin, $\beta\text{-Sn}$ (tetragonal)	1	24
*Pyroaurite, $Mg_6Fe_2CO_3(OH)_{16} \cdot 4H_2O$, phase II	10m	104	*Topaz, $Al_2SiO_4(F, OH)_2$	1m	4
Pyrolusite, $\beta\text{-MnO}_2$	10m	39	Trevorite, $NiFe_2O_4$	10	44
Pyrope, $Mg_3Al_2(SiO_4)_3$	4m	24	Tschermigite, $NH_4Al(SO_4)_2 \cdot 12H_2O$	6	3
*Quartz, SiO_2 (α or low)	3	24	Tungstenite, WS_2	8	65
Rammelsbergite, $NiAs_2$	10	42	Uraninite, UO_2	2	33
Retgersite, $NiSO_4 \cdot 6H_2O$	7	36	Uvarovite, $Ca_3Cr_2(SiO_4)_3$	10	17
Rhodochrosite, $MnCO_3$	7	32	*Valentinitite, Sb_2O_3	10	6
Rutile, TiO_2	7m	83	Villaumite, NaF	1	63
Safflorite, $CoFeAs_4$	10	28	Willemite, Zn_2SiO_4	7	62
Sal-ammoniac, NH_4Cl	1	59	Witherite, $BaCO_3$	2	54
Sanmartinite, $ZnWO_4$	2m	40	Wulfenite, $PbMoO_4$	7	23
Scacchite, $MnCl_2$	8m	43	Wurtzite, ZnS	2	14
*Scheelite, $CaWO_4$	6	23	*Xanthoconite, Ag_3AsS_3	8m	126
Selenium, Se	5	54	Xenotime, YPO_4	8	67
Selenolite, SeO_2	7m	60	Zinc, Zn	1	16
Sellaite, MgF_2	4	33	Zincite, ZnO	2	25
Senarmontite, Sb_2O_3	3	31	Zinkosite, $ZnSO_4$	7	64
Silver, Ag	1	23	*Zircon, $ZrSiO_4$	4	68

U.S. DEPT. OF COMM. BIBLIOGRAPHIC DATA SHEET		1. PUBLICATION OR REPORT NO. NBS-MN 25, Section 12	2. Gov't Accession No.	3. Recipient's Accession No.
4. TITLE AND SUBTITLE Standard X-ray Diffraction Powder Patterns Section 12 - Data for 57 Substances		5. Publication Date February 1975		
		6. Performing Organization Code		
7. AUTHOR(S) Howard F. McMurdie, Marlene C. Morris, Eloise H. Evans, Boris Paretzkin, Johan H. de Groot, Camden R. Hubbard and Simon J. Carmel		8. Performing Organ. Report No.		
9. PERFORMING ORGANIZATION NAME AND ADDRESS NATIONAL BUREAU OF STANDARDS DEPARTMENT OF COMMERCE WASHINGTON, D.C. 20234		10. Project/Task/Work Unit No. 3130163		
		11. Contract/Grant No.		
12. Sponsoring Organization Name and Complete Address (Street, City, State, ZIP) Same as Item 9.		13. Type of Report & Period Covered Interim		
		14. Sponsoring Agency Code		

15. SUPPLEMENTARY NOTES

Library of Congress Catalog Card Number: 53-61386

16. ABSTRACT (A 200-word or less factual summary of most significant information. If document includes a significant bibliography or literature survey, mention it here.)

Standard x-ray diffraction patterns are presented for 57 substances. Twenty-five of these patterns represent experimental data and 32 are calculated. The experimental x-ray powder diffraction patterns were obtained with an x-ray diffractometer. All d-values were assigned Miller indices determined by comparison with computed interplanar spacings consistent with space group extinctions. The densities and lattice constants were calculated, and the refractive indices were measured whenever possible. The calculated x-ray powder diffraction patterns were computed from published crystal structure data. Both peak height and integrated intensities are reported for the calculated patterns.

17. KEY WORDS (six to twelve entries; alphabetical order; capitalize only the first letter of the first key word unless a proper name; separated by semicolons)			
Crystal structure; integrated intensities; lattice constants; peak intensities; powder patterns; reference intensities; standard; x-ray diffraction.			
18. AVAILABILITY	<input checked="" type="checkbox"/> Unlimited <input type="checkbox"/> For Official Distribution. Do Not Release to NTIS <input checked="" type="checkbox"/> Order From Sup. of Doc., U.S. Government Printing Office Washington, D.C. 20402, SD Cat. No. C13. 44:25 / Sec. 12 <input type="checkbox"/> Order From National Technical Information Service (NTIS) Springfield, Virginia 22151	19. SECURITY CLASS (THIS REPORT)	21. NO. OF PAGES
		UNCLASSIFIED	90
		20. SECURITY CLASS (THIS PAGE)	22. Price
		UNCLASSIFIED	\$1.50

NBS TECHNICAL PUBLICATIONS

PERIODICALS

JOURNAL OF RESEARCH reports National Bureau of Standards research and development in physics, mathematics, and chemistry. It is published in two sections, available separately:

• **Physics and Chemistry (Section A)**

Papers of interest primarily to scientists working in these fields. This section covers a broad range of physical and chemical research, with major emphasis on standards of physical measurement, fundamental constants, and properties of matter. Issued six times a year. Annual subscription: Domestic, \$17.00; Foreign, \$21.25.

• **Mathematical Sciences (Section B)**

Studies and compilations designed mainly for the mathematician and theoretical physicist. Topics in mathematical statistics, theory of experiment design, numerical analysis, theoretical physics and chemistry, logical design and programming of computers and computer systems. Short numerical tables. Issued quarterly. Annual subscription: Domestic, \$9.00; Foreign, \$11.25.

DIMENSIONS/NBS (formerly Technical News Bulletin)—This monthly magazine is published to inform scientists, engineers, businessmen, industry, teachers, students, and consumers of the latest advances in science and technology, with primary emphasis on the work at NBS. The magazine highlights and reviews such issues as energy research, fire protection, building technology, metric conversion, pollution abatement, health and safety, and consumer product performance. In addition, it reports the results of Bureau programs in measurement standards and techniques, properties of matter and materials, engineering standards and services, instrumentation, and automatic data processing.

Annual subscription: Domestic, \$9.45; Foreign, \$11.85.

NONPERIODICALS

Monographs—Major contributions to the technical literature on various subjects related to the Bureau's scientific and technical activities.

Handbooks—Recommended codes of engineering and industrial practice (including safety codes) developed in cooperation with interested industries, professional organizations, and regulatory bodies.

Special Publications—Include proceedings of conferences sponsored by NBS, NBS annual reports, and other special publications appropriate to this grouping such as wall charts, pocket cards, and bibliographies.

Applied Mathematics Series—Mathematical tables, manuals, and studies of special interest to physicists, engineers, chemists, biologists, mathematicians, computer programmers, and others engaged in scientific and technical work.

National Standard Reference Data Series—Provides quantitative data on the physical and chemical properties of materials, compiled from the world's literature and critically evaluated. Developed under a world-wide

program coordinated by NBS. Program under authority of National Standard Data Act (Public Law 90-396).

NOTE: At present the principal publication outlet for these data is the **Journal of Physical and Chemical Reference Data (JPCRD)** published quarterly for NBS by the American Chemical Society (ACS) and the American Institute of Physics (AIP). Subscriptions, reprints, and supplements available from ACS, 1155 Sixteenth St. N. W., Wash. D. C. 20056.

Building Science Series—Disseminates technical information developed at the Bureau on building materials, components, systems, and whole structures. The series presents research results, test methods, and performance criteria related to the structural and environmental functions and the durability and safety characteristics of building elements and systems.

Technical Notes—Studies or reports which are complete in themselves but restrictive in their treatment of a subject. Analogous to monographs but not so comprehensive in scope or definitive in treatment of the subject area. Often serve as a vehicle for final reports of work performed at NBS under the sponsorship of other government agencies.

Voluntary Product Standards—Developed under procedures published by the Department of Commerce in Part 10, Title 15, of the Code of Federal Regulations. The purpose of the standards is to establish nationally recognized requirements for products, and to provide all concerned interests with a basis for common understanding of the characteristics of the products. NBS administers this program as a supplement to the activities of the private sector standardizing organizations.

Federal Information Processing Standards Publications (FIPS PUBS)—Publications in this series collectively constitute the **Federal Information Processing Standards Register**. Register serves as the official source of information in the Federal Government regarding standards issued by NBS pursuant to the Federal Property and Administrative Services Act of 1949 as amended, Public Law 89-306 (79 Stat. 1127), and as implemented by Executive Order 11717 (38 FR 12315, dated May 11, 1973) and Part 6 of Title 15 CFR (Code of Federal Regulations).

Consumer Information Series—Practical information, based on NBS research and experience, covering areas of interest to the consumer. Easily understandable language and illustrations provide useful background knowledge for shopping in today's technological marketplace.

NBS Interagency Reports (NBSIR)—A special series of interim or final reports on work performed by NBS for outside sponsors (both government and non-government). In general, initial distribution is handled by the sponsor; public distribution is by the National Technical Information Service (Springfield, Va. 22161) in paper copy or microfiche form.

Order NBS publications (except NBSIR's and Bibliographic Subscription Services) from: Superintendent of Documents, Government Printing Office, Washington, D.C. 20402.

BIBLIOGRAPHIC SUBSCRIPTION SERVICES

The following current-awareness and literature-survey bibliographies are issued periodically by the Bureau:
Cryogenic Data Center Current Awareness Service

A literature survey issued weekly. Annual subscription: Domestic, \$20.00; foreign, \$25.00.

Liquefied Natural Gas. A literature survey issued quarterly. Annual subscription: \$20.00.

Superconducting Devices and Materials. A literature

survey issued quarterly. Annual subscription: \$20.00. Send subscription orders and remittances for the preceding bibliographic services to National Technical Information Service, Springfield, Va. 22161.

Electromagnetic Metrology Current Awareness Service
Issued monthly. Annual subscription: \$100.00 (Special rates for multi-subscriptions). Send subscription order and remittance to Electromagnetics Division, National Bureau of Standards, Boulder, Colo. 80302.

U.S. DEPARTMENT OF COMMERCE
National Bureau of Standards
Washington, D.C. 20234

OFFICIAL BUSINESS

Penalty for Private Use, \$300

POSTAGE AND FEES PAID
U.S. DEPARTMENT OF COMMERCE
COM-215

Fourth Class Mail



Off of Cong Rel's
Room 5835
NEW PUB

