



A11106 395974

NIST
PUBLICATIONS




United States Department of Commerce
Technology Administration
National Institute of Standards and Technology

NIST Special Publication 945

Guide to the Nomenclature of Particle Dispersion Technology for Ceramic Systems

Vincent A. Hackley

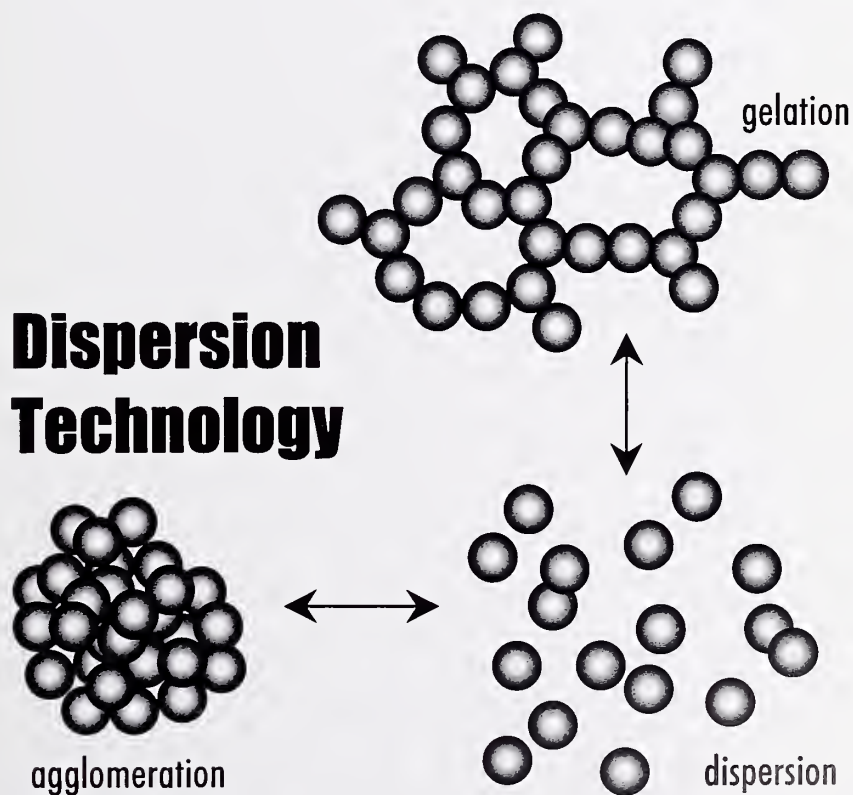

C
00
57
0.945
0000

The National Institute of Standards and Technology was established in 1988 by Congress to "assist industry in the development of technology . . . needed to improve product quality, to modernize manufacturing processes, to ensure product reliability . . . and to facilitate rapid commercialization . . . of products based on new scientific discoveries."

NIST, originally founded as the National Bureau of Standards in 1901, works to strengthen U.S. industry's competitiveness; advance science and engineering; and improve public health, safety, and the environment. One of the agency's basic functions is to develop, maintain, and retain custody of the national standards of measurement, and provide the means and methods for comparing standards used in science, engineering, manufacturing, commerce, industry, and education with the standards adopted or recognized by the Federal Government.

As an agency of the U.S. Commerce Department's Technology Administration, NIST conducts basic and applied research in the physical sciences and engineering, and develops measurement techniques, test methods, standards, and related services. The Institute does generic and precompetitive work on new and advanced technologies. NIST's research facilities are located at Gaithersburg, MD 20899, and at Boulder, CO 80303. Major technical operating units and their principal activities are listed below. For more information contact the Publications and Program Inquiries Desk, 301-975-3058.

Office of the Director

- National Quality Program
- International and Academic Affairs

Technology Services

- Standards Services
- Technology Partnerships
- Measurement Services
- Technology Innovation
- Information Services

Advanced Technology Program

- Economic Assessment
- Information Technology and Applications
- Chemical and Biomedical Technology
- Materials and Manufacturing Technology
- Electronics and Photonics Technology

Manufacturing Extension Partnership Program

- Regional Programs
- National Programs
- Program Development

Electronics and Electrical Engineering Laboratory

- Microelectronics
- Law Enforcement Standards
- Electricity
- Semiconductor Electronics
- Electromagnetic Fields¹
- Electromagnetic Technology¹
- Optoelectronics¹

Chemical Science and Technology Laboratory

- Biotechnology
- Physical and Chemical Properties²
- Analytical Chemistry
- Process Measurements
- Surface and Microanalysis Science

Physics Laboratory

- Electron and Optical Physics
- Atomic Physics
- Optical Technology
- Ionizing Radiation
- Time and Frequency¹
- Quantum Physics¹

Materials Science and Engineering Laboratory

- Intelligent Processing of Materials
- Ceramics
- Materials Reliability¹
- Polymers
- Metallurgy
- NIST Center for Neutron Research

Manufacturing Engineering Laboratory

- Precision Engineering
- Automated Production Technology
- Intelligent Systems
- Fabrication Technology
- Manufacturing Systems Integration

Building and Fire Research Laboratory

- Structures
- Building Materials
- Building Environment
- Fire Safety Engineering
- Fire Science

Information Technology Laboratory

- Mathematical and Computational Sciences²
- Advanced Network Technologies
- Computer Security
- Information Access and User Interfaces
- High Performance Systems and Services
- Distributed Computing and Information Services
- Software Diagnostics and Conformance Testing
- Statistical Engineering

¹At Boulder, CO 80303.

²Some elements at Boulder, CO.

Guide to the Nomenclature of Particle Dispersion Technology for Ceramic Systems

Vincent A. Hackley

Ceramics Division
Materials Science and Engineering Laboratory
National Institute of Standards and Technology
Gaithersburg, MD 20899-8520

February 2000



U.S. DEPARTMENT OF COMMERCE

William M. Daley, Secretary

TECHNOLOGY ADMINISTRATION

Dr. Cheryl L. Shavers, Under Secretary of Commerce for Technology

NATIONAL INSTITUTE OF STANDARDS AND TECHNOLOGY

Raymond G. Kammer, Director

National Institute of Standards and Technology Special Publication 945
Natl. Inst. Stand. Technol. Spec. Publ. 945, 24 pages (February 2000)
CODEN: NSPUE2

U.S. GOVERNMENT PRINTING OFFICE
WASHINGTON: 2000

For sale by the Superintendent of Documents, U.S. Government Printing Office
Washington, DC 20402-9325

Preface

It is generally agreed that measurements and standards play an integral role in the manufacture of ceramic materials. They enhance reliability by providing a basis for quantifying and comparing material properties during each phase of the manufacturing process, from raw materials to the finished product. Equally important is the establishment of a uniform and widely accepted nomenclature to permit the efficient exchange of scientific and technical information, and to provide a sound basis on which to standardize measurement methods and data reporting practices.

In June 1997, NIST established the Ceramic Processing Characterization Council (CPCC)[†] to assist the U.S. ceramics industry in the development of measurements and standards infrastructure. The CPCC is a voluntary, cooperative program among NIST, universities, private companies, other government research laboratories and private sector laboratories. A principal goal of the consortium is to develop guidelines and recommended practices for the implementation of process measurements. Within the CPCC, the Dispersion & Rheology Working Group (DRWG) is responsible for addressing those measurement issues associated with particulates in liquid media. DRWG members quickly recognized the fundamental importance of terminology to any measurement-based strategy, and subsequently initiated a project to develop a uniform nomenclature for dispersion systems.

An ad hoc committee was formed, whose members included J.H. Adair (Penn State), J.A. Casey (IBM), R.A. Condrate (Alfred), M. Frey (3M), V.A. Hackley (NIST), W. Hunt (3M), A. Jillavenkatesa (NIST), M.J. Mayo (Penn State), G.Y. Onoda (NIST), P. Somasundaran (Columbia), and T. Wood (3M). The committee was charged with reviewing the technical content and language of the nomenclature, which I had volunteered to compile. Several revisions were passed through the committee before a draft version was circulated for comment by CPCC members at large. In addition to the committee review, two distinguished authorities in the particle science field, Bob Hunter at the University of Sydney and George Scherer at Princeton, were invited to review the nomenclature and provide input according to their respective areas of expertise. Their help is gratefully acknowledged.

In compiling this nomenclature, every effort was made to maintain a degree of uniformity with existing standards and conventions. To this end, the cooperation of the American Chemical Society and the International Union on Pure and Applied Chemistry (IUPAC) were instrumental.

To help put this nomenclature into practice, I have prepared this special publication. It is my general hope that it will serve as a resource to those working in particle dispersion applications, particularly in the ceramic sciences. It is my further hope that this document will serve to promote the establishment of a commonly recognized system of terminology throughout the ceramics community.

[†] Formally known as the Ceramic Processing Characterization Consortium.

Table of Contents

PREFACE	<i>iii</i>
1. INTRODUCTION	1
2. DEFINITIONS	1
2.1 PHYSICAL DESCRIPTION OF DISPERSED SYSTEMS	1
RELATED TERMS	2
RECOMMENDATIONS	3
2.2 STATES OF SUBDIVISION (DISPERSED PHASE)	3
DEFINITIONS BASED ON SIZE	3
DEFINITIONS BASED ON STRUCTURE	3
RELATED TERMS	4
RECOMMENDATIONS	5
2.3 ASSOCIATION AND DISSOCIATION PROCESSES	5
ASSOCIATION PROCESSES	5
DISSOCIATION PROCESSES	6
RELATED TERMS	6
RECOMMENDATIONS	7
2.4 DISPERSION STABILITY	7
STATES OF STABILITY	7
STABILITY MECHANISMS	7
INTERACTION TERMS	8
RELATED TERMS	9
RECOMMENDATIONS	10
2.5 INTERFACIAL AND ELECTROKINETIC PROPERTIES	10
THE INTERFACE	10
ADSORPTION PROCESSES	11
ELECTRICAL PROPERTIES	12
ELECTROKINETIC EFFECTS	13
RELATED TERMS	14
3. BIBLIOGRAPHY	16
3.1 PRIMARY SOURCES	16
3.2 SECONDARY SOURCES	16
ACKNOWLEDGEMENTS	17
LIST OF REVIEWERS AND CONTRIBUTORS	17
INDEX TO DEFINED TERMS	18

GUIDE TO THE NOMENCLATURE OF PARTICLE DISPERSION TECHNOLOGY FOR CERAMIC SYSTEMS

1. INTRODUCTION

The use of nomenclature for identifying dispersed particle systems, along with their associated properties and components, is often inconsistent and subject to misinterpretation in the ceramic and materials science literature. For example, terms for describing the state of association of particles in suspension (e.g., *aggregate* or *agglomerate*) often carry specific connotations that vary among different authors. In an attempt to standardize usage of dispersion terminology, and as a resource for researchers, engineers and students, an internally consistent system of nomenclature has been developed. In compiling definitions, a variety of sources were examined, including IUPAC¹ recommendations, current and draft ASTM² and ISO³ standards, and published materials drawn from both the ceramic and the more general colloid and interface science literature (*see the bibliography for a complete list of primary and secondary sources*).

Definitions have been written first and foremost to serve those people in the ceramics field, but should be of equal utility to those involved in a broad range of dispersion-based non-ceramic applications. This is not, nor is it intended to be, an exhaustive compilation. Rather, this document focuses on commonly encountered terms, and endeavors to provide a consistent

framework for improved technical communication.

The terms are organized into five subsections, each dealing with a specific aspect of dispersion: (1) physical description of dispersed systems; (2) states of subdivision; (3) association and disassociation processes; (4) dispersion stability; and (5) interfacial and electrokinetic properties. Acceptable alternative expressions and common abbreviations are shown in parentheses adjacent to the defined term. In general, the American Chemical Society's formalism for abbreviations has been adopted here.⁴

In some cases, a definition may have two parts; one more general in context and the other more specific to ceramic applications. Recommendations are also provided, for instance, regarding the discontinuance of terms deemed ambiguous or obsolete, and are presented at the end of each subsection. Within each definition, separately defined terms are identified in *italics* at their first occurrence. In addition, an alphabetized index to defined terms is provided.

2. DEFINITIONS

2.1 Physical Description of Dispersed Systems

Aerosol

Droplets or *particles* dispersed in a gaseous phase.

¹ International Union on Pure and Applied Chemistry

² American Society for Testing and Materials

³ International Organization for Standardization

⁴ The ACS Style Guide, 2nd Edition, 1997.

Continuous Phase

Constituting the *dispersion* medium, a phase that exhibits continuity throughout the dispersion; e.g., the liquid in a *suspension*.

Dispersed Phase (Discontinuous Phase)

In a *dispersion*, the phase that is distributed in the form of discrete discontinuities (*particles*, *droplets* or *bubbles*), in a second immiscible phase that is continuous.

Dispersion

In general, a two-phase system in which discontinuities of any kind (solid, liquid, gas) are dispersed in a *continuous phase* of a different composition or state; more specifically in the field of ceramics, the term dispersion is used to describe a *suspension* of solid *particles* in a liquid medium.

Emulsion

A *dispersion* consisting of two or more liquid phases.

Hydrosol

A *sol* in which water forms the *dispersion* medium.

Liquid Phase

Consisting of a condensed fluid; e.g., the *dispersion* medium in a *suspension*.

Organosol

A *sol* in which an organic liquid forms the *dispersion* medium.

Particulate Phase (Solid Phase)

The particles in a *suspension*, *gel*, or *aerosol*.

Slip

A term that refers to a *suspension* prepared for the expressed purpose of

consolidating the *solid phase* (e.g., by slip-casting, tape-casting, or spray drying).

Slurry

A concentrated ceramic particulate *suspension*.

Sol

A liquid *dispersion* containing particles of *colloidal* dimensions.

Suspension

A liquid in which solid particles are dispersed.

Related Terms

Heterodisperse

Describes a *polydisperse* particulate system in which more than one discrete size distribution mode occurs; e.g., bimodal, trimodal, etc.

Monodisperse

Realistically, all *dispersions* exhibit a finite spread in their *particle* size distribution. In practice, the term monodisperse can be used to identify a dispersed system in which all particles are of nearly the same size, forming a narrow (unimodal) distribution about an average value. Numerically, a dispersion may be considered monodisperse if 90% of the distribution (1.645σ , where σ is the standard deviation of the size distribution) lies within $\pm 5\%$ of the average size, $\langle d \rangle$:

$$\frac{1.645\sigma}{\langle d \rangle} \leq 0.05$$

Polydisperse

Describes a dispersed system in which many *particle* sizes occur. In practice, a system may be considered polydisperse if

less than 90% of the size distribution (1.645σ , where σ is the standard deviation of the size distribution) lies within $\pm 5\%$ of the average size, $\langle d \rangle$:

$$\frac{1.645\sigma}{\langle d \rangle} > 0.05$$

Well-Dispersed

A term used to describe a *stable suspension* in which the *minimum particle size* has been achieved.

Recommendations

Relative Concentration Terms

It is recommended that relative descriptive terms relating to particle concentration in *suspension* (e.g., dilute or concentrated) be defined in such a manner that the reader has a clear understanding of their relevance to the measurement or application at hand. For instance, in a light scattering measurement, "dilute" may infer the absence of multiple scattering, whereas in an ultrasonic measurement this term may imply a linear response with concentration. These conditions may vary by several orders of magnitude with respect to particle concentration. Concentration can also be defined on a more fundamental basis, taking into consideration the relative dominance of thermal, hydrodynamic, or surface forces in controlling suspension properties.

2.2 States of Subdivision (Dispersed Phase)

Definitions Based on Size

Nanosize (Nanophase)

A special state of subdivision implying that the *particles* (or atomic clusters) have average dimensions smaller than

roughly 100 nm, and exhibit properties not normally associated with the bulk phase (e.g., quantum optical effects).

Colloid

State of subdivision implying that the *particles* have at least in one direction a dimension roughly between 1 nm and 1 μm . Colloids are significantly affected by *Brownian motion* when suspended in a liquid.

Ultrafine

State of subdivision implying that the *particles* have in any given direction a maximum dimension lying roughly between 1 μm and 10 μm .

Fine (Subsieve Range)

State of subdivision implying that the *particles* have in any given direction a maximum dimension less than roughly 37 μm .

Coarse (Sieve Range)

State of subdivision implying that the *particles* have in any given direction a dimension greater than roughly 37 μm .

Granule

State of subdivision generally referring to dry particulates with dimensions lying roughly in the 50 μm to 200 μm range; typically, granules are *aggregates* of finer particles produced by spray-drying. Granulation is performed for ease of handling during subsequent consolidation operations.

Definitions Based on Structure

Particle

Any condensed-phase tridimensional discontinuity in a dispersed system may generally be considered a particle; e.g., *droplets* in an *emulsion* or solids

dispersed in a liquid. The term is normally used in reference to solid materials. An *aggregate* may also be regarded as a particle.

Droplet

Liquid-phase *particle* in an *emulsion* or *aerosol*.

Particulate

Composed of distinct *particles*.

Primary Particle

Smallest identifiable subdivision in a *particulate* system. Primary particles may also be subunits of *aggregates*.

Microsphere

Refers to a spherical *particle* in the micrometer size range.

Aggregate

A cohesive mass consisting of *particulate* subunits.

Hard-Aggregate

An *aggregate* that cannot be easily redispersed by the application of moderate mechanical agitation (shaking, stirring, or ultrasonication) and/or mild chemical treatment. Hard-aggregates consist of subunits that have been chemically bonded or *fused*.

Agglomerate

In a *suspension*, an *aggregate* held together by physical or electrostatic forces.

Coagulate (Coagulum)

In a *suspension*, an *aggregate* formed by the addition of electrolyte.

Floc

In a *suspension*, an *aggregate* formed by the addition of a polymer. Flocs are

generally characterized by a loose structure (low density).

Powder

A relatively dry, undispersed accumulation of *particulate* matter with a macroscopic consistency.

Gel

Bicontinuous structure with a solid and a liquid component. The solid network may consist of *particles* or polymers, held together by covalent, ionic, or dispersion (physical) forces. The network may be elastic, viscoelastic, or plastic. The scale of the mesh of the network (distance between cross links) is of *colloidal* dimensions.

Aerogel

A porous solid produced from a *gel* in such a way that very little shrinkage occurs. Typically, the term refers to materials made by supercritical extraction of the solvent, although structurally equivalent materials can be made under ambient conditions by increasing network stiffness and/or elastic recovery, and by reducing interfacial tension.

Alcogel

A *gel* containing an alcoholic liquid phase.

Hydrogel

A *gel* containing an aqueous liquid phase.

Xerogel

Porous solid made by drying a *gel* under subcritical conditions.

Related Terms

Average Agglomeration Number (AAN)

An estimate of the degree of *agglomeration* in a *suspension*. AAN is

the average number of *primary particles* contained within an *agglomerate*. AAN is calculated from the ratio of the median particle size, as determined by, for example, light scattering, *sedimentation* or electrical zone sensing techniques, to the average equivalent spherical volume (V_{BET}) given by the BET gas adsorption method, such that:

$$\text{AAN} = \frac{V_{50}}{V_{\text{BET}}} = \left(\frac{D_{50} \cdot \text{SSA} \cdot \rho}{6} \right)^3$$

where V_{50} is the equivalent spherical volume calculated from the median diameter, D_{50} in μm , SSA is the specific surface area in m^2/g and ρ is the particle density in g/cm^3 .

Equivalent Spherical Diameter

The diameter of a sedimenting particle determined from Stokes' law and assuming a spherical shape. The term is sometimes used in conjunction with other measurement techniques and theoretical constructs, where spherical geometry is assumed.

Fractal

A structure that has an irregular geometry under all scales of observation (i.e., it is non-Euclidian). The fractal dimension of a species, D_f , is the exponent to which a characteristic length scale must be raised to obtain proportionality with the overall size of the species. Destabilized suspensions tend to form aggregates with fractal structures. In this case, D_f has a value lying between 1 and 3, where $D_f=3$ is a fully dense object.

Minimum Particle Size (MPS)

An experimental quantity operationally defined as the minimum *particle* size that can be achieved by a particular *dispersion* process as determined by an appropriate measurement technique. The

characteristic dimension used in determining the MPS should be clearly noted (e.g., mean size, median size, modal size, etc.).

Ultimate Working Unit

An individual *particle* or group of particles that retains its structure throughout a *dispersion* process and subsequent application. See also *minimum particle size*.

Recommendations

Floccule

It is recommended that this term not be used in the ceramic literature. (see *Floc*)

Hard, Soft

With the exception of the defined term *hard-aggregate*, it is recommended that such adjectives be avoided in the context of dispersed phase structure. If their use is deemed necessary to convey material-specific information, then the author should make a clear statement that defines the meaning and extent of usage.

2.3 Association and Dissociation Processes

Association Processes

Aggregation

A general term defined as any process by which particles collect to form a cohesive mass or cluster; the resulting structure is called an *aggregate*.

Agglomeration

Formation of *aggregates* in a *suspension* through physical (van der Waals, hydrophobic) or electrostatic forces. The resulting structure is called an *agglomerate*.

Coagulation

A specific type of *agglomeration* in which formation of *aggregates* is induced by the addition of electrolyte to a *suspension*. The resulting structure is termed the *coagulate* or *coagulum*, while the electrolyte additive is termed the *coagulant*.

Flocculation

Formation of *aggregates* in a *suspension* mediated by polymeric species, that are either attached to the particles or exist freely in the suspending medium. The resulting structure is called a *floc*, while the polymer additive is termed a *flocculant*. Polymer bridging is a flocculation process.

Gelation

Formation of a continuous (space-filling) solid network characterized by a finite static shear modulus (stress/strain ratio); results from percolation of bonds between particles or polymers. The resulting structure is termed a *gel*.

Fusion

Process by which *particles* form irreversibly bonded structures; often characterized by the appearance of interparticle necks. (see also *hard-aggregates*)

Heteroagglomeration, Heterocoagulation, Heteroflocculation

Generally refers to the *aggregation* of dissimilar *particles*; in ceramic applications, the formation of *aggregates* by the cohesion between particles of different materials (e.g., alumina and silica).

Orthokinetic Aggregation

The process of *aggregation* induced by hydrodynamic motions, such as stirring,

sedimentation, or convection.

Perikinetic Aggregation

The process of *aggregation* induced by *Brownian motion*.

Sol-gel

Process for making a *gel* from *colloidal* or molecular precursors.

Dissociation Processes

Deagglomeration

Reversal of *agglomeration*, i.e., the dispersion of *agglomerates* to form a *suspension*.

Deflocculation

Reversal of *flocculation*, i.e., the dispersion of *flocs* to form a *suspension*.

Comminution

Breaking down large pieces to the required size; term commonly used in association with milling of ceramic slurries.

Peptization

Refers to the reversal of *agglomeration* by the addition of a strong acid or strong base, such as HCl or NaOH.

Related Terms

Diffusion-Limited Rate

Refers to a rate of *aggregation* corresponding to the frequency of encounter (collision rate) of the *particles*. Each collision results in particle adherence (i.e., a sticking probability equal to 1). The rate of encounter is controlled by the diffusion rate, which depends on the viscosity of the medium, the dimensions of the particles, and the concentration of the particles.

Reaction-Limited Rate

Refers to a rate of *aggregation* that is controlled by the reactivity of the *particles* (i.e., the frequency of collisions resulting in particle sticking). Usually characterized by a sticking probability much less than 1. A low sticking probability results from the presence of an energy barrier.

Syneresis

Spontaneous shrinking of a gel with exudation of liquid.

Ultrasonication

Application of high-energy, high-frequency sound to a *suspension* in order to disperse *aggregates*. Dispersion is thought to arise from the energy released during fluid cavitation.

Recommendations

Sonication, Sonification

It is recommended that these terms not be used in the ceramic literature. (see *Ultrasonication*)

2.4 Dispersion Stability

States of Stability

Colloidal Stability

A physical state that characterizes the relative ability of *colloids* to remain dispersed in a liquid; *suspensions* that do not *aggregate* at a significant rate are said to be colloiddally stable. The precise connotation depends on the time frame under consideration. Colloidal stability is a form of *kinetic stability*, and is therefore considered a metastable thermodynamic state. From this perspective, *aggregation* may be described as a transition from a metastable to a stable state, occurring at

rates that depend on the magnitude of the activation energy barrier that separates them.

Kinetic Stability

Most dispersed systems are thermodynamically unstable, relative to their separate bulk phases; however, a dispersion may exist for an appreciable length of time and therefore exhibit kinetic stability. The term may be used in reference to various destabilizing processes, e.g., *aggregation*, coalescence, or *sedimentation*.

Stable Suspension

A *suspension* that has sufficient *kinetic stability* to prevent the occurrence of significant *aggregation* as measured over a relevant time frame. Stability may be ascertained by suitable experimental means, such as *particle* size, turbidity, or *sedimentation* measurements.

Unstable Suspension

A *suspension* that lacks *kinetic stability* as measured over a relevant time frame; a highly unstable suspension is one that is subject to rapid (*diffusion-limited*) *aggregation*.

Stability Mechanisms

Electrostatic Stabilization

Mechanism in which *aggregation* is inhibited by the presence of a mutually repulsive electrostatic potential that surrounds each *particle*.

Steric Stabilization

Mechanism in which *aggregation* is inhibited by the presence of an adsorbed polymer layer that is firmly anchored to the *particle* surface so as not to desorb during collisions. In general, a *steric stabilizing* agent has one portion of its

structure that exhibits low solubility in the *dispersion* medium and/or high affinity for the particle surface, and the other portion is soluble in the medium.

Electrosteric Stabilization

Mechanism in which *aggregation* is inhibited by the combined effects of *electrostatic* and *steric stabilization*. Usually associated with the *adsorption* of *polyelectrolytes* onto the *particle* surface.

Depletion Stabilization

Mechanism in which *aggregation* is inhibited by the presence of free (non-adsorbed) polymer due to the creation of high-energy depletion zones (i.e., depleted of polymer compared to the bulk solution) between closely interacting *particle* surfaces.

Interaction Terms

DLVO

An abbreviation for a theory of the stability of *colloidal dispersions* describing the pair-wise interaction between charged *particles* in a dielectric medium. The theory, derived independently by Derjaguin and Landau, and by Verwey and Overbeek, calculates the opposing effects of attractive van der Waals forces and repulsive electrostatic forces on the *interaction potential*.

Interaction Potential

The potential free energy between two surfaces, typically presented as a function of separation distance. By convention, a positive potential is mutually repulsive and a negative potential is mutually attractive.

Primary Maximum

The first appearance of a maximum in the *interaction potential energy* curve with

increasing separation distance. The primary maximum results from the fact that repulsive and attractive forces decay at different rates as a function of separation distance. In *DLVO* theory, a large primary maximum acts as an energy barrier, preventing *aggregation* of *particles* into the *primary minimum*.

Primary Minimum

The first appearance of a minimum in the *interaction potential* curve with increasing separation distance. The primary minimum results from the fact that repulsive and attractive forces decay at different rates as a function of separation distance. In *DLVO* theory, a deep (negative) primary minimum acts as an energy well, allowing *particles* to adhere and resulting in a loss of *colloidal stability*.

Secondary Minimum

A shallow energy minimum (usually of the order of a few *kT*) in the *interaction potential* curve occurring at relatively large separation distances beyond that of the *primary maximum*. In the presence of such an energy well, secondary minimum *aggregation* may occur. Because of the shallow nature of the secondary minimum, the *aggregates* formed are held together weakly and as such tend to be *unstable* toward rather small energy inputs such as stirring.

Born (Hard Core) Repulsion

As two surfaces are brought into close contact, the attractive van der Waals force between them increases continuously. At some point in their approach, the electron clouds of the two surfaces begin to overlap, giving rise to a repulsive force termed the Born or hard core repulsion. This results in a steep increase in the *interaction potential* curve

at very small interatomic separation distances, becoming effectively infinite when interpenetration occurs.

Solvation (Structural) Forces

Non-DLVO forces that occur at extremely small separation distances (typically a few molecular diameters) when *particles* interact through an intervening fluid medium. These forces arise whenever liquid molecules are induced to order into quasi-discrete layers between surfaces, and can result in a monotonically increasing (repulsive), monotonically decreasing (attractive), or oscillatory *interaction potential*. In aqueous solvents these forces may be referred to as hydration forces.

Hamaker Constant

In the case of *particle* interactions, a material constant that measures the relative strength of the attractive van der Waals forces between two surfaces. Particles interacting through an intervening fluid medium will experience a reduced attractive potential due to the presence of the third component.

Hard Sphere Interaction

A largely theoretical construct in which the *interaction potential* between approaching *particles* is assumed to equal zero, except upon contact where it goes abruptly to infinity (i.e., no interpenetration occurs).

Noninteracting

If no barrier to *particle* approach, contact and adherence exists, the particles are said to be noninteracting. If the *primary minimum* is sufficiently deep, every collision will result in particles sticking together. The rate of *aggregation* will then be kinetically controlled (*diffusion-limited rate*).

Related Terms

Critical Coagulation Concentration (ccc)

The molar concentration of electrolyte, C_0 , necessary to induce rapid (*diffusion-limited*) *aggregation*. Experimentally determined by extrapolation of $\ln W$ versus $\ln C_0$ to $\ln W=0$, where W is the *stability ratio*.

Coagulant

An electrolyte additive that induces *coagulation* in a *suspension*.

Schulze-Hardy Rule

An empirical rule summarizing the general tendency of the *critical coagulation concentration* to vary inversely with the sixth power of the *counterion* charge number of added electrolyte.

Lyotropic Series

An ordered series of ions indicating, in decreasing order, their effectiveness in influencing the behavior of *colloidal dispersions*. Typically associated with an ion's relative propensity to *coagulate* a dispersion.

Stability Ratio

Ratio of the *diffusion-limited* to *reaction-limited rate* constants for *aggregation*. A large ratio indicates a high degree of *colloidal stability*, whereas a ratio of unity indicates that diffusion-limited conditions prevail and the system is *colloidally unstable*. The rate constants are determined experimentally from the initial rates of aggregation. Usually denoted by the symbol, W .

Defoaming (Antifoaming) Agent

A *surfactant* that when present in small amounts prevents the formation of a foam or aides in the coalescence of bubbles.

Dispersing Agent (Stabilizing Agent, Dispersant)

A substance that when present in small amounts facilitates the dispersion of *aggregates* and improves the *kinetic stability* of *particles*. For example, *polyelectrolytes* are often used as dispersing agents in ceramic processing.

Surface Active Agent (Surfactant)

A substance that lowers the interfacial tension between the solution in which it is dissolved, and other phases which are present (e.g., solid *particles* in a *suspension*), and, accordingly, is positively adsorbed at the *interface*.

Polyelectrolyte

A macromolecular substance that, on dissolving in water or other ionizing solvent, dissociates to give polyions (polycations or polyanions) – multiply charged ions – together with an equivalent amount of *counter ions*. A polyelectrolyte can be a polyacid, a polybase, a polysalt, or a polyampholyte. Frequently used as *dispersing agents* in ceramic *slurries*.

Sedimentation

The settling of suspended *particles* or *droplets* due to the influence of gravity or an applied centrifugal field.

Sedimentation Volume

The volume of *particulate* sediment formed in a *suspension*. If the sediment is formed in a centrifugal field, the strength of this field should be explicitly indicated, otherwise normal gravity is understood.

Brownian (Thermal) Motion

Random fluctuations in the density of molecules in a liquid, due to thermal energy, cause other molecules and small dispersed *particles* to move along random pathways. This random motion is termed Brownian motion, and is most noticeable for *colloidal* particles.

Coacervation

When a *colloidal suspension* loses stability, a separation into two liquid phases may occur. This process is termed coacervation. The phase that is more concentrated in the colloid is the coacervate, and the other phase is the equilibrium solution.

Recommendations

Deflocculant, Dispersing Aid

It is recommended that these terms not be used in the ceramic literature. (see *Dispersing Agent*)

2.5 Interfacial and Electrokinetic Properties

The Interface

Interface

A boundary between two immiscible phases, at least one of which is condensed. Experimentally, the portion of the sample through which the first derivative of any concentration versus location plot has a measurable departure from zero. In a *suspension*, the region of contact between the *particle* surface and the suspending medium.

Interfacial Region (Interphase)

The region that exists between two phases where the properties vary from those in the bulk.

Surface Region

The tridimensional region, extending from the free surface of a condensed phase towards the interior, where the properties differ from the bulk.

Electrical Double Layer (EDL)

The term describes the non-random array of ions at an *interface* in which two oppositely charged layers coexist. For particles dispersed in a fluid, the EDL consists of the surface charge and the solution charge. The solution charge may be further subdivided into *Stern* and *diffuse* layers, which is often referred to as the triple layer model.

Double Layer Thickness

Length characterizing the decrease of potential with distance from a charged *interface*. Typically defined as $1/\kappa$, where κ is the *Debye-Hückel parameter*. For low potentials it represents the distance over which the potential falls to $1/e$, or about one third, of the value of the surface potential.

Diffuse Layer

The region surrounding a suspended *particle* in which non-specifically adsorbed ions are accumulated and distributed by the opposing action of the electric field and *thermal motion*.

Stern Layer (Compact Layer)

Counter and *co-ions* in immediate contact with a surface are said to reside in the Stern layer, and form with the fixed surface charge a molecular capacitor. Often equated with the immobile portion of the *electrical double-layer* that exists inside the *shear plane*.

Inner Helmholtz Plane (IHP)

At a charged interface, an imaginary plane representing the distance of closest

approach of desolvated ions to the surface, and containing the ions or molecules that are specifically adsorbed.

Outer Helmholtz Plane (OHP)

At a charged interface, an imaginary plane representing the distance of closest approach of solvated (hydrated) ions to the surface. Often equated with the position of the *shear plane*.

Shear Plane (Plane of Shear, Surface of Shear)

In calculating the *electrokinetic potential* from electrokinetic phenomena it is often assumed that a sharp plane separates the liquid adhering to the solid surface from the mobile liquid. This imaginary plane is considered to lie close to the solid surface.

Adsorption Processes

Adsorption

The process by which a substance is accumulated at an *interface* or in an *interfacial region*. Should not be confused with absorption, which denotes accumulation inside a material or phase.

Adsorbate

A substance that is adsorbed at the *interface* or into the *interfacial region* of a substrate material, or *adsorbent*.

Adsorbent

The substrate material onto which a substance is adsorbed.

Adsorption Isotherm

The relationship between the equilibrium quantity of a substance adsorbed and the composition of the bulk phase, at constant temperature.

Specific Adsorption

Ions are specifically adsorbed when they are present in the *Stern layer* in amounts that exceed those expected from simple electrostatic considerations. Empirically, ions that are specifically adsorbed have a noticeable effect on the *isoelectric point*.

Non-Specific Adsorption

Ions are non-specifically adsorbed when they are kept in the *interphase* only by long-range coulombic interactions. They are believed to retain their solvation shell and in the position of closest approach to the interface they are separated from it by one or more solvent molecular layers. Empirically, ions that are non-specific (*indifferent*) have no measurable effect on the value of the *isoelectric point*.

Chemical Adsorption (Chemisorption)

Molecules are chemically adsorbed when they exist within the *Stern layer* and form bonds with the surface groups, which have a significant valence contribution. Empirically, ions that are chemically adsorbed have a noticeable effect on the *isoelectric point* of a *suspension* and exhibit a significant enthalpy (heat of adsorption).

Physical Adsorption (Physisorption)

Adsorption in which the forces involved are intermolecular (i.e., van der Waals, hydrogen bonding) of the same kind as those responsible for the non-ideality of real gases and the condensation of vapors, and which do not involve a significant change in the electronic orbital patterns of the species involved.

Monolayer Adsorption

Adsorption in which only a single layer of molecules becomes adsorbed at an *interface*. In monolayer adsorption, all

adsorbed molecules are in the position of closest approach to the substrate surface.

Multilayer Adsorption

Adsorption in which more than a single layer of molecules is adsorbed at the *interface*. Molecules adsorbed in excess of *monolayer adsorption* are not in the position of closest approach to the substrate surface.

Coadsorption

The simultaneous *adsorption* of two or more species.

Desorption

The process by which the amount of an adsorbed substance is reduced.

Electrical Properties

Isoelectric Point (iep)

For many ceramic systems, the pH at which dispersed *particles* show no *electrophoretic mobility* and the *zeta potential* has a value of zero. More generally, the pI value at which zeta is zero, where I is the *potential determining ion*.

Point of Zero Charge (pzc)

A *particle* carrying no fixed charge. The precise identification of pzc depends on the definition adopted for surface charge. Typically for ceramic systems, the pH at which hydroxyl and proton *adsorption* is just balanced to cancel net charge; here, the hydroxyl and proton are defined as the charge determining species.

Surface Charge Density

The quantity of electrical charge accumulated at a particle-solution interface, expressed per unit area; usually represented by the symbol σ_0 .

Shear Plane Potential

The potential difference across the mobile part of the *electrical double layer* at a charged solid-liquid *interface*; potential at the *shear plane* during an *electrokinetic* measurement. Synonymous with *zeta potential* for the case of particles suspended in a liquid.

Streaming Potential

When a liquid under a pressure gradient is forced through a capillary or porous plug, excess charges (ions) near the wall are swept along by the liquid creating an accumulation of charge downstream. An electric field is also created, which opposes this accumulation. After a steady state has been established, the measured potential difference across the capillary or plug is called the streaming potential and is related to the pressure gradient and to the *shear plane potential*.

Zeta Potential (Electrokinetic Potential, Shear Plane Potential)

The potential drop, ζ , across the mobile part of the *electrical double layer*, that is responsible for the *electrokinetic* phenomena. ζ is positive if the potential increases from the bulk of the liquid phase towards the *shear plane*. Certain assumptions or estimations regarding the double layer properties must be made in order to calculate ζ from experimental data. It is therefore essential to indicate in all cases which equations have been used in the calculation of ζ . It can be shown, however, that for the same assumptions about the double layer properties, all electrokinetic phenomena must give the same value for the electrokinetic potential.

Potential Determining Ions

Those species of ions that by virtue of their equilibrium distribution between

two phases determine the difference in Galvani potential between these phases. They are often, but not always, identical with the ions that stabilize a *colloidal suspension* formed from these phases.

Co-ions

In systems containing large ionic species (e.g., *colloids*), co-ions are those that, compared to the large ions, have low molecular mass and the same polarity. For instance, in a *suspension* of negatively charged *particles* containing sodium chloride, the chloride ions are co-ions and the sodium ions are *counterions*.

Counterions

In systems containing large ionic species (e.g., *colloids*), counterions are those that, compared to the large ions, have low molecular mass and the opposite polarity. For instance, in a *suspension* of negatively charged *particles* containing sodium chloride, the sodium ions are counterions and the chloride ions are *co-ions*.

Charge Reversal

The process wherein a charged *particle* is caused to assume a new charge of the opposite polarity. Such a change can be brought about by oxidation, reduction, dissociation, *adsorption*, or ion exchange.

Electrokinetic Effects

Electrokinetics

Referring to the relative motions of charged species in an electric field. The field may be applied, or it may be created by the motion of a liquid or adjacent solid phase.

Electro-osmosis

When a liquid moves in response to an applied electric field, while an adjacent

solid phase remains stationary (e.g., in a capillary or porous plug), this is called electro-osmotic flow. Fluid motion is due to the reaction of charged species within the fluid, usually dissolved ions, to the applied field.

Electrophoresis

The motion of charged *particles* in an applied electric field.

Electrophoretic Mobility (Static, Dynamic)

The *electrophoretic* velocity per unit field strength, symbol $\mu_e = v/E$; μ_e is positive if the *particle* moves toward lower potential and negative in the opposite direction. When measured in a d.c. electric field, μ_e is referred to as the static mobility. When measured in a high-frequency field it is referred to as the dynamic mobility, and given the symbol μ_d or $\mu(\omega)$. Dynamic mobility may be a complex quantity at high frequencies.

Electroacoustics

Referring to the electric-acoustic coupling in a fluid containing charged colloids or ions; an effect that is responsible for the *electrokinetic sonic amplitude*, *colloid vibration potential* and *ion vibration potential*.

Acoustophoresis

The induced motion of *particles* subjected to an acoustic field. Charged particles will generate an electric field as a result of this motion (see *ultrasonic vibration potential*).

Ultrasonic Vibration Potential (UVP)

When a sound wave propagates through a fluid containing charged *particles* (ions or *colloids*), coherent *acoustophoretic* motion of the particles creates alternating dipoles that generate a macroscopic

potential difference termed the ultrasonic vibration potential.

Ion Vibration Potential (IVP)

The *ultrasonic vibration potential* of an ionic solution; also known as the Debye effect.

Colloid Vibration Potential (CVP)

The *ultrasonic vibration potential* of a *colloidal suspension*. The resulting potential difference is related to the *dynamic mobility* of the particles; reciprocal effect to *electrokinetic sonic amplitude*.

Electrokinetic Sonic Amplitude (ESA)

When a high-frequency alternating electric field is applied to a *dispersion* of charged *colloids*, the oscillatory *electrophoretic* motion of the *particles* relative to the surrounding medium results in a measurable acoustic field whose amplitude is related to the *dynamic mobility*; reciprocal effect of *colloid vibration potential*. The phase difference between the applied field and the resulting acoustic response can also be used to estimate the particle size distribution.

Related Terms

Amphoteric

Refers to a type of surface in which the same surface group (reactive site) is able to function as both an acid and a base. That is, the site may dissociate to release a proton or accept a proton.

Zwitterionic

Refers to a type of surface in which two distinct surface groups (reactive sites) are present. One is capable of dissociating to release a proton (acid group), and the

other is capable of accepting a proton (base group).

Hydrophilic

May be used to describe the character of interaction of a particular atomic group (or substance) with an aqueous medium. In this usage the term has the relative qualitative meaning of "water loving." The more general term, lyophilic ("solvent loving"), is used to distinguish a class of colloidal systems.

Hydrophobic

The tendency of hydrocarbons (or of lipophilic hydrocarbon-like groups in solutes) to form intermolecular *aggregates* in an aqueous medium, and analogous intramolecular interactions. In this usage the term has the relative qualitative meaning of "water fearing." The more general term, lyophobic ("solvent fearing"), is used to distinguish a class of colloidal systems.

Indifferent (Supporting) Electrolyte

An ionic solution, whose constituents are not electroactive (i.e., they have no significant effect on the surface potential of the material under study; no oxidative or reductive capacity) in the range of applied potentials being studied, and whose *ionic strength* (and, therefore, contribution to the conductivity) is usually much larger than the concentration of an electroactive substance to be dissolved in it. The ions constituting an indifferent electrolyte are said to exhibit no specificity for the *particle* surface.

Ionic Strength

A measure of electrolyte concentration given by $I = \frac{1}{2} \sum c_i z_i^2$, where c_i are the concentrations, in moles per liter, of the individual ions, i , and z_i are their ion

charge numbers.

Debye-Hückel Parameter

A parameter in the Debye-Hückel theory of electrolyte solutions, denoted as κ . For aqueous solutions at 25 °C, $\kappa = 3.288\sqrt{I}$ in reciprocal nanometers, where I is the *ionic strength*. See *Thickness of the Electrical Double Layer*.

Double Layer Compression (Screening)

Increasing *ionic strength* causes the electrical potential near a charged surface to fall off more rapidly with distance. This is referred to as double layer compression or screening, because the *double layer thickness* shrinks as the *Debye-Hückel parameter* increases with increasing ionic strength.

Electroviscous Effects

For *dispersions* of charged *particles*, these are those components of the viscosity connected with the charge on the particles.

Suspension Effect

The Donnan e.m.f. between a *suspension* and its equilibrium liquid. The effect is most commonly encountered with pH measurements in *colloidal suspensions*.

Potentiometric Analysis

Analysis based on the measurement of electrical potential using, for example, a pH or ion-selective electrode. Potentiometry is often combined with *titrimetric analysis* in the determination of *particle* surface charge.

Titrant

The solution containing the active agent with which a *titration* is made.

Titration

The process of determining the amount of a substance A by adding increments of substance B with provision for some means of recognizing the point at which all of A has reacted. This allows the amount of A to be found from the known amount of B added up to this point.

Titrimetric Analysis

Analysis of test sample properties based on *titration*.

3. BIBLIOGRAPHY

3.1 Primary Sources

Compendium of Chemical Terminology – IUPAC Recommendations, Compiled by V. Gold, K.L. Loening, A.D. McNaught, and P. Sehmi, Blackwell Scientific Publications, Oxford, UK, 1987.

L.L. Schramm, *The Language of Colloid and Interface Science – A Dictionary of Terms*, American Chemical Society, Washington, DC, 1993.

R.J. Hunter, *Foundations of Colloid Science*, Volume 1, Oxford University Press, Oxford, UK, 1989.

P.C. Hiemenz and R. Rajagopalan, *Principles of Colloid and Surface Chemistry*, 3rd Edition, Marcel Dekker, NY, 1997.

G.Y. Onoda and L.L. Hench, "Physical Characterization Terminology," Chapter 5, pp. 35-37 in *Ceramic Processing Before Firing*, Edited by G.Y. Onoda and L.L. Hench, John Wiley & Sons, NY, 1978.

3.2 Secondary Sources

Adsorption of Inorganics at Solid-Liquid Interfaces, Edited by M.A. Anderson and A.J. Rubin, Ann Arbor Science Publishers, Ann Arbor, MI, 1981.

Chemical Processing of Ceramics, Edited by B.I. Lee and E.J.A. Pope, Marcel Dekker, NY, 1994.

Sample Preparation for the Determination of Particle Size Distribution of Ceramic Powders, ISO/DIS 14703, 1998.

Particle Size Analysis: Dispersing Agents for Powders in Liquids, ISO Working Document 14887, 1997.

Surface and Colloid Chemistry in Advanced Ceramics Processing, Edited by R.J. Pugh and L. Bergström, Marcel Dekker, NY, 1994.

Ultrasonic and Dielectric Characterization Techniques for Suspended Particulates, Edited by V.A. Hackley and J. Texter, American Ceramic Society, Westerville, OH, 1998.

C.J. Brinker and G.W. Scherer, *Sol-Gel Science*, Academic Press, NY, 1990.

D.F. Evans and H. Wennerström, *The Colloidal Domain*, VCH Publishers, NY, 1994.

E.K. Fischer, *Colloidal Dispersions*, John Wiley & Sons, NY, 1950.

R.J. Hunter, *Zeta Potential in Colloid Science – Principles and Applications*, Academic Press, NY, 1981.

D. Myers, *Surfaces, Interfaces, and Colloids - Principles and Applications*, Chapter 10, "Colloids and Colloidal Stability," VCH Publishers, NY, 1991.

D.H. Napper, *Polymeric Stabilization of Colloidal Dispersions*, Academic Press, NY, 1983.

R.H. Ottewill, "Stability and Instability in Dispersed Systems," *Journal of Colloid and Interface Science*, **58**, 357-373 (1977).

Th.F. Tadros, "Control of the Properties of Suspensions," *Colloids and Surfaces*, **18**, 137-173 (1986).

Acknowledgements

A number of terms were included courtesy of the American Chemical Society from the book by L.L. Schramm. Some definitions contained in the Compendium of Chemical Terminology were used, in part or in whole, courtesy of the International Union on Pure and Applied Chemistry.

List of Reviewers and Contributors

James H. Adair, Merrilea J. Mayo
The Pennsylvania State University,
Particulate Materials Center

Jon A. Casey
IBM, Materials Technology

Robert A. Condrate
Alfred University, New York State
College of Ceramics

*Matthew Frey, William Hunt,
Thomas Wood*
3M Company, Ceramic Technology
Center

*Vincent A. Hackley, Ajit Jillavenkatesa,
George Y. Onoda (retired)*
National Institute of Standards and
Technology, Ceramics Division

Robert J. Hunter
University of Sydney, School of
Chemistry, Australia

George W. Scherer
Princeton University, Department of
Chemical Engineering

Ponisseril Somasundaran
Columbia University, Langmuir Center
for Colloids and Interfaces

Index to Defined Terms

A

AAN. See Average Agglomeration Number
Acoustophoresis, 14
Adsorbate, 11
Adsorbent, 11
Adsorption, 11
 Chemical, 12
 Monolayer, 12
 Multilayer, 12
 Non-Specific, 12
 Physical, 12
 Specific, 12
Adsorption Isotherm, 11
Aerogel, 4
Aerosol, 1
Agent
 Antifoaming, 10
 Defoaming, 10
 Dispersing, 10
 Stabilizing, 10
 Surface Active, 10
Agglomerate, 4
Agglomeration, 5
Aggregate, 4
Aggregation, 5
 Orthokinetic, 6
 Perikinetic, 6
Alcogel, 4
Amphoteric, 14
Average Agglomeration Number, 4

B

Born, 8
Brownian Motion, 10

C

ccc. See Critical Coagulation Concentration
Charge Reversal, 13
Chemisorption, 12
Coacervation, 10
Coadsorption, 12
Coagulant, 9
Coagulate. See Coagulum
Coagulation, 6
Coagulum, 4
Co-ions, 13
Colloid, 3
Comminution, 6
Concentration. See Relative Concentration Terms
Counterions, 13
Critical Coagulation Concentration, 9
CVP. See Potential, Colloid Vibration

D

Deagglomeration, 6
 Debye effect. See Potential, Ion Vibration
Debye-Hückel Parameter, 15
Deflocculant. See Agent, Dispersing
Deflocculation, 6
Desorption, 12
Dispersant, 10
Dispersing Aid. See Agent, Dispersing
Dispersion, 2
DLVO, 8
Double Layer Compression, 15
Droplet, 4

E

EDL. See Electrical Double Layer
Electrical Double Layer, 11
Electroacoustic, 14
 electroactive. See Indifferent Electrolyte
Electrokinetic, 13
Electrokinetic Sonic Amplitude, 14
Electro-osmosis, 13
Electrophoresis, 14
Electroviscous Effects, 15
Emulsion, 2
Equivalent Spherical Diameter, 5
ESA. See Electrokinetic Sonic Amplitude

F

Floc, 4
Flocculation, 6
Floccule, 5
Fractal, 5
Fusion, 6

G

Gel, 4
Gelation, 6
Granule, 3

H

Hamaker Constant, 9
Hard Core. See Born Repulsion
Hard Sphere Interaction, 9
Hard-Aggregate, 4
Heteroagglomeration, 6
Heterocoagulation, 6
Heterodisperse, 2
Heteroflocculation, 6
 hydration forces. See Solvation Forces

Hydrogel, 4
Hydrophilic, 15
Hydrophobic, 15
Hydrosol, 2

I

iep. See Isoelectric Point
IHP. See Inner Helmholtz Plane
Indifferent Electrolyte, 15
Interface, 10
Interfacial Region, 10
Interphase, 10
Ionic Strength, 15
Isoelectric Point, 12
IVP. See Potential, Ion Vibration

L

Layer
 Compact, 11
 Diffuse, 11
lyophilic. See Hydrophilic
lyophobic. See Hydrophobic
Lyotropic Series, 9

M

Microsphere, 4
Minimum Particle Size, 5
Mobility
 Dynamic, 14
 Electrophoretic, 14
 Static, 14
Monodisperse, 2
MPS. See Minimum Particle Size

N

Nanoparticle, 3
Noninteracting, 9

O

OHP. See Plane, Outer Helmholtz
Organosol, 2

P

Particle, 3
 Coarse, 3
 Fine, 3
 Primary, 4
 Ultrafine, 3
Particulate, 4
Peptization, 6
Phase
 Continuous, 2
 Discontinuous, 2
 Dispersed, 2

Liquid, 2
 Particulate, 2
 Solid, 2
Physisorption, 12
Plane
 Inner Helmholtz, 11
 Outer Helmholtz, 11
Plane of Shear, 11
Point of Zero Charge, 12
Polydisperse, 2
Polyelectrolyte, 10
Potential

 Colloid Vibration, 14
 Electrokinetic, 13
 Interaction, 8
 Ion Vibration, 14
 Shear Plane, 13
 Streaming, 13
 Ultrasonic Vibration, 14
 Zeta, 13
Potential Determining Ions, 13
Potentiometric Analysis, 15
Powder, 4
Primary Maximum, 8
Primary Minimum, 8
pzc. See Point of Zero Charge

R

Rate
 Diffusion-Limited, 6
 Reaction-Limited, 7
Relative Concentration Terms, 3

S

Schulze-Hardy Rule, 9
Screening, 15
Secondary Minimum, 8
Sedimentation, 10
Sedimentation Volume, 10
Shear Plane, 11
Sieve Range. See Particle, Coarse
Slip, 2
Slurry, 2
Sol, 2
Sol-gel, 6
Solvation Forces, 9
Sonication, 7
Sonification, 7
Stability
 Colloidal, 7
 Kinetic, 7
Stability Ratio, 9
Stabilization
 Depletion, 8
 Electrostatic, 7
 Electrosteric, 8
 Steric, 7
Structural Forces, 9
Subsieve Range. See Particle, Fine
Supporting Electrolyte, 15

Surface Charge Density, 12

Surface of Shear, 11

Surface Region, 11

Surfactant, 10

Suspension, 2

Stable, 7

Unstable, 7

Suspension Effect, 15

Syneresis, 7

T

Thermal Motion, 10

Titrant, 15

Titration, 16

Titrimetric Analysis, 16

triple layer model. *See* Electrical Double Layer

U

Ultimate Working Unit, 5

Ultrasonication, 7

UVP. *See* Potential, Ultrasonic Vibration

W

Well-Dispersed, 3

X

Xerogel, 4

Z

Zwitterionic, 14

NIST *Technical Publications*

Periodical

Journal of Research of the National Institute of Standards and Technology—Reports NIST research and development in those disciplines of the physical and engineering sciences in which the Institute is active. These include physics, chemistry, engineering, mathematics, and computer sciences. Papers cover a broad range of subjects, with major emphasis on measurement methodology and the basic technology underlying standardization. Also included from time to time are survey articles on topics closely related to the Institute's technical and scientific programs. Issued six times a year.

Nonperiodicals

Monographs—Major contributions to the technical literature on various subjects related to the Institute's scientific and technical activities.

Handbooks—Recommended codes of engineering and industrial practice (including safety codes) developed in cooperation with interested industries, professional organizations, and regulatory bodies.

Special Publications—Include proceedings of conferences sponsored by NIST, NIST annual reports, and other special publications appropriate to this grouping such as wall charts, pocket cards, and bibliographies.

National Standard Reference Data Series—Provides quantitative data on the physical and chemical properties of materials, compiled from the world's literature and critically evaluated. Developed under a worldwide program coordinated by NIST under the authority of the National Standard Data Act (Public Law 90-396). NOTE: The Journal of Physical and Chemical Reference Data (JPCRD) is published bimonthly for NIST by the American Chemical Society (ACS) and the American Institute of Physics (AIP). Subscriptions, reprints, and supplements are available from ACS, 1155 Sixteenth St., NW, Washington, DC 20056.

Building Science Series—Disseminates technical information developed at the Institute on building materials, components, systems, and whole structures. The series presents research results, test methods, and performance criteria related to the structural and environmental functions and the durability and safety characteristics of building elements and systems.

Technical Notes—Studies or reports which are complete in themselves but restrictive in their treatment of a subject. Analogous to monographs but not so comprehensive in scope or definitive in treatment of the subject area. Often serve as a vehicle for final reports of work performed at NIST under the sponsorship of other government agencies.

Voluntary Product Standards—Developed under procedures published by the Department of Commerce in Part 10, Title 15, of the Code of Federal Regulations. The standards establish nationally recognized requirements for products, and provide all concerned interests with a basis for common understanding of the characteristics of the products. NIST administers this program in support of the efforts of private-sector standardizing organizations.

Order the following NIST publications—FIPS and NISTIRs—from the National Technical Information Service, Springfield, VA 22161.

Federal Information Processing Standards Publications (FIPS PUB)—Publications in this series collectively constitute the Federal Information Processing Standards Register. The Register serves as the official source of information in the Federal Government regarding standards issued by NIST pursuant to the Federal Property and Administrative Services Act of 1949 as amended, Public Law 89-306 (79 Stat. 1127), and as implemented by Executive Order 11717 (38 FR 12315, dated May 11, 1973) and Part 6 of Title 15 CFR (Code of Federal Regulations).

NIST Interagency or Internal Reports (NISTIR)—The series includes interim or final reports on work performed by NIST for outside sponsors (both government and nongovernment). In general, initial distribution is handled by the sponsor; public distribution is handled by sales through the National Technical Information Service, Springfield, VA 22161, in hard copy, electronic media, or microfiche form. NISTIR's may also report results of NIST projects of transitory or limited interest, including those that will be published subsequently in more comprehensive form.

U.S. Department of Commerce
National Institute of Standards
and Technology
Gaithersburg, MD 20899-0001

Official Business
Penalty for Private Use \$300